

1
2
3
4
5
6
7
8
9
10
11
12
13

**INDEX AND STRENGTH CHARACTERISTICS OF
RESIDUAL LATERITIC SOILS FROM SOUTH-
WESTERN NIGERIA**

N.O. Adebisi¹, D. Kalumba^{2*} and F. O. Akintayo³

¹Department of Earth Sciences, Olabisi Onabanjo University, Nigeria

²Department of Civil Engineering, University of Cape Town, South Africa

³Department of Civil Engineering, University of Ibadan, Ibadan, Nigeria

* Tel.: +27 21 6502590
E-mail address: denis.kalumba@uct.ac.za

14 **ABSTRACT (ARIAL, BOLD, 11 FONT, LEFT ALIGNED, CAPS)**
15

Aim: To test consistency of residual lateritic soil of migmatite gneiss of the gneiss complex from Abeokuta and Ibadan of South-western Nigeria for utilisation as sustainable road construction materials.

Study design: A reconnaissance survey was carried out for location and identification of major outcrops around the area. The test pit investigative method was adopted by profiling the subsoil 3 m below the ground surface. Disturbed soil samples were used for the determination of the index properties, while shear strength parameters were determined on undisturbed soil specimens.

Place and Duration: The study was undertaken in Ibadan and Abeokuta, Southwest, Nigeria between Dec 2011 and March 2012.

Methodology: All the procedures adopted for the tests were in accordance with the British Standard 1377. The specific gravity of the samples was determined using the pycnometer method. The sieve analysis and hydrometer methods were employed to study the particle size distribution of coarse and fine soils respectively, while the Atterberg tests were performed to investigate the consistency limits of fine grained soils.

Results: The lateritic soils are predominantly well-graded silty, clayey sands with average specific gravity and clay content of 2.72 and 31.8% respectively. The colloidal activity of the clay ranged up to 2.25, signifying considerable volume change when wetted and large shrinkage when dried. Kaolinite and Ca montmorillonite are the principal clay minerals present in the soils. The fines are silty clays of low to medium plasticity.

Conclusion: Fairly strong inverse relationship was established between undrained cohesion and flow index, implying that the rate of loss of shearing stress of the soils is comparatively a function of increase in their moisture content.

16
17 *Key words: residual lateritic soil, clay, consistency, flow index.*
18

19
20 **1. INTRODUCTION**
21

22 Residual lateritic soils are abundant in Abeokuta and Ibadan, South-western Nigeria.
23 This is as a result of the action of water and other weathering agents including tropical
24 climate on the Precambrian rocks of the basement complex in the gneiss complex area
25 of the region, which are mainly gneisses [1, 2,]. Lateritic soils are commonly used as
26 subbase and base materials in road construction works due to their engineering
27 properties. Abeokuta is 78 km on the older trunk road from Lagos to Ibadan, while
28 Ibadan is Ibadan is located at 128 km inland northeast of Lagos.

29 Many studies have been carried out to relate the engineering properties of residual
30 lateritic soils to the geological formation of the parent rock in South-western Nigeria. It
31 has been reported that geological factors needed due consideration when searching for
32 suitable soils for road projects [3]. Studies have also shown that the clay content, as well
33 as its mineralogical composition, controlled the engineering performance of laterised
34 soils [4, 5,].

35 This investigative study carried out in Abeokuta established that the origin of the parent
36 rock strongly affects the strength properties of laterised soils stabilised with lime [6].
37 Well-graded reddish brown, sandy-silt-clay of medium plasticity and compressibility with
38 some little contents of clay of inorganic origin and higher plasticity index was reported
39 from the various tests carried out on quartzschist and granite derived lateritic soils of the
40 area [7].

41 Clay-sized particles constitute a vital portion of lateritic soils and play an important role in
42 their plasticity and cohesive strength. This study was therefore carried out to determine
43 the relationship between flow index and cohesive strength of residual lateritic soils in the
44 South-western Nigeria.

2. METHODOLOGY

2.1 Field Mapping and Sample Collection

A reconnaissance survey was carried out for location and identification of major outcrops around the study area (see Figure 1). The positions of the investigation pits were then established after pedological mapping to identify profiles with appreciable thicknesses for sampling. The test pit, as an investigation technique, was selected because it provided a very quick and economical method of obtaining substantially reliable samples and information, making it very suitable in profiling the pits. In addition, the soils were competent enough for the pit side-walls to remain stable during excavation and profiling. Each test pit was dug using a chisel-like digger and excavating the underlying material to a depth of 3.0 m. In the process, soil samples were obtained whenever pit materials changed. At applicable depths, both disturbed and undisturbed soil samples were redeemed from the pit using a hand auger and U-tube core cutters (100 mm in diameter) respectively. This was done taking cognisance of change in nature of the profile. Undisturbed samples were sealed with wax (on either end of the cutter) to avoid any loss of moisture before being transported carefully to the laboratory avoiding any disturbance to the soil structure.

2.2 Laboratory Testing

Disturbed soil samples were used for the determination of the index properties, while shear strength parameters were determined on undisturbed soil specimens. All the procedures adopted for the tests were in accordance with the British Standard 1377 [8]. The specific gravity of the samples was determined using the pycnometer method. The sieve analysis and hydrometer methods were employed to study the particle size distribution of coarse and fine soils respectively, while the Atterberg tests were performed to investigate the consistency limits of fine grained soils. Consistency limits, which included liquid limit (L_L) and plastic limit (L_p), were determined on air-dried soil samples passing through the British standard sieve no. 40 (slot size of 0.425 mm) as highlighted by [9]. The Casagrande method was used for L_L tests as well as the measurement of the consistency index (I_c).

Undrained cohesion (C_u) and angle of shearing resistance (ϕ_u) were both obtained using the undrained triaxial compression apparatus on undisturbed specimens. In each case, the triaxial procedure was followed at different three cell pressures of 50 kN/m², 100 kN/m² and 200 kN/m² in order to obtain the failure envelope on the Mohr-Coulomb graph.


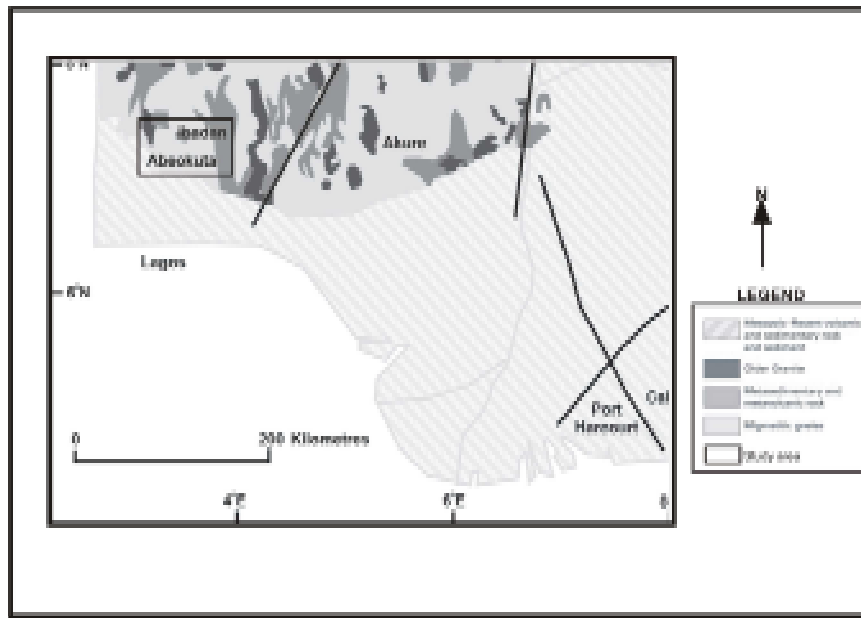


Figure 1: Geological map of South-western Nigeria showing the study area [11]

2.3 Site Geology and Soil Profile


From published geological data, the terrain of South-western Nigeria was known to be underlain by a varying thickness of lateritic profile strata, which emanated from the Precambrian crystalline rocks in the Migmatite-Gneiss Complex and the Older Granites Suite areas [10]. The variable cover of weathered residual soils was confirmed by the sub-surface investigation on the site upon the digging of 3 test pits (1 and 2 from Abeokuta and Ibadan respectively). It revealed uniform sub-soil conditions across the investigation area, that is, there were no significant differences in the depth and thickness of the residual material within the respective lateral distances. Based on visual inspection of the test pits and more specifically, examination of the undisturbed core, the overall consistency of the material was found to be relatively high (medium dense to dense) over the area.

The tropically-weathered residual material occurred as a dense deposit, the bottom of which was established at about 3 m below ground level. The deposit represented an upper silty clayey zone approximately 0.3 m thick, underlain by a sandy silty clay zone and finally into slightly weathered rock. The soil profile generally, comprised sub-rounded weathered, very soft largely intact clayey silt towards the ground level and completely weathered very stiff consolidated brown reddish sandy silty clay. Groundwater was not encountered at all the depths investigated. A full description of the material layers is illustrated in Figure 2.

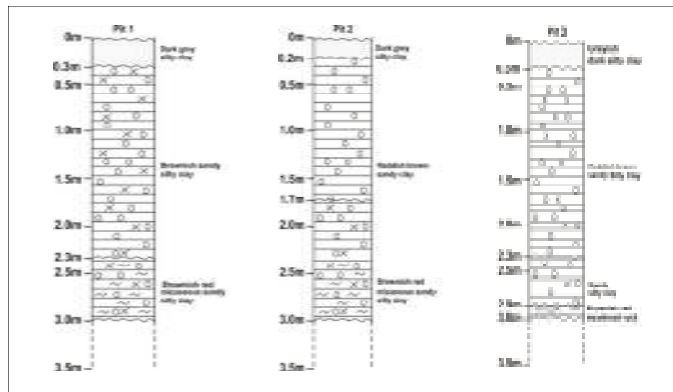

3.0 RESULTS AND DISCUSSION

A typical set of grading curves for the studied soils is shown in Figures 3a, 3b and 3c. The observed range of soil particles sizes present is indicative of a well-graded residual material. On the basis of the British Standard BS 5930 for the Unified Soil Classification System (1981) the studied soils are silty clays, silty sand gravels and clayey silty sands in Pits 1, 2 and 3 respectively. It is apparent that these laterites contain a considerable amount of fines, i.e. silt and clay. Specifically, the average clay contents of 31.8%, 12% and 20.6% are realised in Pits 1, 2 and 3 respectively. This is peculiar to lateritic soils in parts of South-western Nigeria.

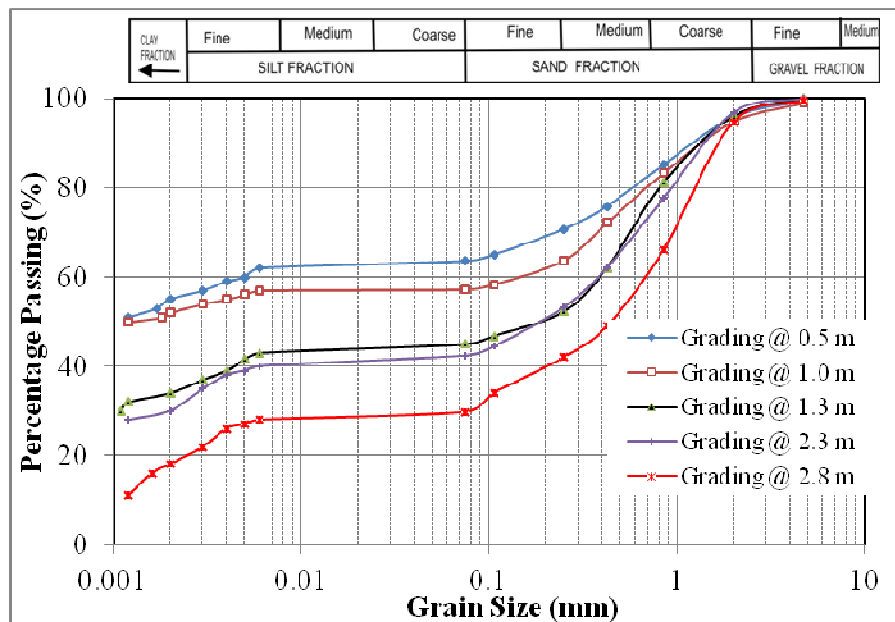

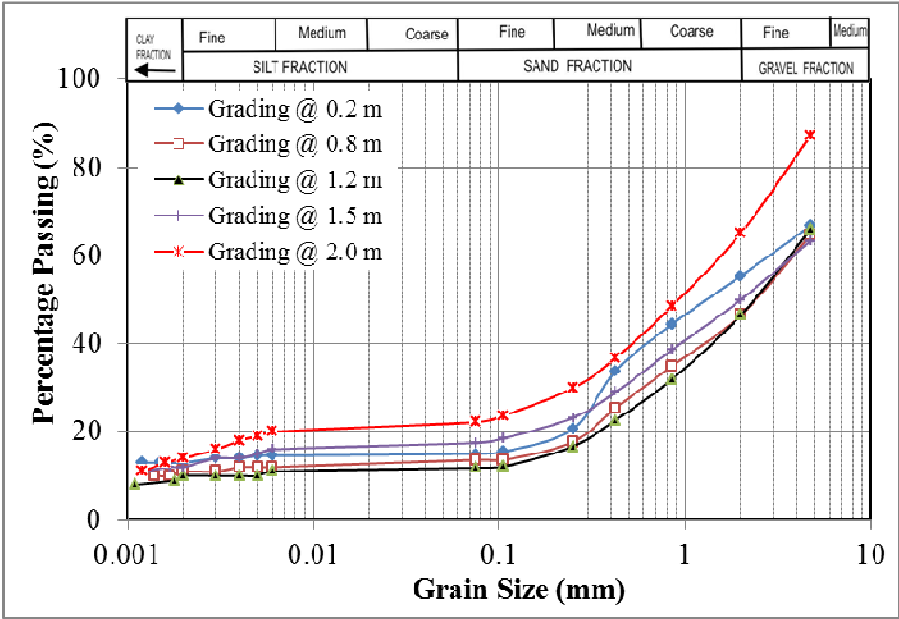


Figure 3b: Grain-size distribution curves for soils from Pit 2

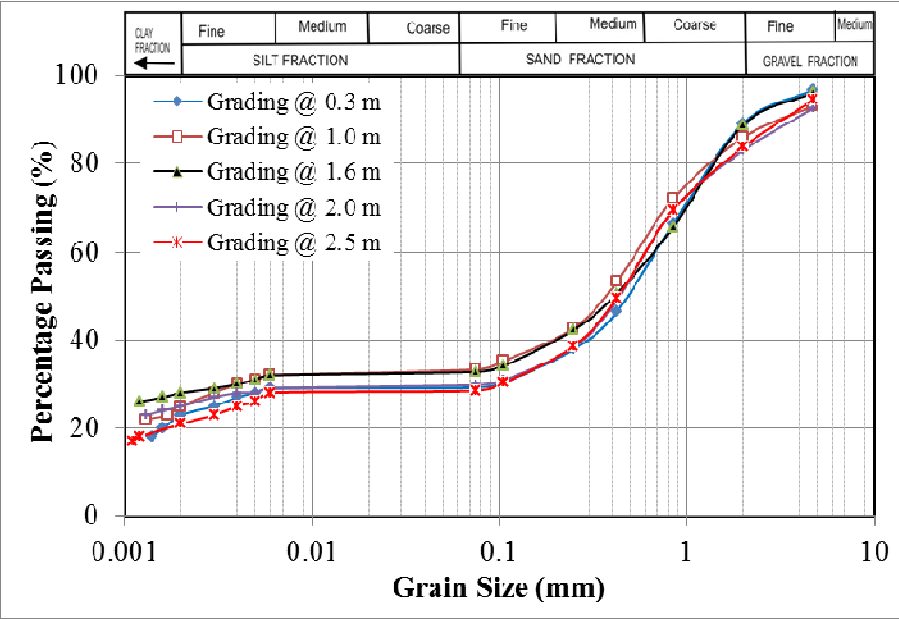


Figure 3c: Grain-size distribution curves for soils from Pit 3

The specific gravity, activity and grading characteristics of the soil are given Table 1. Grain specific gravity (G_s) of the studied soils ranges between 2.64 and 2.76 with a wide range of overlap. It falls within those of gravel, sand, silt and clay sizes. This is consistent with established variations in specific gravity values for lateritic soils of the tropical region [11, 12,13].

In the assessment of lateritic a soil for construction purposes, the colloidal activity (A_c) of its clay content is important to determine. This is evident when considering the manner in

136 which plasticity index relates to the percentage finer than $0.002 \mu\text{m}$ of such soil.
137 Therefore, it is possible to infer the clay mineralogical composition of a soil from the
138 value of colloidal activity of clay content in a lateritic soil. In table 1, the A_c values
139 generally range between 0.18 and 2.25 in all the studied soils. On the basis of the
140 standard established by [16], kaolinite and Ca montmorillonite are inferred to be the
141 principal clay minerals that could be present in the soils, with illite only present in those
142 samples obtained from pit 2. In laterite literature, kaolinite has been established to be the
143 dominant clay mineral with subordinate amount of illite, while montmorillonite is rarely
144 identified in lateritic soils of the Basement Complex. However, [1] identified smectite, of
145 the montmorillonite group in lateritic soils developed over granite and gneiss at depth of
146 3.0 m, where differential settlement of a small magnitude may occur if employed as
147 foundation material. On the other hand, likely unfavourable engineering performances of
148 such soils are swelling and flow [14]. The implication is that the studied soils may
149 undergo foundation settlement when loaded by structures.

150 A detailed consistency limits characteristics of the studied soils is presented in Table 2.
151 Plots of plasticity index (I_p) against corresponding liquid limit (L_L) values on a
152 Casagrande chart [15] show that fines are present as silt and clay of low to nearly high
153 plasticity. The derived consistency limits, which include plasticity index (I_p), consistency
154 index (I_c), liquidity index (I_L), toughness index (I_T) and flow index (I_F), were also
155 estimated and presented in the same Table 3. The consistency index (I_c) values for the
156 studied soils range between 0.36 and 2.92 in the three pits, showing a combination of
157 soft, stiff, solid and hard characteristics. Majority of the studied soils have I_c value less
158 than 2.5, indicating that they are structurally unstable. It follows that virtually 90% of the
159 soils are susceptible to weathering and erosion. Values of liquidity index (I_L) of the
160 residual laterised soils are generally less than zero (-5 to - 0.33). Soils with I_L values
161 within this range are semi-plastic to solid in nature. Toughness index (I_T) of the studied
162 soils fall between 0 and 3, while few of them have I_T values less than 1, indicating friable
163 soils at plastic limit. The swell index (I_s) was greater than 15, which is indicative of low
164 swell soils.

165 The undrained cohesion (C_u) values which measure the rate of shearing strength also
166 vary greatly within each of the sampled pits. They range from 9 kN/m^2 to 16 kN/m^2 in Pit
167 1, 8 kN/m^2 to 19 kN/m^2 in Pit 2 and 10 kN/m^2 to 23 kN/m^2 in Pit 3. The rate of loss of
168 shearing strength upon increase in moisture content of the soils in this study can be
169 related to flow index (I_F). This is considered necessary so as to establish a relationship
170 between C_u and I_F of the soils, and make a categorical statement on how the two
171 parameters vary with each other. A regression plot of I_F against C_u for soils in each of the
172 sampled pits is shown in Figure 4. Fairly strong inverse correlation exists between I_F and
173 C_u of the soils with coefficient of correlation (r) equals - 0.71 in pit2 and - 0.62 in pit3. The
174 best line of fit in each case is defined by $C_u = -0.632 I_F + 26.24$ for soils from pit2 and C_u
175 $= -0.566 I_F + 18.81$ for soils from pit3. Beyond all doubts, cohesion increases with
176 decreasing flow index, except that r' values are not reliable enough to suggest the
177 determination of one property in absence of the other. By and large, the soils will
178 increase in shearing strength only when there is decrease in water content as revealed
179 by the flow index. The problems likely to be caused by such soils in engineering
180 construction will range from swell to flow, leading to foundation settlement.

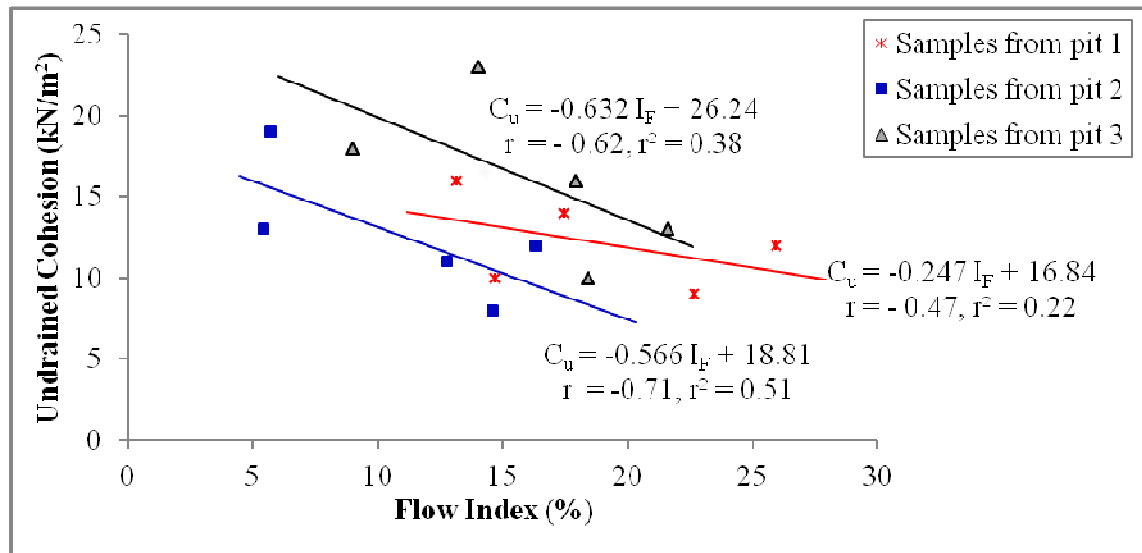


Figure 4: Regression plots of cohesion and flow index of the studied soils

186 **Table 1: Grain-size distribution, activity and specific gravity of the studied soils**

187

Pit No.	Depth (m)	Depth Range (m)	% Clay	% Clay Range	Colloidal Activity of clay (A_c)	A_c Range	Inferred Clay Mineral(s)	% Silt	% Silt Range	% Sand	% Sand Range	% Gravel	% Gravel Range	Specific Gravity (G_s)	G_s Range
1	0.5	0.5– 2.8	51	9 – 51	0.18	0.18 -1.67	Kaolinite, Illite and Ca Montmorillonite	27	26 – 44	18	18 – 42	4	3 – 5	2.72	2.70 – 2.76
	1.0		49		0.27			26		20		5		2.72	
	1.3		28		0.25			38		30		4		2.70	
	2.4		22		0.23			43		32		3		2.71	
	2.8		9		1.67			44		42		5		2.76	
2	0.2	0.2 – 2.0	12	9 – 15	2.25	1.0 – 2.25	Illite and Ca Montmorillonite	24	13 – 28	19	18 – 25	45	45 – 54	2.64	2.62 – 2.71
	0.8		15		1.27			13		18		54		2.68	
	1.2		9		2.0			16		22		53		2.62	
	1.5		12		1.67			19		19		50		2.71	
	2.0		12		1.0			28		25		35		2.64	
3	0.3	0.3 – 2.5	18	15 - 28	1.28	0.5 – 1.45	Kaolinite, Illite and Ca Montmorillonite	28	28 – 40	44	28 - 44	10	10 - 16	2.67	2.64 – 2.69
	1.0		20		0.6			34		31		15		2.69	
	1.6		28		0.5			26		35		11		2.71	
	2.0		22		1.45			32		28		18		2.64	
	2.5		15		1.33			40		29		16		2.68	

Table 2: Natural moisture content and consistency limits of the studied soils

Pit. No.	Depth (m)	Natural Moisture Content (%)	Liquid Limit (%)	Plastic Limit (%)	Plasticity Index (%)
1	0.5	12	52	34	17
	1.0	11	47	27	20
	1.3	13	42	21	21
	2.4	17	46	27	19
	2.8	10	40	35	5
2	0.2	10	28	15	13
	0.8	10	38	17	21
	1.2	10	29	18	11
	1.5	8	27	14	13
	2.0	8	35	15	20
3	0.3	9	47	34	13
	1.0	13	33	23	10
	1.6	15	44	30	14
	2.0	12	40	12	28
	2.5	14	31	20	11

Table 3: Derived limits and undrained cohesion of the studied soils

Pit No.	Depth (m)	Consistency Index (I_c)	I_c Range	Liquidity Index (I_L)	I_L Range	Swell Index (I_s)	I_s Range	Toughness Index (I_T)	I_T Range	Flow Index (I_F)	Undrained Cohesion (kN/m^2)
1	0.5	2.29	0.36 – 2.29	-1.29	-5 - -0.38	23	23 – 39	1.16	0.38 – 1.21	14.71	10
	1	1.8		-0.8		32		0.88		22.68	9
	1.3	1.38		-0.38		33		1.21		17.42	14
	2.4	1.53		-0.53		39		0.73		25.92	12
	2.8	0.36		-5		25		0.38		13.15	16
2	0.2	1.38	1.33 – 1.73	-0.38	-0.73 - -0.33	36	23 -36	0.8	0.75 – 3.67	16.35	12
	0.8	1.33		-0.33		26		3.67		5.72	19
	1.2	1.73		-0.73		34		0.75		14.6	8
	1.5	1.46		-0.46		30		2.39		5.44	13
	2	1.33		-0.35		23		1.57		12.76	11
3	0.3	2.92	1 – 2.92	-1.92	-1.92 - -0.55	26	10 – 57	1.44	0.46 – 1.36	9.01	18
	1	2		-1		57		0.46		21.61	13
	1.6	2.07		-1.07		50		1		14.01	23
	2	1		0		10		1.36		17.94	16
	2.5	1.35		-0.55		70		0.6		18.43	10

4. CONCLUSION

The study showed that the lateritic soils developed over gneisses and widespread all over the Basement Complex Terrain of South-western Nigeria. These soils are well graded silty clay sands with an average specific gravity of 2.72 and clay content of 31.8%. The colloidal activity of the clay in the soils is high, and generally ranges between 0.18 and 2.25. The generally high activity demonstrated potential substantial volume changes when the soils are wetted, and large shrinkages when dried. It also revealed likely presence of kaolinite and Ca montmorillonite as the principal clay minerals in the residual soils. The fines in the weathered laterites were largely silty clays exhibiting low to nearly high plasticity. The montmorillonitic clay predicted to be present could be instrumental to the soils' tendency to swell as clay absorbs water, lowering the bearing capacity of the composite. The greatest engineering threat to the lateritic soils will come from their strength characteristics generated by their clay content, which most often contains minerals especially montmorillonite.

REFERENCES

- [1] Ajibade, O., Afolabi, A. Ogungbesan, G. and Adelaja, L. A., Geochemical assessment of soils within Oke-Ogun Area, Southwestern Nigeria. Civil and Environmental Research. 2012; 2(9):1-14.
- [2] Elueze, A.A. and Bolarinwa, A.T., Appraisal of the residual and sedimentary clays in parts of Abeokuta area, Southwestern Nigeria. Journal of Mining and Geology. 2001; 37(1): 7-14.
- [3] Mesida, E.A., The geology factor in the engineering classification of some lateritic soils in Southwestern Nigeria. Proceeding of 1st National Conference of Nigerian Geotechnical Association, Lagos, 1982.
- [4] Oloruntola, M.O., Adeyemi, G.O., Adebisi, N.O. and Oduneye, O.C., Geotechnical properties of cement stabilized soils developed over pegmatite and banded gneiss from Ago-Iwoye, Southwestern Nigeria. Quarterly publication of the scientific society of the mineral wealth technologists. 2005;135: 25 – 36.
- [5] Adeyemi, G. O. Clay mineralogy, major element geochemistry and strength characteristics of three highway subgrade soils in South-western Nigeria, Bulletin of Engineering Geology and Environment. 1994; 50(1).
- [6] Balogun, L.A., The influence of geological origin on the geotechnical properties of lime stabilized laterites. Proceeding of 8th Regional Conference Africa on Soil Mechanics and Foundation. Engineering, Harare. 1984; 355-362.
- [7] Badmus, B.S., Plasticity and compressibility characteristics of lateritic soil from Southwestern Nigeria. Journal of Natural Sciences and Technology. 2010; 9(1): 14-22
- [8] British Standard B.S., Methods of testing of soils for civil engineering purposes. BS1377, Parts 2 and 8, British Standard Institution, 1990.
- [9] Donker, N.H.W. 1974. A selection of procedures for soil analysis and testing. ITC – International Report.
- [10] Oyinloye, A.O, Geology and geotectonic setting of the Basement Complex rocks in Southwestern Nigeria: Implications on provenance and evolution. 'Earth and Environmental sciences' Imran Ahmad Dar and Mithas Ahmad Dar, edited, 2011: 97-118.
- [11] Adebisi, N. O., Geotechnical investigation of foundation soils in parts of the Basement Complex Terrain of South-western Nigeria, Ph.D. Thesis University of Ibadan, 2010.
- [12] Gidigas, M.D., Degree of weathering in identification of laterite materials for engineering purposes. Engineering Geology. 1974; 8(3): 213-266.
- [13] Gidigas, M.D. and Yebo, S.L. The significance of pretesting preparations in evaluating index properties of laterite material. Highway Resources and Reclamation. 1972; 405: 105-116.
- [14] Skempton, A.W. and Bjerrum, L., A contribution to the settlement analysis of foundations on clay. Geotechnique. 1957; 7:168-178.
- [15] Casagrande, A., Classification and identification of soils. Proceeding of the American Society of Civil Engineers. Part 1 1947; 763-810.
- [16] Skempton, A.W..1953. The colloidal activity of clays. Proceeding of 3rd International Conference on Soil Mechanics and Foundation. London, Vol. 1, pp. 57- 61.