

1 **Photocatalytic degradations of malachite green on**
2 **magnetically separable $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles synthesized**
3 **by using a hydrothermal process**

4 *H- Y. He*

5 *College of Material Science and Engineering, Shaanxi University of Science and Technology, Xi'an, Shaanxi,*
6 *China(710021)*

7 **H.-Y. He**

8 hehy@sust.edu.cn

9
10 **Abstract:** $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ ($x=0-1.0$) ferrite nanoparticles were synthesized by using a
11 hydrothermal process. The nanoparticles had average particle sizes of 14.8–29.4 nm
12 and a narrow band gap of 1.75–1.91 eV, decreasing with increasing Co content. The
13 nanoparticles showed an excellent sunlight-excited photocatalytic activity to
14 malachite green in water. Moreover, the addition of a small amount of H_2O_2 resulted
15 in an obviously enhanced photodegradation, indicating a Fenton-like reaction. The
16 photodegradation and Fenton-like photodegradation rates increased with increasing
17 Co content. Complete Co substitution for Ni resulted in an optimal effect.
18 Quasi-kinetic rate constant k values were in the range of $2.23-7.2 \times 10^{-2} \text{ min}^{-1}$ and
19 increased to $1.3-6.0 \times 10^{-1} \text{ min}^{-1}$ upon the addition of H_2O_2 . The measurement of
20 oxidation-reduction potential of the nanoparticles in the photodegradation condition
21 indicated a reductive characteristic enhanced with increasing Co content. Furthermore,
22 the nanoparticles possessed high saturation magnetizations of $50.7-64.2 \text{ emu} \cdot \text{g}^{-1}$ and
23 low coercivity of 0.4–1.7 kOe, which ensured that they gave magnetic separable in
24 finally degraded dye aqueous solution.

Keywords: Nanostructure; semiconductors; dye photodegradation; Fenton-like reaction; magnetic separation

1. Introduction

Photocatalysis plays an important role in dealing with today's challenging demand for decontamination of environment. For this purpose, nano-TiO₂ as a photocatalyst has been widely studied because of its excellent chemical stability and photocatalytic activity. To fully utilize sunlight and enhance the photocatalytic activity of nano-photocatalyst, developing photocatalyst with narrower band gap semiconductor than pure TiO₂ should be of interest. In some cases, such as waste water treatment, photocatalyst nanoparticles are also required to be separated from the photodegraded aqueous solution after the photodegradation process is completed. Magnetic separation is generally believed to be an effective technique.

Spinel ferrites have narrow band gap (~2.0 eV), so their nanoparticles could be potential photocatalysts for decontamination of environment because of their superiority in full utilization of natural sunlight. Moreover, this type of ferrites are ferrimagnetic and thus magnetic separable from aqueous solution. Previous studies have shown the excellent photocatalytic activity of some ferrite nanoparticles [1, 2]. Recent studies further indicated that the composites of different ferrites [2] and ferrite with other photocatalysts [3, 4] have higher efficiency than single ones. Different metal cations have different physical chemical behavior. Thus, it is necessary to investigate the effect of Co substitution for Ni on photocatalytic activity of nickel

47 ferrite nanoparticles.

48 In recent years, advanced oxidation processes (AOPs) by using UV/H₂O₂ have
49 become a way to degrade organic compounds in dilute solutions. In general, it is
50 believed that the UV/H₂O₂ processes result in the formation of OH radicals in solution,
51 which accelerate the oxidation degradation of the organic compounds in water. The
52 use of H₂O₂ has a main disadvantage of high cost, whereas the low oxidation rate is
53 the major draw back of semiconductors, such as TiO₂. The combined use of H₂O₂ and
54 semiconductors is a way of solving this problem. Many studies have been devoted to
55 the examination of organic compound photodegradation in the presence of H₂O₂ and
56 TiO₂ [5,6]. This process is usually called Fenton-like process because it is similar to
57 the advanced oxidation process based on the homogeneous Fenton reagent (Fe²⁺/H₂O₂)
58 or Fenton-like (Fe³⁺/H₂O₂) [7,8]. Up to now, various Fenton and Fenton-like
59 processes have been used for the degradation of organic pollution. For example,
60 activated carbon fibers [9], impure bismuth ferrite [10], copper slag (90% Fe₂SiO₄)
61 [11], ferrioxalate complexes [12], iron/ordered mesoporous carbon catalyst [13], iron
62 oxide nanotube layer [14], Cu²⁺ [15], et al. have been used as Fenton-type
63 photocatalyst or assisted Fenton-type photocatalysts. However, the photocatalytic and
64 Fenton-like photocatalytic activities of Ni_{1-x}Co_xFe₂O₄ ferrite nanoparticles have not
65 been reported as dye removal from waste water.

66 To date, many methods have been developed to synthesize spinel ferrite
67 nanoparticles, such as aerosol route [16], co-precipitation method [17, 18], ceramic
68 technique [19], hydrolysis method [20], microwave-hydrothermal method [21], and

hydrothermal method [22]. The hydrothermal process has been widely used to synthesize the spinel ferrites because of its simple process, low cost, low synthesis temperature and small particle size [22].

In this study, we focus on hydrothermal synthesis of $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles, examining the effect of Co content on microstructure, photocatalytic activity for malachite green removal from aqueous solution, and magnetic property of the nanoparticles.

2. Experimental

Nickel chloride ($\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$, Shenyang Hua Bai Tai Chemical Co. Ltd., China), cobalt chloride ($\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$, Hebei Kingway Chemical Co. Ltd., China), and iron nitrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$, Beijing Baishunchem. Co. Ltd., China) were used as starting materials. The starting materials were all analytical agent without further processing. The starting materials were first weighed according to the compositions of $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ ($x=0, 0.2, 0.4, 0.6, 0.8, \text{ and } 1.0$) and dissolved in 15 mL deionized water. The solutions have Fe^{3+} concentration of 0.02 mol L^{-1} . The solutions were then transferred into autoclaves (volume: 25 mL). Subsequently, NaOH with fourfold gram equivalent of all metal cations was dissolved in deionized water (5 mL) and added dropwise into the metal cation aqueous solutions with constant magnetic stirring. The use of excess NaOH can assure full precipitation of all cations. After sealing, hydrothermal reaction was carried out in a hydrothermal oven at 180°C for 24 h. Heating rate was about $30^\circ\text{C} \cdot \text{min}^{-1}$. After naturally cooling in the oven, the products were finally washed repeatedly with distilled water, and then dried at 100°C for 24

92 h.

93 Phase composition of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles was identified by using
94 X-Ray diffractometer (XRD, $\text{CuK}_{\alpha 1}$, $\lambda=0.15406\text{nm}$, Model No: D/Max--2200PC,
95 Rigaku, Japan). Morphology of the nanoparticles was analyzed by using scanning
96 electron microscope (SEM, Model No: JXM-6700F, Japan). Fourier transform
97 infrared spectra of the nanoparticles were measured with Fourier transform infrared
98 spectrometer (FTIR, Model no: VERTEX 70, Bruke, German). KBr was used as
99 matrix to disperse the ferrite nanoparticles for compressing disk sample. Absorbance
100 spectra of the nanoparticles were determined with an ultraviolet-visible
101 spectrophotometer (Model No: 722, Hengping, China). Magnetic property was
102 measured with a vibrating sample magnetometer (VSM, Model No: Versa Lab,
103 Quantun Design, USA)

104 To study the photocatalytic and photo-Fenton like degradation of malachite green in
105 a water on the nanoparticles, malachite green aqueous solution with a concentration of
106 $1 \times 10^{-6} \text{ M}$ was first prepared. In each experiment, 50 mL malachite green aqueous
107 solution and 25 mg the ferrite nanoparticles were added into a glass beaker with
108 constant stirring for 1-2 min. The photocatalysis experiment was carried out under the
109 irradiation of sunlight. The intensity of sunlight reaching the surface of the solutions
110 measured with a solar power meter (Model no: SM206, China) was $\sim 250 \text{ W} \cdot \text{m}^{-2}$.
111 After leaving to steady state in dark for 10 min and at each irradiation interval, $\sim 3 \text{ mL}$
112 solutions were took out and filtrated out the suspended tiny particles and subsequently
113 measured to check their absorbance on a spectrophotometer (Model No: 722N,

114 Hengping, China). The solutions after the test were returned to the beakers to
115 maintain the normal volume of the solutions under test. Similar experiment was
116 carried out by adding 0.5 mL H₂O₂ into each of the 50 mL dye aqueous solution.

117 In first hour of the above processes, the oxidation-reduction potential (ORP) of the
118 malachite green aqueous solutions with and without the photocatalysts was determined
119 by using an oxidation-reduction potential tester (ORP-286, China). The ORPs of the
120 nanoparticle surfaces in the condition of dye photodegradation were estimated by
121 calculating the differences between the measured ORP of the dye aqueous solutions
122 with and without the nanoparticles. The absorbance and ORP of the dye aqueous
123 solutions were all the average value of two repeated measurement values

124

125 **3. Results and discussion**

126 **3.1. XRD analysis**

127 Figure 1a shows XRD patterns of the synthesized nanoparticles. All diffraction
128 peaks match with the diffraction data of spinel ferrites. This indicates that the
129 nanoparticles are single phase. The intensity of the XRD peaks first slightly decreases
130 when the Co content (x) is increased from 0 to 0.8 and then increases with further
131 cobalt substitution, drawing out variation trend in crystallinity of the nanoparticles.
132 This decrease trend of the crystallinity with cobalt substitution was also reported for
133 the Ni_{1-x}Co_xFe₂O₄ nanoparticles synthesized by using solvothermal route [23]. This
134 could be mainly due to smaller radius difference (0.72–0.64 Å) between Ni²⁺ and
135 Fe³⁺ ions than that (0.74–0.64 Å) between Co²⁺ and Fe³⁺ ions. The smaller radius

136 difference leads to smaller inhibition of Ni^{2+} substitution for Fe^{3+} to the spinel crystal
 137 growth than Co^{2+} substitution. Moreover, the position of strongest peak (311) shifts to
 138 lower 2θ with Co substitution (Fig. 1b). This can be ascribed to the increase in the
 139 interplanar crystal spacing (d) based on Bragg's equation. The lattice parameter of the
 140 nanoparticles with cubic crystal structure can be calculated by following equation
 141 with the XRD analysis data:

$$142 \quad \frac{a^2}{d^2} = h^2 + k^2 + l^2 \quad (1)$$

143 Calculated a values are 0.8236 nm, 0.8263 nm, 0.8298 nm, 0.8321 nm, 0.8339 nm
 144 and 0.8377 nm for the Co content $x=0, 0.2, 0.4, 0.6, 0.8,$ and 1.0 , respectively (Fig.
 145 1c). This indicates the expansion of the lattice with the cobalt substitution, agreeing
 146 with the shift of (311)-peak. Similar lattice parameter variation was also reported in
 147 previous literature [16, 24]. Moreover, the lattice parameter a of CoFe_2O_4 equals to
 148 0.8391 nm (JCPDS: 22-1086) that is larger than 0.83379 nm (JCPDS: 74-2081) and
 149 0.83390 nm (JCPDS: 10-0325) of the NiFe_2O_4 . Furthermore, the lattice parameter of
 150 the all ferrites is smaller than the value given in the JCPDS card, especially as the Co
 151 content approaches zero. This could be ascribed to the high-pressure effect in the
 152 condition of hydrothermal synthesis. Similarly, the lattice parameter of the NiFe_2O_4
 153 nanoparticle is smaller when they were synthesized by using hydrothermal process
 154 than sol-gel method [25]. The average crystal sizes of the nanoparticles are
 155 determined from XRD data with Debye–Scherrer's formula [26]:

$$156 \quad D = \frac{0.9\lambda}{\beta \cos \theta} \quad (2)$$

157 where λ is the X-ray wavelength, β the full width at half maximum (FWHM) of the

158 considered peak and θ is the Bragg angle. The results are 23.4, 29.4, 23.6, 19.4, 16.5,
159 and 14.8 nm for the $x=0, 0.2, 0.4, 0.6, 0.8, 1.0$, respectively.

160 **3.2. SEM**

161 Figure 2 shows SEM micrographs of the nanoparticles. Most of the nanoparticles
162 show spherical morphology with some agglomeration (Fig. 2c–2f), while the
163 $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ ($x=0.8$ and 1.0) nanoparticles have approximately cubical morphology
164 (Fig. 2a and 2b). This could be mainly due to same reason of the difference in
165 crystallinities of the nanoparticles. From the SEM micrographs, the average particle
166 sizes are also increased as increasing x from 0 to 0.8 and then decreased with further
167 cobalt substitution. The sizes of the nanoparticles with $x=0.8$ and 1.0 are obviously
168 larger than the results of XRD analysis, which means that these nanoparticles are
169 polycrystalline.

170 **3.3. FTIR analysis**

171 Figure 3 shows FTIR spectra of the nanoparticles. The peak centered at $\sim 3416\text{ cm}^{-1}$
172 is attributed to the stretching vibration of surface hydroxyls absorbed on surface and
173 O–H groups in absorbed water [27]. The peak centered at 1620 cm^{-1} is assigned to the
174 H–O–H bending vibration in water molecular [28] or the OH deformation vibration
175 due to surface hydroxyls [29, 30]. These imply good nanoparticle surface
176 hydrophilicity that may be favorable for the photocatalytic activity. The weak peak at
177 1124 cm^{-1} could be assigned to the C–O stretching [31] due to the adsorbed CO_2 . The
178 two peaks at $\sim 483\text{ cm}^{-1}$ and $\sim 616\text{ cm}^{-1}$ are assigned to the vibrations of ferrite groups
179 [32], corresponding to the octahedral and tetrahedral sites of positive ions in the

180 ferrite, respectively [28, 33]. The difference in absorption positions between the
181 octahedral and tetrahedral complexes of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ crystals is due to the
182 different distances between $\text{Fe}^{3+}-\text{O}^{2-}$ in the octahedral and tetrahedral sites. This
183 confirms the formation of single phase $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ structure.

184 **3.4. Optical absorption**

185 Figure 4 shows absorbance spectra of the ferrite nanoparticles. The absorbances in
186 UV-visible region are large and increase with increasing Co content. The estimated
187 absorption edge increases from ~648 nm to ~710 nm. Accordingly, the band gap
188 energies of the nanoparticles decrease from ~1.91 eV to ~1.75 eV (Inserted figure in
189 Fig. 4).

190 **3.5. Photocatalytic degradation of the dye in water**

191 Figure 5 shows concentration variations of the malachite green aqueous solutions on
192 the nanoparticles with the irradiation time of sunlight. The degradation rate increases
193 with increasing Co content. This increase of degradation rate could be ascribed to the
194 decrease of band gap and average particle size and the increase of light absorbance of
195 nanoparticles as the increase of Co content. In addition, the ORP values are negative
196 and decrease (Fig. 6). This indicates that the nanoparticles surface are dominantly
197 reductive in the photocatalysis condition, This characteristics is enhances with
198 increasing Co content.

199 **3.6. Fenton-like photodegradation**

200

201 Figure 7 shows concentration variations of the malachite green aqueous solution

with H₂O₂ on the nanoparticles with the irradiation time of sunlight. The degradation is obviously faster than that without H₂O₂, which indicates a significant photo-Fenton-like reaction. Similarly, the degradation rate increases as the Co content is increased. This increase could also be ascribed to the decrease of band gap and average particle size and the increase of light absorbance. The photo-generated electron-hole pairs in the nanoparticles could play similar role of Fe²⁺ and Fe³⁺ in Fenton reaction. The concentration increase in photo-generated electrons and holes leads to the enhanced photo-Fenton-like reaction. The ORP values in this process are larger than those in the cases without H₂O₂. The ORP also shows a nonlinear variation with Co contents, (Fig. 6). The difference and variation of ORP could be related to the surface characteristics of the nanoparticles, the acidic-alkaline behavior of the dye, oxidation of H₂O₂ and Fenton-like reaction.

Kinetic relation between concentration (*C*) of the malachite green aqueous solution and photocatalytic reaction time (*t*) can be given by:

$$\frac{C_0}{C} = A \exp\left(\frac{kt}{T}\right) \quad (3)$$

where *C*₀ is initial concentration, *k* is quasi-kinetic rate constant, *T* is reaction temperature and *A* is a constant. Fig. 8 shows the plots of ln(*C*/*C*₀) versus *t*. The plots are approximately linear. The *k* values can be estimated directly from the plots. The estimated *k* values are in the range of 2.23–7.2×10⁻² min⁻¹, which is increased nearly one order of magnitude to 1.3–6.0×10⁻¹ min⁻¹ as H₂O₂ is used. The *k* values increase with increasing Co content in both cases with and without H₂O₂.

3.7. Magnetic property of the nanoparticles

Figure 9a show room temperature hysteresis loops of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles. The nanoparticles are all ferrimagnetic. With increasing applied field, the magnetization of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles increases, and reaches saturation state under highest applied magnetic fields of 30 kOe. Maximum value of magnetization at applied field of 30 KOe (saturation magnetization M_s) is in the ranges of 50.7–64.2 $\text{emu}\cdot\text{g}^{-1}$ (Fig. 9b). The coercivity (H_c) is in the range of 0.4–1.7 kOe (Fig. 9b). The ferrite nanoparticles with Co content $x=0.8$ show maximal M_s and H_c . This can be mainly ascribed to the maximal cation distribution of Fe^{3+} and Co^{2+} at the octahedral site (B-site) since the magnetic moments of Zn^{2+} , Co^{2+} and Fe^{3+} are 0 μ_B , 3 μ_B and 5 μ_B , respectively. Other reasons include the difference in particle size, easy magnetization axis and shape anisotropy. The large M_s and low H_c can provide excellent magnetic separation performance for the ferrite nanoparticles in the final degraded dye aqueous solution.

237

238 **4. Conclusions**

Single phase $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ ($x=0.1-1.0$) ferrite nanoparticles showed high photocatalytic activity in the sunlight-excited photodegradation of malachite green in water. The addition of small amount of H_2O_2 resulted in remarkably enhanced photodegradation, indicating the present of Fenton-like reaction. Due to the increases in light absorbance and the decrease in band gap and average particle size, the photodegradation and Fenton-like photodegradation rates increased with increasing Co content. The ferrite nanoparticles also showed high saturation magnetizations and

low coercivities, which ensured that they can be easily separated after the photodegradation.

Acknowledgements: The authors thank the Mr. H. Tian of the Northwest Institute for Non-Ferrous Metal Research for his kind assistance in SEM measurement

References

- [1] P.-G. Guo, G.-L. Zhang, J.-Q. Yu, H.-L. Li, X.-S. Zhao, Controlled synthesis, magnetic and photocatalytic properties of hollow spheres and colloidal nanocrystal clusters of manganese ferrite, *Colloids and Surf., A* 395 (2012) 168-174
- [2] E. Casbeer, V.K. Sharma, X.-Z. Li, Synthesis and photocatalytic activity of ferrites under visible light: A review, *Sep. Purif. Technol.* 87 (5) (2012) 1-14
- [3] A.A. Aziz, K.S. Yong, S. Ibrahim, S. Pichiah, Enhanced magnetic separation and photocatalytic activity of nitrogen doped titania photocatalyst supported on strontium ferrite, *J. Hazard. Mater.* 199–200 (15) (2012) 143–150
- [4] Y.-S. Fu, H.-Q. Chen, X.-Q. Sun, X. Wang. Combination of cobalt ferrite and graphene: High-performance and recyclable visible-light photocatalysis, *Appl. Catal. B: Environ.* 111–112 (12) (2012) 280-287
- [5] Adrián M.T. Silva, Ekaterini Nouli, Nikolaos P. Xekoukoulotakis and Dionissios Mantzavinos, Effect of key operating parameters on phenols degradation during H₂O₂-assisted TiO₂ photocatalytic treatment of simulated and actual olive mill wastewaters, *Appl. Catal. B: Environ.* 73(1–2)(2007) 11–22

- 269 [6] Emad S. Elmolla, and Malay Chaudhuri, Photocatalytic degradation of amoxicillin,
270 ampicillin and cloxacillin antibiotics in aqueous solution using UV/TiO₂ and
271 UV/H₂O₂/TiO₂ photocatalysis, *Desalination* 252(1–3) (2010) 46–52
- 272 [7] Neamtu M, Zaharia C, Catrinescu C, Yediler A, Macoveanu M, Kettrup I A,
273 Fe-exchanged Y zeolite as catalyst for wet peroxide oxidation of reactive azo dye
274 Procion Marine H-EXL, *Appl Catal B: Environ.* 48 (2004) 287–294.
- 275 [8] Guelou E, Barrault J, Fournier J, Tatibouet JM, Active iron species in the catalytic
276 wet peroxide oxidation of phenol over pillared clays containing iron, *Appl Catal*
277 *B: Environ.* 44 (2003) 1–8.
- 278 [9] Lie Wang, Yuyuan Yao, Zhanhao Zhang, Lijie Sun, Wangyang Lu, Wenxing Chen,
279 Haixiang Chen, Activated carbon fibers as an excellent partner of Fenton catalyst
280 for dyes decolorization by combination of adsorption and oxidation, *Chem. Eng. J.*
281 251 (2014) 348–354
- 282 [10] Tayyebi Soltani, Mohammad H. Entezari, Solar-Fenton catalytic degradation of
283 phenolic compounds by impure bismuth ferrite nanoparticles synthesized via
284 ultrasound, *Chem. Eng. J.* 251 (2014) 207–216
- 285 [11] M. Solís-López, A. Durán-Moreno, F. Rigas, A.A. Morales, M. Navarrete, R.M.
286 Ramírez-Zamora, Assessment of copper slag as a sustainable Fenton-type photo-
287 catalyst for water disinfection, *Water Reclamation and Sustainability* June (2014)
288 199–227
- 289 [12] Isabelli N. Dias, Bruno S. Souza, João H.O.S. Pereira, Francisca C. Moreira,
290 Márcia Dezotti, Rui A.R. Boaventura, Vítor J.P. Vilar, Enhancement of the

291 photo-Fenton reaction at near neutral pH through the use of ferrioxalate
 292 complexes: A case study on trimethoprim and sulfamethoxazole antibiotics
 293 removal from aqueous solutions, *Chem. Eng. J.* 247 (2014) 302–313
 294 [13] Feng Duan, Yuezhu Yang, Yuping Li, Hongbin Cao, Yi Wang, Yi Zhang,
 295 Heterogeneous Fenton-like degradation of 4-chlorophenol using iron/ordered
 296 mesoporous carbon catalyst, *J. Environ. Sci.* 26 (5) (2014) 1171–1179
 297 [14] Jun-Won Jang, Jae-Woo Park, Iron oxide nanotube layer fabricated with
 298 electrostatic anodization for heterogeneous Fenton like reaction, *J. Hazard. Mater.*
 299 273 (30) (2014) 1–6
 300 [15] Hye-Jin Lee, Hongshin Lee, Changha Lee, Degradation of diclofenac and
 301 carbamazepine by the copper(II)-catalyzed dark and photo-assisted Fenton-like
 302 systems, *Chem. Eng. J.* 245 (2014) 258–264
 303 [16] T.E. Agustina, H.M. Ang, V.K. Vareek. A review of synergistic effect of photo-
 304 catalysis and ozonation on wastewater treatment, *J. Photochem. Photobiol. C:*
 305 *Photochem. Rev.* 6 (2005) 264–273
 306 [17] V.L. Mathe, A.D. Sheikh. Magnetostrictive properties of nanocrystalline Co–Ni
 307 ferrites, *Physica B* 405 (2010) 3594–3598
 308 [18] R. Arulmurugan, G. Vaidyanathan, S. Sendhilnathan, B. Jeyadevan, Thermo-
 309 magnetic properties of $\text{Co}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ ($x=0.1-0.5$) nanoparticles, *J. Magn. Magn.*
 310 *Mater.* 303 (2006) 131–137.
 311 [19] A. Tawfik, I.M. Hamada, O.M. Hemeda, Effect of laser irradiation on the
 312 structure and electromechanical properties of Co–Zn ferrite, *J. Magn. Magn.*

313 Mater. 250 (2002) 77–82.

314 [20] G.V. Duong, N. Hanh, D.V. Linh, R. Groessinger, P. Weinberger, E. Schafner, M.
 315 Zehetbauer, Monodispersed nanocrystalline $\text{Co}_{1-x}\text{Zn}_x\text{Fe}_2\text{O}_4$ particles by forced
 316 hydrolysis: Synthesis and characterization, J. Magn. Magn. Mater. 311 (2007)
 317 46–50.

318 [21] C.-K. Kim, J.-H. Lee, S. Katoh, R. Murakami, M. Yoshimura, Synthesis of Co-,
 319 Co-Zn and Ni-Zn ferrite powders by the microwave-hydrothermal method, Mater.
 320 Res. Bull. 36 (2001) 2241–2250.

321 [22] F. Gözüak, Y. Köseoğlu, A. Baykal, H. Kavas, Synthesis and characterization of
 322 $\text{Co}_x\text{Zn}_{1-x}\text{Fe}_2\text{O}_4$ magnetic nanoparticles via a PEG-assisted route, J. Magn. Magn.
 323 Mater. 321 (2009) 2170–2177.

324 [23] Y. Tang, X.-W. Wang, Q.-H. Zhang, Y.-Q. Li, H.-Z. Wang, Solvothermal
 325 synthesis of $\text{Co}_{1-x}\text{Ni}_x\text{Fe}_2\text{O}_4$ nanoparticles and its application in ammonia vapors
 326 detection, Progress in Natural Science: Materials International 22 (2012) 53–58

327 [24] R. Mukherjee, T. Sahu, S. Sen, P. Sahu, Structural and microstructural evolution
 328 due to increasing Co substitution in $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$: An X-ray diffraction study
 329 using the Rietveld method, Mater. Chem. Phys. 128 (2011) 365–370

330 [25] M. Srivastava, S. Chaubey, A.K. Ojha, Investigation on size dependent structural
 331 and magnetic behavior of nickel ferrite nanoparticles prepared by sol–gel and
 332 hydrothermal methods, Mater. Chem. Phys. 118 (2009) 174–180

- 333 [26] H.P. Klug, L.E. Alexander, X-ray Diffraction Procedures for Polycrystalline and
334 Amorphous Materials, 2nd ed., John Wiley & Sons, New York, 1974.
- 335 [27] S. Yáñez-Vilar, M. Sánchez-Andújar, C. Gómez-Aguirre, J. Mira, M.A.
336 Señarís-Rodríguez, S. Castro-García, A simple solvothermal synthesis of MFe_2O_4
337 ($M^{1/4}Mn$, Co and Ni) nanoparticles, J. Solid State Chem. 182 (2009) 2685–2690.
- 338 [28] C.-H. Lu, S.-J. Liou, Hydrothermal preparation of nanometer lithium nickel
339 vanadium oxide powder at low temperature, Mater. Sci. Eng., B 75 (2000) 38–
340 42.
- 341 [29] P. Priyadharsini, A. Pradeep, P. Sambasiva Rao, G. Chandrasekaran, Structural,
342 spectroscopic and magnetic study of nanocrystalline Ni–Zn ferrites, Mater.
343 Chem. Phys. 116 (2009) 207–213
- 344 [30] X.-C. Shen, X.-Z. Fang, Y.-H. Zhou, H. Liang, Synthesis and characterization of
345 3-aminopropyltriethoxysilane-modified superparamagnetic magnetite nano-
346 particles, Chem. Lett. 33 (2004) 1468–1469.
- 347 [31] M. Ma, Y. Zhang, W. Yu, H.-Y. Shen, H.-Q. Zhang, N. Gu, Preparation and
348 characterization of magnetite nanoparticles coated by amino silane, Colloids Surf.
349 A 212 (2003) 219–226.
- 350 [32] H. Sozeri, Z. Durmus, A. Baykal, Structural and magnetic properties of
351 triethylene glycol stabilized $Zn_xCo_{1-x}Fe_2O_4$ nanoparticles. Mater. Res. Bull. 47
352 (2012) 2442–2448
- 353 [33] S.-H. Xiao, W.-F. Jiang, L.-Y. Li, X.-J. Li, Low-temperature auto-combustion

354 synthesis and magnetic properties of cobalt ferrite nanopowder, Mater. Chem.

355 Phys. 106 (2007) 82–87.

356

357

358

359

360

361

362

363

364

365

366

367

368

369

370

371

372

373 **Figures:**

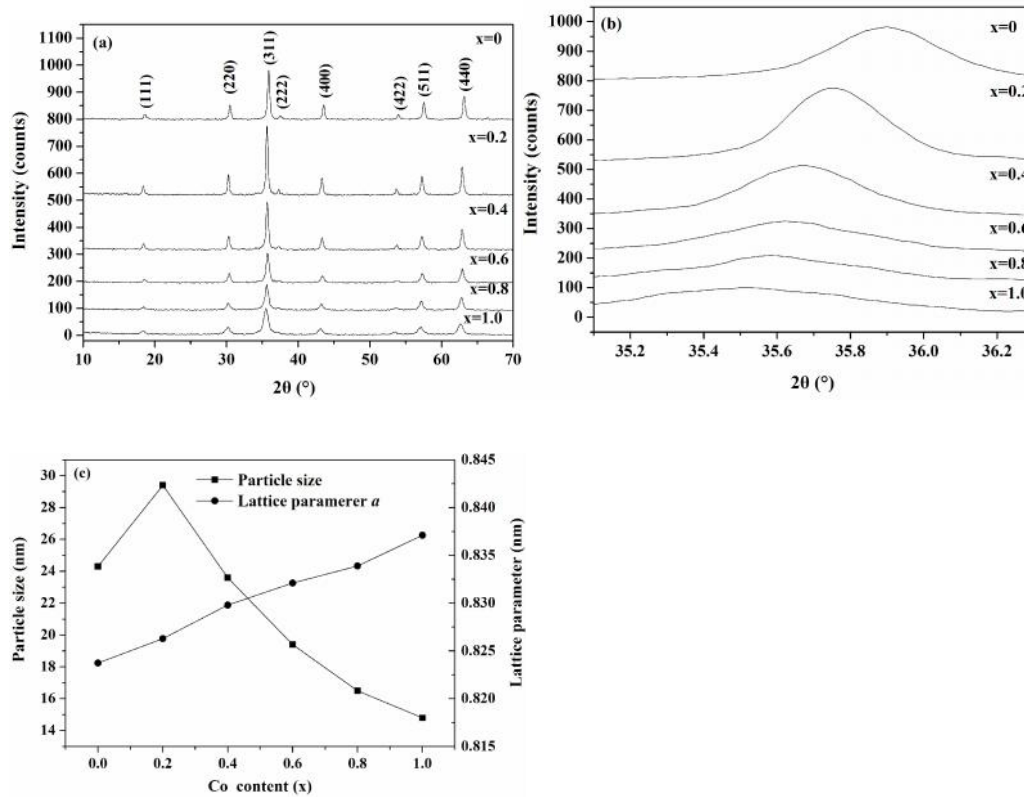


Figure 1. (a) XRD patterns and (b) enlarged (311) peak. (c) Average particle size and lattice parameter of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles.



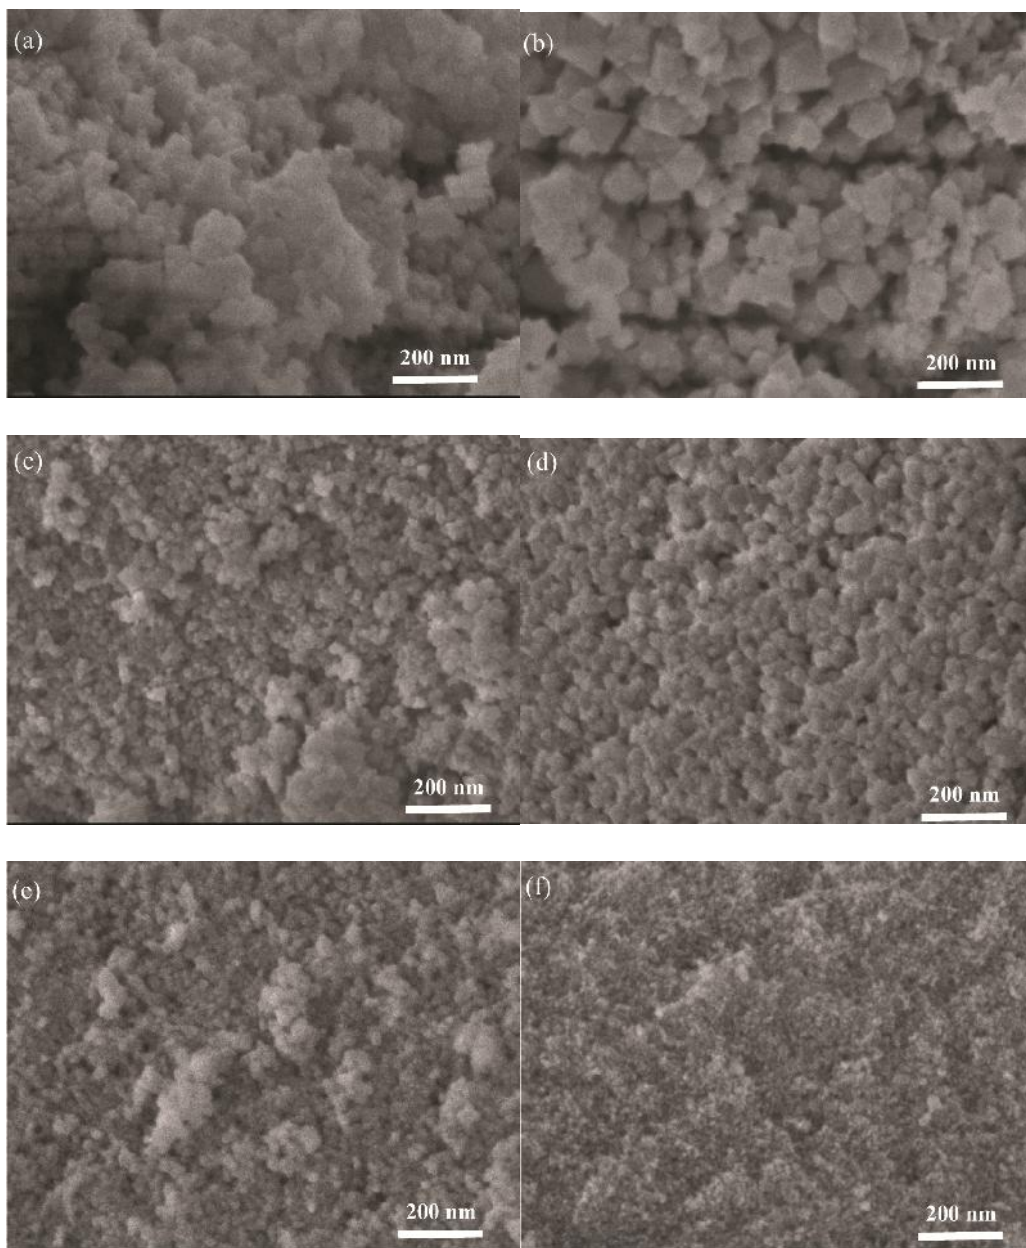


Figure 2. SEM micrographs of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles with various Co content: (a) $x=0$, (b) $x=0.2$, (c) $x=0.4$, (d) $x=0.6$, (e) $x=0.8$ and (f) $x=1.0$.

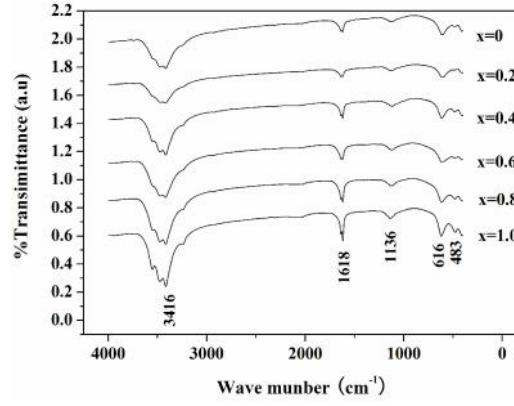

391

392 Figure 3. FTIR spectra of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles.

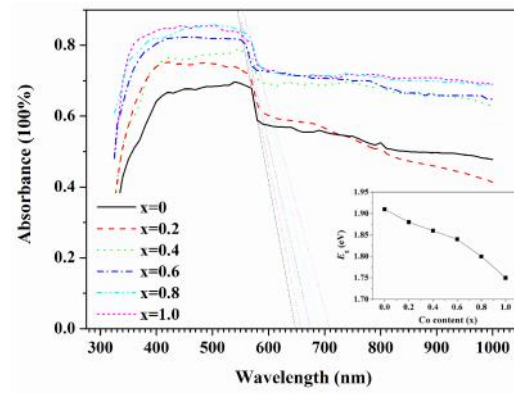

393

394 Figure 4. Absorbance spectra of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles. The inset is the plot
395 of band gap (E_g) vs. Co content (x).


396

397

398

399

400

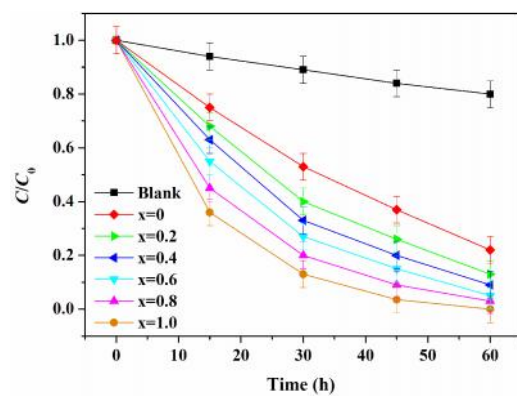


401

402 Figure 5. Concentration variations of malachite green aqueous solutions on the

403 $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles with the irradiation time of sunlight.

404

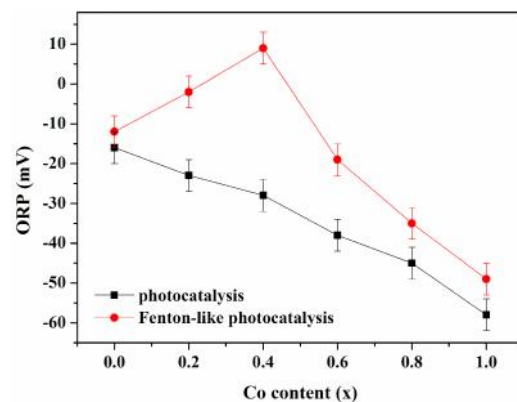

405


406 Figure 6. ORP variations of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles with Co content (x) in

407 the photocatalytic and photo-Fenton-like degradation systems.

408

409


410

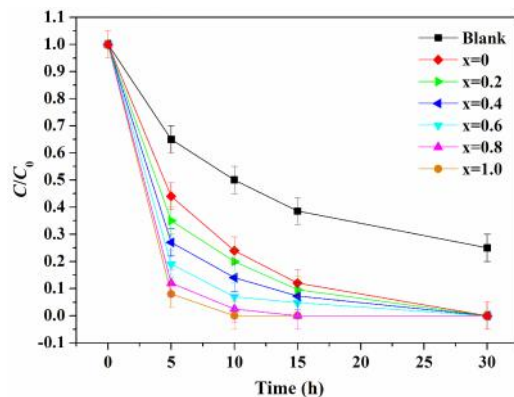

411

412 Figure 7. Concentration variations of malachite green aqueous solutions containing
 413 H_2O_2 (concentration equals to 10 ml/l) on the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles
 414 with irradiation time of sunlight.

415

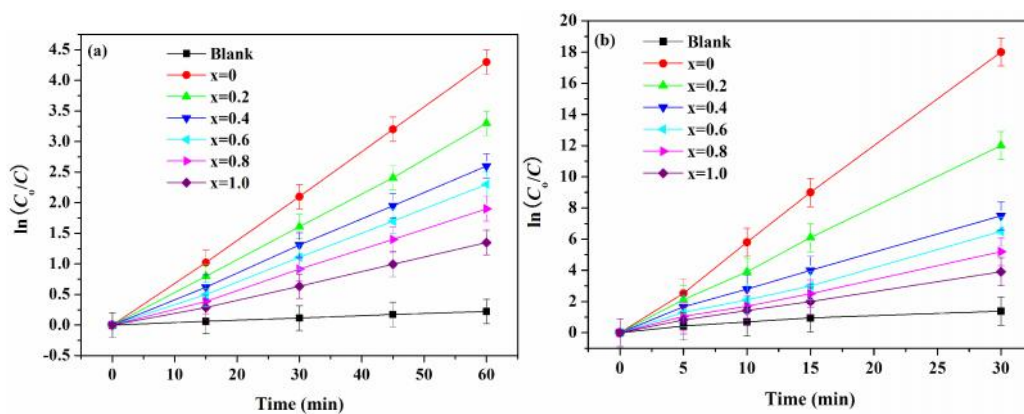

416

417 Figure 8. Plots of $\ln(C/C_0)$ vs. irradiation time of sunlight without (a) and with (b)

418

H_2O_2 .

419

420

421

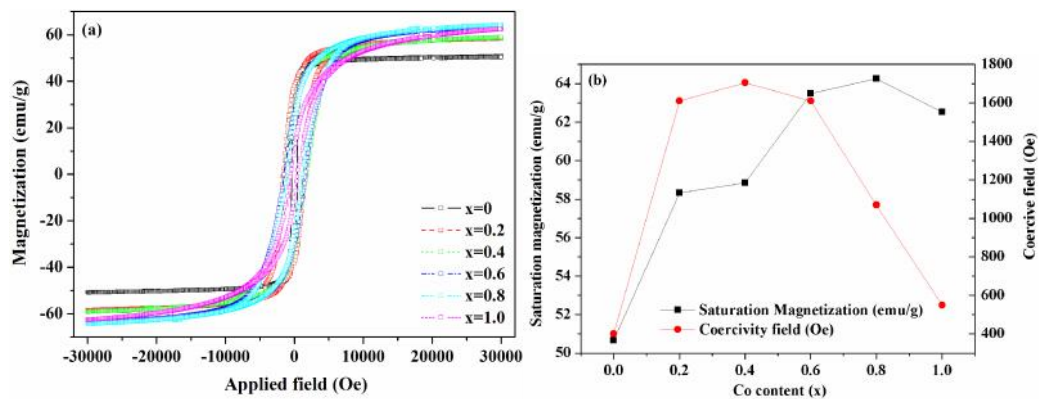


Figure 9. (a) Room temperature magnetic hysteresis loops of the $\text{Ni}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ nanoparticles and (b) variations of saturation magnetization and coercivity as a function of Co content.