

Improvement of Delignification, Desilication and Cellulosic Content Availability in Paddy Straw via Physico-Chemical Pretreatments

ABSTRACT

Aim: Paddy straw consists of cellulose and hemicellulose as their plant materials leading to their potential to produce bioethanol through several processes such as pretreatment, enzymatic hydrolysis and ethanol fermentation. Among these processes, pretreatment of paddy straw is particularly important for enzymatic hydrolysis process as they are being limited by the presence of ash and silica content. This study was set to observe the effect of different pretreatments on cellulose, hemicellulose, lignin and ash content of paddy straw.

Place and Duration of Study: This study was conducted in Department of Biology, Faculty of Science, Universiti Putra Malaysia, between October 2015 and June 2016.

Methodology: Pretreatments comprises the combination of physical (mechanical) and chemical treatments to modify the lignocellulosic structure while reduce lignin and separate silica content in paddy straw fibre. Paddy straw was prepared into three different sizes (2mm, 5mm and 8 mm) for physical treatment. Autoclave, boiled and four different concentrations (0.5%, 1%, 2% and 5% (v/v) and (w/v) respectively) of nitric acid and sodium hydroxide, respectively for chemical treatment were used on paddy straw.

Results: Size five millimeter paddy straw showed the highest cellulose content (35.61%) compared to the other sizes and when the paddy pretreated with 2% (w/v) sodium hydroxide (NaOH), the percentage of cellulose content escalated to 72.47%. Pretreatment of 2% (w/v) NaOH have performed the most efficient delignification and desilication process (1.02% lignin; 5.44 ash content); and the performance was supported with SEM images on surface area of the paddy straw with large distortion caused by the treatment.

Conclusion: Therefore, 2% (w/v) NaOH was found to be the most suitable condition to break the cellulose-lignin complex and make the paddy straw becomes feasible for biofuel production.

Keywords: Biofuel, chemical pretreatment; lignocellulosic biomass; physical pretreatment; SEM images.

1. INTRODUCTION

Agro-industrial wastes are deposited in landfills and burning of the residues has increased the production of greenhouse gases [1]. Over 90% worldwide production of this biomass is found in the Asia region [2]. The waste produced by industries including municipal waste, pulp and paper, agriculture, food, forestry and animal wastes is in huge amount and can potentially be treated to produce more valuable products like animal feed, chemicals and biofuels [3]. The production of biofuels from agro wastes stand a good prospective as the raw materials do not compete with other food-source materials and they are rich in sugar and starch [4]. Rice is the most preferred food and energy source among Malaysian than any other agricultural crops [5]. Prior to consumers' demand, recent technologies in rice production have been developed to increase its productivity. However, the increase of paddy rice production has also raised the bulks of its by-products including paddy straw.

As a lignocellulosic material, paddy straw comprises cellulose, hemicelluloses and lignin as its major component with a potential to produce bioethanol through bioconversion process of lignocellulosic biomass to fermentable sugar [6]. This has leads to the need in developing a biotechnical process using a low cost cellulolytic enzyme production that is economically feasible [7]. While it has been known that paddy straw is useful in bioethanol production, Ibrahim [8] concluded in his study that this process is limited by the existence of high ash and silica content in paddy straw, which makes it difficult for the paddy straw to be converted into ethanol. Generally, paddy straws differ from other cereal straws as they have a relatively high amount of silicon dioxide (SiO₂) in their ash content but with low amount of lignin content [9]. According to Liu et al [10], the ash is made up of 75% SiO₂, 3% P₂O₅, 1.5% CaO, 2% Fe₂O₃, 10% K₂O and small portions of Na, Mg, and S. Silicon has played many significant roles for paddy such as grain yield, phenolic synthesis, as well as serving as the shield for plant cell wall [9]. Nevertheless, silicon has become a limiting factor in paddy straw pretreatment for enzymatic digestion.

The structure of cellulose and hemicellulose is heavily packed with layers of lignin to protect them against enzymatic hydrolysis [11]. Lignin, on the other hand, is an aromatic biopolymer with an integral cell wall component in all vascular plants built up by the oxidative coupling of three-major C₆-C₃ (phenylpropanoid), forming a randomized assembly in a tri-dimensional system inside the cell wall [12,13]. Lignin acts as a matrix for the cellulose microfibrils made up by polymer chains, which contain tightly packed and crystalline regions [14]. The hydrogen bond between polysaccharides and adhesion of lignin to the polysaccharides has caused them to be insoluble in water and partially soluble in organic solvent.

The complex structure of a cell wall makes it hard for paddy straw to be digested using anaerobic microorganisms, resulting in low digestion rate for biogas production [15]. The main problem in the consumption of lignocellulosic biomass is the disruption of complex matrix of polymers; liberating the monosaccharides and improvement of pretreatment methods to maximize the material digestibility for the following enzymatic hydrolysis [16]. Pretreatment process is consequently crucial to remove lignin, silica, reduce cellulose crystallinity, and to maximize the accessible surface area of materials [17].

Pretreatment, or other known as the delignification, is a process that usually involves physical, physiochemical, chemical and thermal methods, as well as the combination of these method to break the lignin layers of protection that limit the accessibility of enzymes to celluloses and hemicelluloses. According to Zhu et al [18], many pretreatment techniques have been developed to improve this conversion process. The effectiveness of a pretreatment technique has been defined as the ability to rupture the matrix of cell-wall that includes the connectivity between lignin and carbohydrates, along with depolymerizing and solubilizing hemicellulose polymers [19]. Among these techniques, pretreatment is believed to be predominantly important, considering the difficulties of lignocellulosic structure for enzymatic hydrolysis as well as one of the most expensive processing steps over the whole conversion process [20]. Hence, this study attempts to determine the effectiveness of various physical and chemical pretreatments used to increase the accessibility to the cellulose and hemicellulose content in paddy straw by reducing the lignin shield and separating the silica that encloses the monosaccharide

2. MATERIAL AND METHODS

2.1 Substrate Preparation

Paddy straw was washed to remove the undesired particles, sundried and kept in a dry container. Extractives were removed by Soxhlet extraction for 2 hours using toluene-ethanol (2:1) mixed solvent [21].

2.2 Pretreatment of Paddy Straw

Combination of physical and chemical pre-treatments was carried out on the paddy straw. The physical treatment includes grinding the paddy straw in hammer mill to several mesh sizes (8 mm, 5 mm and 2 mm). All grinded paddy straws were treated in treatment listed in Table 1, respectively. All pretreated paddy straws were washed with distilled water until their pH values reach at almost neutral before being dried in an oven at 60 °C until reaching a constant weight.

Table 1. Pretreatments on paddy straw.

Pre-treatments	Conditions
Control (Untreated)	No treatment given
Autoclaved	Autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
Boil	Soaked in boiled water ($100^{\circ}\text{C} \pm 0.5$) for 4 hours at room temperature (RT); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
0.5% (v/v) HNO_3	Soaked in 0.5% (v/v) HNO_3 (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
1.0% (v/v) HNO_3	Soaked in 1.0% (v/v) HNO_3 (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
2.0% (v/v) HNO_3	Soaked in 2.0% (v/v) HNO_3 (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
5.0% (v/v) HNO_3	Soaked in 5.0% (v/v) HNO_3 (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
0.5% (w/v) NaOH	Soaked in 0.5% (w/v) NaOH (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
1.0% (w/v) NaOH	Soaked in 1.0% (w/v) NaOH (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
2.0% (w/v) NaOH	Soaked in 2.0% (w/v) NaOH (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)
5.0% (w/v) NaOH	Soaked in 5.0% (w/v) NaOH (room temperature; 4 hours); autoclaved ($121^{\circ}\text{C} \pm 0.5$; 15 minutes)

84

85 2.3 Determination of cellulose and hemicellulose content availability percentages

86 The percentage of cellulose and hemicellulose content was determined and calculated adopting the
 87 method proposed by Han and Rowell [21]. The calculations involved expressed data on loss of dry
 88 matter and dry matter basis that occurs in processing steps.

89 2.4 Determination of lignin content

90 The lignin content of paddy straw was determined by using Acid-Detergent Lignin (ADL) procedure.
 91 The process requires preparation of Acid-Detergent Fiber (ADF) before carrying out the ADL process
 92 and the calculations were carried out based on the amount of loss upon ignition at $500 \pm 25^{\circ}\text{C}$ after
 93 being treated with 72% (v/v) sulfuric acid (H_2SO_4) for 3 hours [22].

94 2.5 Determination of ash content

95 The percentage of ash content was determined and calculated from the method by Han and Rowell
 96 [21]. The fibers were weighed and burned over a low flame of Bunsen burner until well and fully
 97 carbonized. The fibers were ignited in the furnace at $575 \pm 25^{\circ}\text{C}$ for 3 hours. The calculations were
 98 based on moisture-free weight of the fibre.

99

2.6 Physical observation using Scanning Electron Microscope (SEM)

The SEM viewing of untreated (control) and pretreated (2% (w/v) NaOH and 0.5% (v/v) HNO₃) paddy straws was done in Microscopy Unit at the Institute of Bioscience, Universiti Putra Malaysia using Phillips XL30 SEM. For SEM viewing, the paddy straw was oven dried at 60 °C for 24 hours [23]. The images were then viewed and observed using SEM at 1.0 K magnification.

3. RESULTS AND DISCUSSION

The main approach used to improve enzymatic hydrolysis is by removing lignin and silica while increasing the cellulosic accessible surface area [24]. In this study, the percentages of cellulose, hemicellulose, lignin and ash content were used as parameters to measure the effectiveness of physical and chemical pretreatment of paddy straw. Theoretically, pretreatment could further enhance the delignification and desilication processes on lignocellulosic material [25]. Therefore, both cellulose and hemicellulose will be exposed for further saccharification by selected conversion agent.

3.1 Physical pre-treatments

Lignocellulosic materials contain two types of surface area, which are internal and external. In order to increase the external surface area, the size particle of paddy straw was reduced. Thus, three different fiber sizes were chosen (2 mm, 5 mm and 8 mm) to demonstrate the effect of physical pretreatment on paddy straw by comparing the delignification of fiber in each treatment.

The best size of paddy straw with highest cellulosic composition (35.61% cellulose; 26.96% hemicellulose) and accessibility was displayed by 5 mm with lowest amount of lignin, 10.79%. Paddy straw size 8 mm showed second best physical pretreatment by producing an amount of 34.64% of cellulose. However, the percentage of lignin in 8 mm slightly went up to 10.92%. The 2 mm paddy straw has failed to indicate better result in which they were only able to produce 33.55% cellulose and significantly high lignin percentage (12.14%) compared to the percentage of cellulose and lignin produced by 5 mm and 8 mm (Table 2). Paddy straw with size 2 mm also displayed the highest amount of ash content and lignin; 12.14% and 13.68% respectively. This further suggests that there is a limit in substrate's size in achieving optimum delignification.

Table 2. Percentage of lignocellulosic composition of untreated paddy straw fibres for all sizes

Size	Ash Content (%)	Cellulose (%)	Hemicellulose (%)	Lignin (%)
2 mm	13.68±0.97 ^a	33.55±0.71 ^b	20.09±0.25 ^b	12.14±0.16 ^a
5 mm	12.17±0.44 ^b	35.61±0.80 ^a	26.96±3.31 ^a	10.79±0.27 ^b
8 mm	11.52±0.34 ^c	34.64±0.39 ^{ab}	21.85±1.50 ^{ab}	10.92±0.28 ^b

Values are means of three replicates with ±SD.

*Means in each column with same superscript letter are not significantly different amongst themselves when Tukey test were used at 5% significance level

Reducing the particle size of paddy straw by grinding is expected to assist the delignification process by facilitating heat and mass transfer in enzymatic hydrolysis [20]. Hypothetically, reduction in paddy straw particle size would give a higher surface volume ration, delignification and enhanced enzyme accessibility for hydrolyzation, thus increases the availability of lignocellulosic compound [26, 27]. However, the size of 2 mm may impose negative effects since very fine particles prefer to form clumps during the following steps involving liquid, causing a channeling effect [28]. Channeling is a process that limits the path of a charged particle in a crystalline solid [29]. On the other hand, 8 mm paddy straw may have a low surface area and poor in eliminating mass and has a difficulty in transferring heat during hydrolysis reactions, thus leading to a less effectiveness in delignification and lignocellulosic availability.

Size 5 mm may have the traits to maximize the availability of specific surface area and reduce the degree of polymerization (DP) by accompanying the formation of more cellulose ends available to the exoglucanase [25, 30]; as they were able to exposed highest of cellulose availability (35.61%). The particle size also plays important role in determining the power requirement for mechanical comminution (a reduction process of raw materials from one particle size to a smaller). A study proposes if particle size held to the range of 3-6 mm, the energy input for comminution can be kept below 30 kWh per ton of biomass [31]. Too small, less than 3 mm, requires more energy inputs in substrate preparation. Not only size 5 mm was able to produce the highest amount of cellulose among other sizes, the study also strongly suggests that medium size requires lower energy inputs; thus, making the whole conversion process becomes more cost-effective.

3.2 Pretreatments with different concentration of acid and alkali

Physico-chemical pretreatment were referred as a combination of physical and chemical pre-treatments. In this study, the combination of both pretreatment was carried out to enhance the lignocellulosic material availability for bioconversion process in later stages (Table 1). Autoclaved at 121 ± 5 °C for 20 minutes has showed improved amount of cellulose content from untreated paddy straw of size 5 mm; increased to 46.52% from initial percentage of untreated paddy which is 35.61%. This treatment also has encouraged the delignification process by dropping to 9.66% from 10.79% of untreated paddy straw. In order to further investigate the effectiveness of autoclave treatment, combination of boiled water were tested and result shows boiled water has promotes larger delignification and desilication process (8.46% lignin; 9.44% ash content) but no further improvement of cellulose content from only autoclave treatment.

A combination of physical and chemical pre-treatments of paddy straw with size 5 mm treated with various concentrations of acid and alkali pretreatments were carried out (Table 3). The best pretreatment were based on the lignocellulosic composition of the paddy straw. Pretreatment of 2% (w/v) NaOH (4 hour) has shown 2 folds of cellulose content and almost 90.54% reduction of lignin from 35.61% to 72.47% and 1.02% from 10.79% compared to untreated paddy straw, respectively. The percentage of hemicellulose has also been reduced from 26.96% to 19.42% when pretreated with 2% (w/v) NaOH compared to untreated paddy straw. The pretreatment with NaOH with other agro waste such as wheat straw results in slight degradation of hemicellulose, whereas the contents of lignin after alkali pretreatment were particularly low (121 °C, 4% NaOH, 2.2%), indicating that alkaline solutions efficiently remove lignin by breaking ester bonds, thereby increasing the porosity of biomass [32]. A study by Harun and Geok [33] was only managed to achieve the highest delignification of 79.6% using more concentrated alkali (12% (w/v) NaOH for 1 hour). Aside from their high efficiency, pretreatment with dilute concentration of alkali was preferred due to their economic feasibility and the residual of alkali on the substrate that can be easily removed compared to a more concentrated alkali. The determination of ash content is vital as the quality of ash determines the total amount of recoverable silica due to it is the largest constituent in the ash. This would be particularly useful in the case of paddy, which the material is initially considered unsuitable for a biofuel feedstock as they contain high percentage of silica [34]. However, with the pretreatment of 2% (w/v) NaOH, the content of ash has been reduced to 5.44% compared to the percentage of ash content in untreated paddy straw of 12.17%

185

Table 3. Percentage of lignocellulosic composition of 5mm paddy straw fibres after treated with different pretreatment.

Treatment	Ash Content (%)	Cellulose (%)	Hemicellulose (%)	Lignin (%)
Untreated	12.17±0.44 ^d	35.61±0.80 ^d	26.96±3.31 ^{bcd}	10.79±0.27 ^{de}
Autoclaved without chemical treatment	12.99±0.74 ^{cd}	46.52±1.91 ^c	20.47±2.94 ^{cde}	9.66±0.30 ^{ef}
Boil with autoclaving	9.44±2.23 ^e	43.97±0.45 ^c	28.90±2.37 ^{bc}	8.46±1.23 ^f
Acidic treatment with autoclaving				
0.5% (v/v) HNO ₃	13.33±1.11 ^{cd}	60.72±1.08 ^b	10.79±5.25 ^f	12.68±0.08 ^c
1.0% (v/v) HNO ₃	15.11±0.79 ^{bc}	58.09±0.43 ^b	16.50±3.85 ^{ef}	12.90±0.43 ^c
2.0%(v/v) HNO ₃	16.03±0.11 ^b	46.10±4.09 ^c	28.73±3.12 ^{bc}	15.43±1.04 ^b
5.0% (v/v) HNO ₃	18.99±1.57 ^a	44.83±2.69 ^c	39.48±3.33 ^a	18.66±0.40 ^a
Alkaline treatment with autoclaving				
0.5% (w/v) NaOH	13.74±0.69 ^{bcd}	58.57±0.38 ^b	17.47±2.27 ^{ef}	11.55±0.50 ^{cd}
1.0% (w/v) NaOH	7.22±0.25 ^{ef}	46.42±0.16 ^b	34.16±0.28 ^{ab}	2.38±0.27 ^g
2.0% (w/v) NaOH	5.44±2.87 ^f	72.47±2.06 ^a	19.42±2.14 ^{de}	1.02±0.09 ^g
5.0% (w/v) NaOH	7.09±6.88 ^{ef}	48.32±2.05 ^c	23.20±4.05 ^{cde}	1.45±0.13 ^g

186

Values are means of three replicates with ±SD.

187

**Means in each column with same superscript letter are not significantly different amongst themselves when Tukey test were used at 5% significance level.*

The second best pretreatment in this study was 0.5% (v/v) HNO₃. The composition of cellulose obtained was 60.72%; which is behind 2% (w/v) NaOH by 11.75%. The percentage of hemicellulose composition has been reduced significantly to only 10.79%; with a total of loss of 59.97%, making this pretreatment as the lowest producers of hemicellulose. For bioethanol production, removal of hemicellulose in initial stage is important to reduce structural constrains for further enzymatic cellulose hydrolysis [35]. Despite the increased percentage of cellulose in dilute acid pretreatment, the treatments failed to reduce the amount of lignin and ash content in the paddy straw. The values rose higher than the percentage of untreated paddy straw.

Out of all various concentration of acid pretreatment were used, the least effective concentration of HNO₃ was 5% (v/v); which only produced 44.83% cellulose. The percentage of cellulose decreases as the concentration of acid becomes higher. This pattern can also be seen in the percentage of lignin and ash content of the treatment; both of the parameter increases as the concentration of the treatment exposed to the paddy straw become more concentrated.

In this study, a combination of physical, autoclaved (by means of steaming without explosion) and chemical pretreatment were used to heighten up to their possible maximum capacity in degrading the cellulosic materials of paddy straw. Steaming with or without explosion (autohydrolysis) is known to their function in removing hemicellulose and helps to elevate the mean pore size of the substrate for the probability of the cellulose to become hydrolyzed [36, 37]. This process is totally different from steam explosion. Steam explosion seems to be suitable for hardwoods, but become limited for softwoods that contain a comparatively large amount of condensed-type lignin [38]. There are some limitations of steam explosion which includes the incomplete disruption of the lignin-carbohydrate matrix [39]. The autoclave pretreatment has successfully displayed their efficiency in increasing the accessibility of cellulose up to 46.52%; with an increment of 10.91% from untreated paddy straw. Meanwhile, boiled or liquid hot water (LHW) pretreatment does improved delignification and disilication process but failed to improve the cellulose availability. This event occurred as water under high pressure penetrate into the biomass to hydrate the cellulose but somehow causing the removal of hemicellulose and part of the lignin [24].

Dilute nitric acid (HNO₃) and sodium hydroxide (NaOH) were used at various concentrations to observe the effectiveness of the treatments in removing ash and lignin content in order to enhance the accessibility towards cellulose and hemicellulose of the paddy straw. Dilute acid pre-treatments, HNO₃ were chosen over other acid treatments such as sulfuric acid (H₂SO₄) and hydrochloric acid (HCl) due to their ability to produce highest glucose content and good in cellulose-to-sugar conversion process [40]. According to Kumar and Sharma [41], the most common alkali pretreatments are using hydroxyl derivatives of sodium, potassium, calcium, and ammonium salts. The selection of NaOH were based on the report by Vaccarino et al [42], in which the effects of SO₂, Na₂CO₃, and NaOH pretreatments were tested on the enzymatic digestibility of grape marc and found out the greatest degrading effects were obtained by pretreatment with 1% (w/v) NaOH solution.

In this study, the best pretreatment of paddy straw with size 5 mm was by 2% (w/v) NaOH. The mechanism of dilute NaOH pretreatment works by rupturing the structural linkages between lignin and carbohydrates of hemicelluloses, leading to a decrease in the lignin polymerization degree, a decrease in cellulose crystallinity, and a separation of the hemicellulose sugars [43]. The effectiveness of 2% (w/v) NaOH has been reported by Rahnama et al [44], where higher enzymatic hydrolysis and glucose were detected with the use of substrate pretreated with 2% (w/v) NaOH compared to higher NaOH concentration. Concentration more than 2% (w/v) could cause loss of carbohydrate through solubilization while the substrate was being pretreated. This explains why pretreatment of 5% (w/v) NaOH becomes less effective in exposing cellulosic materials as the percentage of cellulose dropped to 48.32%.


Acid pretreatment is known for their ability to remove hemicellulose efficiently from straws to provide high yields of fermentable sugars and have been used as parts of overall processes in fractionating the components of lignocellulosic biomass [45]. However, the concentration of the acid influenced their efficiency as the percentage of hemicellulose increases along with the amount of acid concentration. The acid concentration of more than 0.5% (v/v) showed increased percentage of lignin and ash content

compared to the percentage of the untreated paddy straw; as the structure of lignin changes due to undesirable reaction of the simultaneous depolymerization and repolymerization of lignin during acid-catalyzed treatment of biomass [46, 47]. However in the context of ash, more than 100% was detected where the apparent increased of silicon content may due to the mechanism of HNO_3 in removing organic and inorganic (non-silicon) components in paddy straw during soaking process, thus resulting the sample weigh more than 50% of control samples [48]. In some cases, the pretreatment of HNO_3 also involved in the leaching process instead of dissolution of SiO_2 in which they are significantly better at removing impurities, carbon and obtained high purity of silica with 99% and more [49]. According to Brodeur et al [50], another drawback of acid pretreatment is the production of fermentation inhibitors like furfural and hydroxymethyl furfural (HMF) that reduces the effectiveness of the pretreatment method and further processes.


3.3 SEM images of cell wall structure of paddy straw

Physico-chemical pretreatments with various concentrations of HNO_3 and NaOH has significantly increased the cellulose and hemicellulose content and reduced the lignin. Figure 1 depicts the impact of acid and alkali in pretreatment where the surface structure of untreated paddy straw was densely packed (Fig. 1a) compared to rough surface of pre-treated paddy straw (Fig.1b & 1c).


This rough surface is an evidence of cellulose crystallization resulted from the breakdown of hemicellulose, lignin and ash by hydrolyzing uronic acid and acetic esters and also by the swollen cellulose layer [51, 28]. The initial structure of untreated paddy straw (size 5 mm) is coarse and brown in color, but after been treated with 2% (w/v) NaOH , the structure become softer and green in color. Dilute alkali treatments reduce the recalcitrant nature of lignocellulosic biomass by digesting cellulose fibers and maximize the cellulose accessibility [52]. According to Zhang and Cai [53], pretreatment with 2% (w/v) NaOH on paddy straw has caused the microfibril separated from the initial connected structure (Fig. 1a) and fully exposed, causing the increment in the external surface area and the porosity of the rice straw. In comparison to acid pre-treatment, alkali pretreatment has caused a larger surface area of distortion, which further increased the accessibility towards cellulose and hemicellulose.

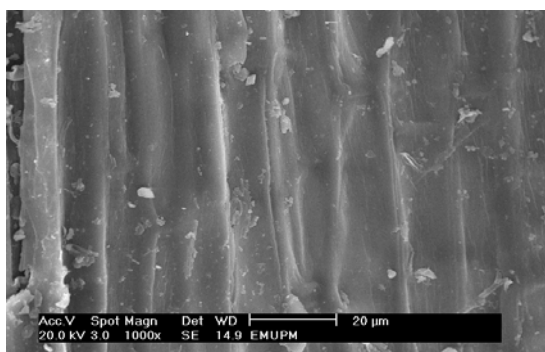

(a)

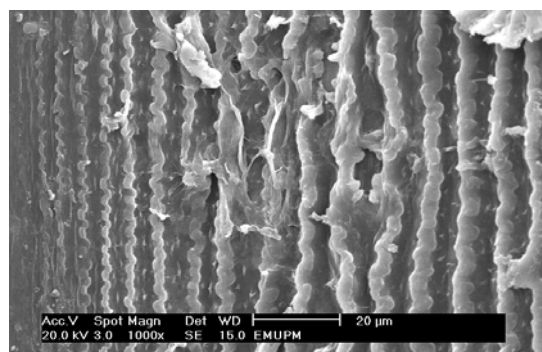

(b)

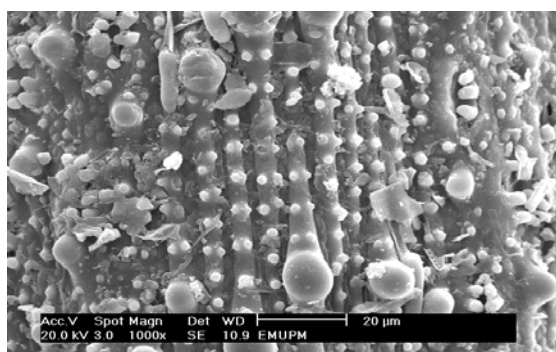

(c)

Fig. 1: Scanning electron micrographs of 5mm paddy straw fibres. (a) Untreated (b) Treated with 2% (w/v) sodium hydroxide (NaOH) (c) Treated with 0.5% (v/v) nitric acid (HNO₃)

4. CONCLUSION

Based on the percentage of lignocellulosic composition and ash content analysis, a physico-chemical pretreatment of size 5 mm and 2% (w/v) NaOH was chosen as the best pretreatment for paddy straw since it exhibits the highest cellulose percentage which is 35.61% and 72.47%, respectively; due to their ability to performed desilication and delignification efficiently (5.44% ash content; 1.02% lignin). The performance of 2% (w/v) NaOH was supported by SEM images on surface structure of paddy straw.

REFERENCES

1. Abu Qdais H, Al-Widyan M. Evaluating composting and co-composting kinetics of various agro-industrial wastes. *Int. J. Recycl. Org. Waste Agricult.* 2016; 5(3):273–280. doi: 10.1007/s40093-016-0137-3
2. Hsu TC, Guo GL, Chen WH, Hwang WS. Effect of dilute acid pretreatment of rice straw on structural properties and enzymatic hydrolysis. *Bioresour. Technol.* 2010; 101(13): 4907–4913. doi: 10.1016/j.biortech.2009.10.009
3. Dashtban M, Schraft H, Qin W. Fungal bioconversion of lignocellulosic residues; opportunities & perspectives. *Int. J. Biol. Sci.* 2009;5(6):578-595. doi: 10.7150/ijbs.5.578

4. Ruriani E, Sunarti TC, Meryandini A. 2012. Yeast isolation for bioethanol. *Hayati J. Biosci.* 2012; 19(3): 145-149. doi: 10.4308/hjb.19.3.145
5. Vaghefi N, Shamsudin MN, Makmom A, Bagheri M. The economic impacts of climate change on the rice production in Malaysia. *Int. J. Agric. Res.* 2011; 6(1): 67-74. doi: 10.3923/ijar.2011.67.74
6. Pointing SB. Qualitative methods for the determination of lignocellulolytic enzyme production by tropical fungi. *Fungal Diversity.* 1999; 2: 17-33.
7. Shimokawa T, Shibuya H, Ishihara M, Yamaguchi M, Ota Y, Miyazaki K, Ikeda T, Magara K, Nojiri M. Screening of lignocellulolytic enzyme producers: enzyme system from *Aspergillus Tubingensis* for hydrolysis of sugi pulp. *Bull. FFPRI.* 2012; 11(2): 58-64.
8. Ibrahim HA. Pretreatment of straw for bioethanol production. *Energy Procedia.* 2012; 14: 542 – 551. doi: 10.1016/j.egypro.2011.12.973
9. Van Soest PJ. Rice straw, the role of silica and treatments to improve quality. *Anim. Feed Sci. Technol.* 2006; 130(3-4): 137–171. doi: 10.1016/j.anifeedsci.2006.01.023
10. Liu Z, Xu A, Zhao T. Energy from combustion of rice straw: status and challenges to China. *Energy Power Eng.* 2011; 3(3): 325-331. doi: 10.4236/epe.2011.33040
11. Binod P, Sindhu R, Singhanian RR, Vikram S, Devi L, Nagalakshmi S, Kurien N, Sukumaran RK, Pandey A. Bioethanol production from rice straw: an overview. *Bioresour. Technol.* 2010; 101(13): 4767–4774. doi: 10.1016/j.biortech.2009.10.079
12. Ämmälähti E, Brunow G, Bardet M, Robert D, Kilpeläinen I. Identification of side-chain structures in a poplar lignin using three-dimensional HMQC-HOHAHA NMR spectroscopy. *J. Agric. Food Chem.* 1998; 46(12):5113–5117. doi: 0021-8561(199812)46:12<5113:IOSSIA>2.0.ZU;2-F
13. Xiao B, Sun SF, Sun RC. Chemical, structural, and thermal characterizations of alkali-soluble lignins and hemicelluloses, and cellulose from maize stems, rye straw, and rice straw. *Polym. Degrad. Stability.* 2001; 74(2): 307–319. doi: 10.1016/S0141-3910(01)00163-X
14. Ghaffar SH, Fan M. Structural analysis for lignin characteristics in biomass straw. *Biomass Bioenergy.* 2013; 57: 264-279. doi: 10.1016/j.biombioe.2013.07.015
15. He Y, Pang Y, Liu Y, Li X, Wang K. Physicochemical characterization of rice straw pretreated with sodium hydroxide in the solid state for enhancing biogas production. *Energy Fuels.* 2008; 22(4): 2775–2781. doi: 10.1021/ef8000967
16. Ma H, Liu WW, Chen X, Wu YJ, Yu ZL. Enhanced enzymatic saccharification of rice straw by microwave pretreatment. *Bioresour. Technol.* 2009; 100(3): 1279–1284. doi: 10.1016/j.biortech.2008.08.045
17. Karimi K, Emitiazi G, Taherzadeh MJ. Ethanol production from dilute-acid pretreated rice straw by simultaneous saccharification and fermentation with *Mucor indicus*, *Rhizopus oryzae*, and *Saccharomyces cerevisiae*. *Enzyme Microb. Technol.* 2006; 40(1):138–144. doi: 10.1016/j.enzmictec.2005.10.046
18. Zhu S, Wu Y, Yu Z, Wang C, Yu F, Jin S, Ding Y, Chi R, Liao J, Zhang Y. Comparison of three microwave/chemical pretreatment processes for enzymatic hydrolysis of rice straw. *Biosyst. Eng.* 2006; 93(3): 279–283. doi: 10.1016/j.biosystemseng.2005.11.013
19. Ramos LP. The chemistry involved in the steam treatment of lignocellulosic materials. *Quim Nova.* 2003; 26(6): 863-871. doi: 10.1590/S0100-40422003000600015
20. Wati L, Kumari S, Kundu BS. Paddy straw as substrate for ethanol production. *Indian J. Microbiol.* 2007; 47(1): 26-29. doi: 10.1007/s12088-007-0005-y
21. Han JS, Rowell JS. Chemical composition of fibers. In Rowell RM, Young RA, Rowell JK (eds). *Paper and Composites from Agro-Based Resources.* CRC Press Inc; United States of America; 1997.
22. Goering HK, Van Soest PJ. Forage fiber analysis (apparatus, reagents, procedures, and some applications). In Goering HK, Van Soest PJ (eds). *Agriculture Handbook No. 379.* USDA-ARS; Washington DC; 1970.
23. Phutela UG, Sahni N. Microscopic structural changes in paddy straw pretreated with *Trichoderma reesei* MTCC 164 and *Coriolus versicolor* MTCC 138. *Indian J. Microbiol.* 2013; 53(2): 227–231. doi: 10.1007/s12088-012-0321-8
24. Taherzadeh MJ, Karimi K. Pretreatment of lignocellulosic wastes to improve ethanol and biogas production: a review. *Int. J. Mol. Sci.* 2008; 9(9): 1621-1651. doi: 10.3390/ijms9091621

25. Mosier N, Wyman C, Dale B, Elander R, Lee YY, Holtzapple M, Ladisch M. Features of promising technologies for pretreatment of lignocellulosic biomass. *Bioresour. Technol.* 2005; 96(6): 673-686. doi: 10.1016/j.biortech.2004.06.025
26. Wen Z, Liao W, Chen S. Production of cellulase/ β -glucosidase by mixed fungi culture *Trichoderma Reesei* and *Aspergillus Phoenicis* on dairy manure. *Process Biochem.* 2005; 40(9): 3087-3094. doi: 10.1016/j.procbio.2005.03.044
27. Gude VG. Microwave pretreatment of feedstock for bioethanol production. In Gude VG (eds). *Microwave-mediated biofuel production*. CRC Press; United States of America; 2017.
28. Sarkar NS, Ghosh SK, Bannerjee S, Aikat K. Bioethanol production from agricultural wastes: an overview. *Renew Energy.* 2012; 37(1): 19-27. doi: 10.1016/j.renene.2011.06.045
29. Robinson MT, Oen OS. The channeling of energetic atoms in crystal lattice. *Appl. Phys. Lett.* 1963; 2(2): 30-32. doi: 10.1063/1.1753757
30. Karimi K, Taherzadeh MJ. A critical review on analysis in pretreatment of lignocelluloses: Degree of polymerization, adsorption/desorption, and accessibility. *Bioresour. Technol.* 2016; 203: 348 – 356. doi: 10.1016/j.biortech.2015.12.035
31. Kumar P, Barrett DM, Delwiche MJ, Stroeve P. Methods for pretreatment of lignocellulosic biomass for efficient hydrolysis and biofuel production. *Ind. Eng. Chem. Res.* 2009; 48 (8): 3713–3729. doi: 10.1021/ie801542g
32. Zheng Q, Zhou T, Wang Y, Cao X, Wu S, Zhao M, Wang H, Xu M, Zheng B, Zheng J, Guan X. Pretreatment of wheat straw leads to structural changes and improved enzymatic hydrolysis. 2018; 8: 1321. doi: 10.1038/s41598-018-19517-5
33. Harun S, Geok SK. Effect of sodium hydroxide pretreatment on rice straw composition. *Ind. J. Sci. Tech.* 2016; 9(21): 1-9. doi: 10.17485/ijst/2016/v9i21/95245
34. Sorek N, Yeats TH, Szemenyei H, Youngs H, Somerville CR. The implications of lignocellulosic biomass chemical composition for the production of advanced biofuels. *BioScience.* 2014; 64(3): 192 – 201. doi: 10.1093/biosci/bit037
35. Gírio FM, Fonseca C, Carneiro F, Duarte LC, Marques S, Bogel-Lukasik R. Hemicelluloses for fuel ethanol: a review. *Bioresour. Technol.* 2010; 101(13): 4775 – 4800. doi: 10.1016/j.biortech.2010.01.088
36. Chandra RP, Bura R, Mabee WE, Berlin A, Pan X, Saddler JN. Substrate pretreatment: the key to effective enzymatic hydrolysis of lignocelluloses? *Adv. Biochem. Eng. Biotechnol.* 2007; 108: 67–93. doi: 10.1007/10_2007_064
37. Alvira P, Tomás-Pejó M, Ballesteros M, Negro MJ. Pretreatment technologies for an efficient bioethanol production process based on enzymatic hydrolysis: a review. *Bioresour. Technol.* 2009; 101: 4851- 4861. doi: :10.1016/j.biortech.2009.11.093
38. Asada C, Sasaki C, Uto Y, Sakafuji J, Nakamura Y. Effect of steam explosion pretreatment with ultra-high temperature and pressure on effective utilization of softwood biomass. *Biochem. Eng. J.* 2012; 60: 25-29. doi: 10.1016/j.bej.2011.09.013
39. Chiaramonti D, Prussi M, Ferrero S, Oriani L, Ottonello P, Torre P, Cherchi F. Review of pretreatment processes for lignocellulosic ethanol production, and development of an innovative method. *Biomass Bioenergy.* 2012; 46: 25-25. doi: doi.org/10.1016/j.biombioe.2012.04.020
40. Bensah ED, Mensah M. Chemical pretreatment methods for the production of cellulosic ethanol: technologies and innovations. *Int. J. Chem. Eng.* 2013; 1-21. doi: 10.1155/2013/719607
41. Kumar AK, Sharma S. Recent updates on different methods of pretreatment of lignocellulosic feedstocks: a review. *Bioresour. Bioprocess.* 2017; 4:7. doi: 10.1186/s40643-017-0137-9
42. Vaccarino C, Lo Curto RB, Tripodo MM, Bellocchio E, Laganfi G, Patan R. Effect of SO₂, NaOH and Na₂CO₃ pretreatments on the degradability and cellulase digestibility of grape marc. *Biol. Waste.* 1987; 20:79–88.
43. Woiciechowski AL, Karp SG, Sobral K, De Carvalho JC, Letti LAJ, Soccol VT, Soccol CR. Pretreatment strategies to enhance value addition of agro-industrial wastes. In: Brar S, Dhillon G, Soccol C (eds) *Biotransformation of waste biomass into high value biochemicals*. Springer; New York; 2014. doi: 10.1007/978-1-4614-8005-1_2
44. Rahnema N, Foo HL, Abdul Rahman NA, Ariff A, Md Shah UK. Saccharification of rice straw by cellulase from a local *Trichoderma harzianum* SNRS3 for biobutanol production. *BMC Biotechnol.* 2014; 14:103. doi: 10.1186/s12896-014-0103-y

45. Zhang YHP, Ding SY, Mielenz JR, Cui JB, Elander RT, Laser M, Himmel ME, McMillan JR, Lynd LR. Fractionating recalcitrant lignocellulose at modest reaction conditions. *Biotechnol. Bioeng.* 2007; 97: 214–223. doi:10.1002/bit.21386
46. Li J, Henriksson G, Gellerstedt G. Lignin depolymerization/repolymerization and its critical role for delignification of aspen wood by steam explosion. *Bioresour. Technol.* 2006; 98 (16):3061-3068. doi: 10.1016/j.biortech.2006.10.018
47. Ko JK, Kim Y, Ximenes E, Ladisch MR. Effect of liquid hot water pretreatment severity on properties of hardwood lignin and enzymatic hydrolysis of cellulose. *Biotechnol. Bioeng.* 2015; 112(2): 252-262. doi: 10.1002/bit.25349
48. Inglesby MK, Wood DF, Gray GM. Effect of chemical fractionation treatments on silicon dioxide content and distribution in *Oryza sativa*. In Stokke D D, Groom L H (eds). *Characterization of the cellulosic cell wall*. Blackwell Publishing; Ames, IA; 2006.
49. Junko U, Kutsuyoshi K. Process optimization to prepare high-purity amorphous silica from rice husks via citric acid leaching treatment. *Trans. JWRI.* 2008; 37(1): 13-17. doi: 11094/6542/1/jwri37_01_013
50. Brodeur G, Yau E, Badal K, Collier J, Ramachandran KB, Ramakrishnan S. Chemical and physicochemical pretreatment of lignocellulosic biomass: a review. *Enzyme Research.* 2011; 1-17. doi: 10.4061/2011/787532
51. Carrasco F. Fundamentos del fraccionamiento de la biomasa. *Afinidad.* 1989; 46(423): 425-429. doi: 0001-9704
52. Kshirsagar SD, Waghmare PR, Loni PC, Patil SA, Govindwar SP. Dilute acid pretreatment of rice straw, structural characterization and optimization of enzymatic hydrolysis conditions by response surface methodology. *RSC Adv.* 2015; 5: 46525–46533. doi: 10.1039/C5RA04430H
53. Zhang QZ, Cai WM. Enzymatic hydrolysis of alkali-pretreated rice straw by *Trichoderma reesei* ZM4-F3. *Biomass Bioenergy.* 2008; 32(12): 1130-1135. doi: 10.1016/j.biombioe.2008.02.006