

Geotechnical evaluation of Malikhore Formation as coarse aggregate and dimension stone, SE Balochistan, Pakistan

ABSTRACT

Geotechnical properties of coarse aggregate of Malikhore Formation of Jurassic age of districts Lasbela and Khuzdar, SE Balochistan were made. It belongs to fabulous Mor Range, situated in the southern part of western fold belt of Pakistan. Bulk specific gravity (SSD), water absorption, sieve analysis, Los Angeles abrasion test, unconfined compressive strength, soundness, silica alkali reactivity, clay lump and friable particles, loose and rodded density, flakiness and elongation indices of coarse aggregate were evaluated for building and road material. Nearly all the samples were found within the specified limits of ASTM specifications and are appropriate material for concrete, asphalt and as suitable dimension stone. The variation in colour and texture of Malikhore Formation has good demand in the local and foreign markets as dimension stones.

Keywords: Geotechnical properties, coarse aggregate, Malikhore Formation, dimension stone, Balochistan

1. INTRODUCTION

Karachi is a big, growing megapolis city having large population [1]. As the population increases in any area, lots of civil structures like buildings, offices, roads etc. are needed to fulfill the socio-economic necessities of the people. For this purpose, huge quantity of building material in form of aggregates and dimension stones are required. Within the Karachi city, a number of mega projects such as high-rise buildings, shopping malls, overhead bridges, underground passes and creek city are under construction. Network of highways, industrial estates, mega cities, small dams etc. are also planned in the Lasbela and Khuzdar districts. The adjoining mountain ranges are the main sources of acquiring most of the building materials in Karachi and Balochistan. The area of study is extended from north of Karachi to Khuzdar District, Balochistan (Fig. 1).

Civil engineers, architects and geologists are an integral part for construction and designing beautiful and durable buildings, bridges, highways and dams. Geotechnical engineers assess site characterization and geotechnical design of modern and mega structures [2]. Material engineer select appropriate earth materials (aggregate, sand, silt, clay etc.) and evaluate their geotechnical properties as per American Society for Testing and Materials (ASTM) standards [3]. A common understanding of the relationship between geologic origin and geotechnical properties is essential to assure the best product quality. Millogo et al. [4] emphasize to study geotechnical and mechanical properties of aggregates and the structure for durable construction.

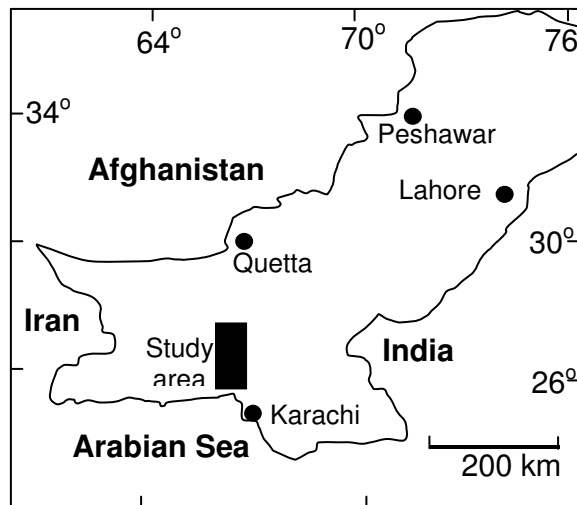


Fig. 1. Map displays the location of the study area within Pakistan.

Keeping in view the above considerations, the present research work was undertaken to evaluate the geotechnical characteristics of Malikhore Formation of Lasbela and Khuzdar regions. This is very first attempt to carry out this sort of work in the area and is expected to open new research endeavors in future. This work may also draw attention of the community of local and foreign builders in the selection of good quality building material of world standards and can play its due role in developing the country and boosting the economy.

2. GENERAL GEOLOGY

Geologically, study area is a part of the Western Fold Belt (WFB) which is outcome of collision between Indian and Eurasian plates. The WFB represents the fore land fold and thrust belt along the western margin of the Indian Plate [5]. The area is located in the west of the Pab and Mor ranges. In Lasbela District, Bela Ophiolite is sandwiched between the two ranges. They are comprised of Jurassic to Miocene age sedimentary rocks [6].

The Jurassic clastic and carbonate rocks of Ferozabad Group are extensively exposed in the Mor Range. They are shelf deposits formed as a result of breakup of Pangaea [7]. The group is comprised of Kharrari, Malikhore and Anjira formations [8]. Fatmi et al. [9], introduced term Malikhore Formation in place of Loralai Member of Shirinab Formation. It is derived from the Malikhore Village, west of Khuzdar. Major lithology of the formation is hard, compact, crystalline limestone deposited in platform conditions with thin partings of subordinate shale [10]. Repetition of strata with pelletal, oolitic, conquinoid and micritic textures is important character of formation [11]. Formation shows variation in thickness at different places; at type locality it is 387m thick [12]. The age of formation is assigned as Early Jurassic [13,14].

Sedimentary rocks including Sembar, Goru, Parh, Moghalkot and Pab formations of Cretaceous age are widely distributed in the Pab Range [6]. In the upper part of the study area, tertiary rocks like Jhakkar group, Nal, Thar, Wad formations are well exposed.

Exposures of Malikhore Formation are found throughout study area. It is well exposed at east of Bela, Asandro, Jurri, Khuzdar and Gunga localities. The hardness and compact nature of formation makes it suitable for construction material and presence of variable texture also makes it more apposite for embellishment purpose.

3. MATERIAL AND METHODS

Samples of Malikhore Formation for the study of geotechnical properties of aggregate were collected from Lasbela and Khuzdar districts of Balochistan. Approximately 40kg fresh piece of rock was collected as per ASTM [15] specification. Specific standard methods of ASTM were adopted for geotechnical properties. Thin sections were prepared by using Buehler Petro-thin device and were studied using Laborlus Pols microscope and photographed on Leica Microsystem, (DFC 280).

4. RESULTS AND DISCUSSION

4.1 Geotechnical Properties

4.1.1 Bulk Saturated Surface Dry (SSD) Specific Gravity

The specific gravity (SSD) of an aggregate is measured according to ASTM [16] specification. In this procedure aggregate has been soaked and absorbed water into its pore spaces; then excess, free surface moisture has been removed so that the particles are still saturated, but surface of the particle is essentially dry is known as SSD specific gravity.

Bulk specific gravity, $SSD = A / (A - B)$

A = mass of saturated surface dry aggregate

B = weight of aggregate submerge in water

Bulk gravity (SSD) of sample collected is presented (Table 1) and shows minor difference in minimum, average and maximum values (Fig. 2). The range of SSD of all collected samples is classified as normal-weight aggregate.

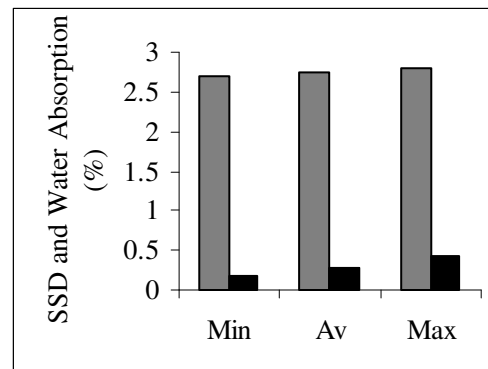


Fig. 2: Minimum, average and maximum values of SSD and water absorption of Malikhore Formation.

4.1.2 Water Absorption

The content of absorbed water in the samples of study area is low (Table 1), probably due to less porous nature of limestone. All the samples have water absorption within 2% specified limits of [16,17]. Samples of Malikhore Formation have low water absorption capacity with little variation (Fig. 2), because all fractures and pores are filled-up by calcite. The assumption also gets support from the negative correlation matrix ($r = -0.146$) between the SSD and water absorption.

Table 1. Geotechnical characteristics of Malikhore Formation, Lasbela and Khuzdar areas, Balochistan.

110

	SSD	Water Ab.%	Los Angles	Soundness	Clay Lumps	Flakiness	Elongation
M1	2.72	0.42	24	0.9	0.22	5.5	4.2
M2	2.73	0.31	26	1.2	0.23	6.3	5.2
M3	2.72	0.28	28	1.2	0.24	7.5	6.1
M4	2.72	0.17	23	1.4	0.12	7.9	5.6
M5	2.77	0.24	25	1.3	0.32	8.8	9.2
M6	2.71	0.19	21	0.9	0.41	5.7	5.9
M7	2.81	0.25	24	1.7	0.32	9.3	6.1
M8	2.75	0.28	23	1.7	0.31	5.3	6.7
M9	2.71	0.34	21	1.3	0.3	5.9	6.3
M10	2.74	0.31	22	1.3	0.25	6.2	4.8
M11	2.76	0.29	21	1.3	0.21	6.8	4.7
Min	2.71	0.17	21	0.9	0.12	5.3	4.2
Max	2.81	0.42	28	1.7	0.41	9.3	9.2
Av.	2.74	0.28	23.45	1.29	0.26	6.83	5.89

111

112

4.1.3 Sieve Analysis

113

114

115

116

117

118

119

120

121

122

123

124

125

126

127

128

129


130

131

In material science, distribution of particle size is important, both in the concrete and asphalt. In Portland cement and concrete (PCC), the proper gradation will helps to assess workability, strength, durability and shrinkage; while it also facilitates to evaluate stiffness permeability, moisture susceptibility and fractional and fatigue resistance in the hot mix design [18].

Gradation curve is one of the simplest ways to demonstrate variation in the size of aggregate. Fuller and Thompson's [19] equation is also used, in which size of the sieve is raised to the nth power (usually taken as 0.45) and convenient for determining the maximum density line and adjusting gradation [18]. In the graph, size of the aggregate is plotted on x-axis in descending order; while passing percent is plotted on y-axis. A diagonal straight line is created from zero to the maximum size of the aggregate (Fig. 3). This 0.45 power curve of gradations provides a concept to appraise the distribution of different sized aggregate. Based on variation in the size of aggregate, five different types of size distribution curves are familiar, namely, dense graded, gap-graded, uniformly graded, well graded and open graded (Fig. 3). The average grain size curve of Malikhore Formation illustrate that coarse fraction have affinity with uniform gradation while finer materials show resemblance with open gradation. In spite of the fact, the gradation curve is within the upper and lower limit of coarse aggregate (Fig. 3). The size is good enough for durable and high strength concrete,

132 because it requires less cement for binding. Similarly, the size is convenient to bear freeze-
 133 thaw damage.
 134

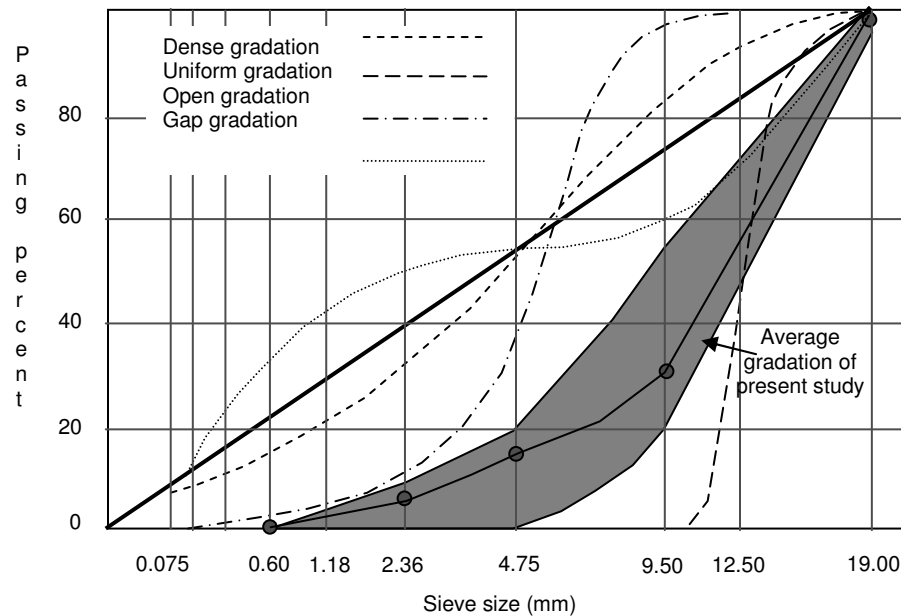

135
 136 **Fig. 3. Types of gradation graphs and graph of study area, based on average grain**
 137 **size. Shaded area specify upper and lower limit of coarse aggregate.**
 138

139 **4.1.4 Los Angeles Abrasion**

140 Los Angeles (LA) abrasion test provides a clear perception for abrasion, hardness,
 141 degradation and disintegration of the aggregate. Estimate of LA abrasion is essentially
 142 required to judge the firmness of either the concrete or asphalt to bear wear and tear right
 143 from their manufacturing and during their utilization for long time. In the present study, ASTM
 144 [20] procedure is applied for estimation of LA abrasion. Retained of 19 and 9.5mm sieves
 145 (5kg) are used for the measurement. Mass of the coarser aggregate (>1.7mm) is noted, after
 146 the specified 500 revolutions of the drum, to calculate exact mass of aggregate. Loss
 147 percent values of the samples of study area are ranged between 21 to 28% (Table 1). The
 148 LA values of present study, lower than of maximum permissible limit (<50%) signifies that
 149 the values are good enough not only for concrete cement to control mixture problems but
 150 also it will minimize the production of excessive fine particles during working, which would
 151 ultimately reduce the risk of possible environmental hazards.
 152

153 **4.1.5 Unconfined Compressive Strength**

154 Unconfined compressive strength (UCS) of construction material is probably the most
 155 important index properties for the evaluation of mechanical behavior of rocks [21]. The UCS
 156 provides a clear perception regarding the selection of material for appropriate civil structure.
 157 Study of UCS is also effective to calculate energy required to cut the sample [22,23].
 158 Furthermore, it is used to select the appropriate excavation technique. In the present study,
 159 sample M3 was cored to measure UCS as per ASTM [24] specifications and was noted
 160 6,179psi. The moderate value of UCS is mainly due to presence of calcite filled veins. The
 161 strength of rock decreases in the presence of joints and veins [25].
 162

163 **4.1.6 Soundness (NaSO₄ method)**

164 Sulphate soundness is commonly employed for measuring the freezing and thawing
 165 durability of aggregates. Freezing and thawing characters of an aggregate is assessing by

repeatedly submerging the aggregate in a sulphate solution and oven drying. In the present work, NaSO₄ soundness method is opted for the studies, as per ASTM [26] specifications. The result of soundness is given in Table 1. It shows minimum value 0.9%, while 1.7% is the maximum. The average is found to be 1.29. The present study indicates that the entire samples are good, and have low soundness as compared to [26] recommended value of 12%.

4.1.7 Alkali Silica Reactivity

The ASR is one of the most familiar harmful incidents in concrete. The ASR is chemical reaction occurs between the reactive SiO₂, present in the aggregate and the alkalis (K₂O + Na₂O), common in the Portland cement. During the hydration of cement, Ca ions are easily integrated in the hydrating concrete but K and Na remain in fluid, which eventually increase the pH >13. The samples of present study are relatively pure limestone and apparently they are free from any reactive silica. In the presence of high amount of Ca ions, Na and K are not able to compete with Ca because of slow rate of migration, thus the chances of gel swelling is minimum and the resultant concrete is free from cracking [27]. Similarly, high Ca obstructs diffusion of silicate ions from the reactive grains [28].

Evaluation of the potential reactivity of aggregate is assessed from the graph (Fig. 4). Graph is constructed by plotting silica (Sc) versus reactivity (Rc). Area of the graph is divided into two portions, plots in the left hand side show innocuous material for concrete while right side plots belong to deleterious materials. The division is not straight but a curve line demarcates boundary between them (Fig. 4). On the basis of silica and reactivity, deleterious aggregate are further divided into potentially deleterious aggregates (top) and less deleterious material (below). All the samples plotted within the domain of innocuous material with low reactivity (Fig. 4).

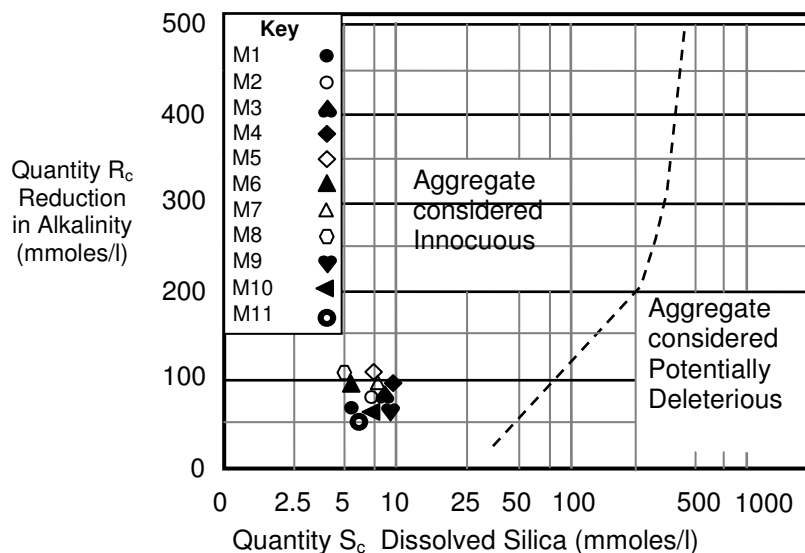


Fig. 4. Sc versus Rc plot of Malikhore Formation aggregates (Field after ASTM # C-289-87).

4.1.8 Clay Lumps and Friable Particles

The clay lumps and friable particles is defined as any soft friable or clay like material, which can easily be removed when squeezed between the thumb and forefinger or will disintegrate

into small pieces when aggregate is immersed in water for a short period. Coating clay which sticks on the surface of aggregate will hinder the bonding between cement and aggregate. If the quantity of clay in aggregate exceeds from the maximum allowable limit (1.5%), it will harmfully influence on the durability and strength of concrete. Excessive clay lumps present in aggregate interfere with the bonding between asphalt and aggregate. This will cause stripping and pop-outs in the pavement [29].

The method follows the procedure of ASTM [30], for determination of clay lumps and friable particles in aggregate. The carbonate rocks of Malikhore Formation are relatively pure and clays are present in minor quantity. Results of clay lumps and friable particles of current study are given in Table 1; shows low amount of fine particles, thus it is good for asphalt and concrete.

4.1.9 Loose/Rodded Density

The loose and rodded density of an aggregate is another important property that depends upon mainly on specific gravity. The term loose unit density refers to weight of an oven-dry aggregate required to fill a container of known volume without any external force to compress the mass. It is measurement of volume of aggregate with the volume of voids spaces [31].

The average bulk density of aggregate, commonly used in normal weight concrete ranges from 1.2 to 1.75g/cm³. Values of the loose density mainly rely on density of the aggregate, surface texture, size and shape of the particles. Aggregates lacking predominance of one size will usually have a higher bulk density in contrast to those having preponderance of one size particles present [32]. High amount of flaky and angular shape particles reduces the bulk density of material.

Method of ASTM [33] is adopted for present study and calculated bulk loose and rodded densities (Fig. 5). Bulk loose density of the samples of study area is in the range of 1.41-1.68g/cm³, while rodded density varies between 1.64 and 1.89g/cm³. The mutual relation in form of correlation matrix between loose and rodded densities is noted good ($r = 0.71$). The plots of bulk loose and rodded densities show good relationship, however minor variation in the densities is mainly due the shape and density of the aggregate itself (Fig. 5). Well compacted aggregates are stronger and require less amount of cement in the concrete. In the construction of road, nearly 110% rodded unit weight is generally considered to be the upper limit of coarse aggregate [31]. The samples of the study area are also suitable material in this regard, because the average compaction is 115%.

4.1.10 Flakiness and Elongation Index

Shape of the aggregate is very crucial in the cement concrete. Proper shaped (equant) aggregates is needed for easy workability, deformation resistance and proper compaction. However, quantity and proportion of different shaped particles largely relies on the nature of civil work [34]. Poor strength of concrete is obtained in the presence of high amount of flat and elongated particles in the aggregate. Both of them are unable to bear heavy load and fracture more easily than the other aggregate particles [35]. Such flat and elongated particles also require more water for binding, which ultimately influence the mechanical characteristics of concrete. Furthermore, aggregate with high proportions of flat and elongated particles may also cause segregation in the fresh mix, which leads to low durability and strength of the concrete. In the pavement structure, proportion of aggregates is nearly 90-95% of the total volume of hot-mix asphalt (HMA). For this reason, shape of the aggregates; appreciably affect the overall quality and durability of the pavement [36]. The high quality of HMA mixture is largely depends upon the presence of rough and angular aggregates [37]. Cubical shaped aggregates are most advantageous in HMA, while flat and elongated particles are adverse because they tend to break during compaction and under heavy traffic [38].

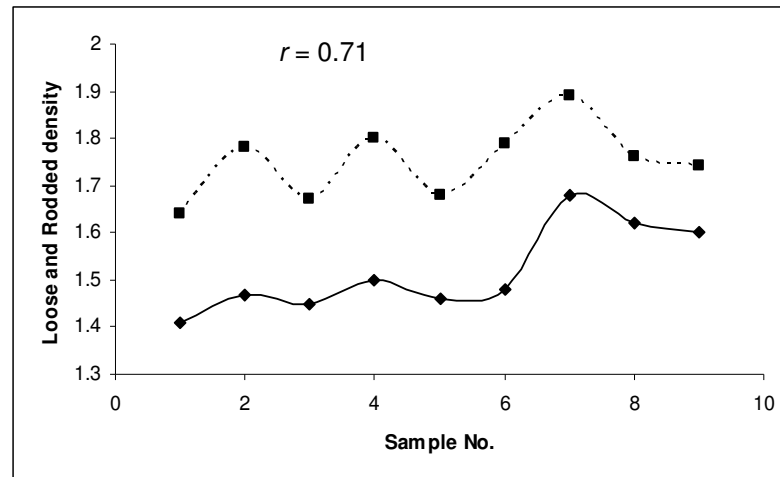


Fig. 5. Relationship between loose and rodded density of corresponding samples.

The samples of the study area show av. 5.89% elongated and 6.83% flat particles (Table 1) and are within the specified limit of 15%. Percentage of flat and elongated particles in the sample is largely depends upon the composition, nature of bedding, compactness, hardness and influence of tectonism prevailed in the area [39] and also on way of crushing.

4.1.11 Petrography

Petrography is the systematic study of rock specimens in thin-section. It is an integral part of material science, widely used to assess and classifies aggregate for civil works, under ASTM [40] specifications. The petrographic study plays a supportive role in order to assess the results and interpretation of other geotechnical tests [41]. It is very essential parameter to infer about the composition of an aggregate. The study can be used to identify weak and reactive minerals, known to be linked with poor performance of aggregate [42]. During the petrographic study, examination of weathered and altered particles of the aggregate is also intended. Joints, cracks and other fracture are noticed during petrographical observations on microscopic level.

4.1.11.1 Sample M3


The thin section study revealed it as a micritic limestone. Calcispheres are also common. Patches of hematite are common in the entire body. A number of micro veins are also common, which are filled with pure sparry calcite (Fig. 6a). At places, stylolitic structure is also seen, reflecting Jurassic tectonism in the area. Fossils are not present.

4.1.11.2 Sample M6

The limestone is grey in colour and fine crystalline. Rounded hematitic bodies are also visible in the groundmass of the thin section. Few fossils and their fragments are visible. The thin section area is full of fractures, which are healed up by hematite (Fig. 6b). Some sort of rock cleavage is also developed at microscopic level indicating complexity in the structure of the rocks.

4.1.11.3 Sample M7

288 It is a fine crystalline (micritic) and relatively pure limestone. Numerous laths and cavity-filled
 289 hematite are visible. The sample has several criss-cross rhombohedral calcite filled veins
 290 (Fig. 6c).
 291

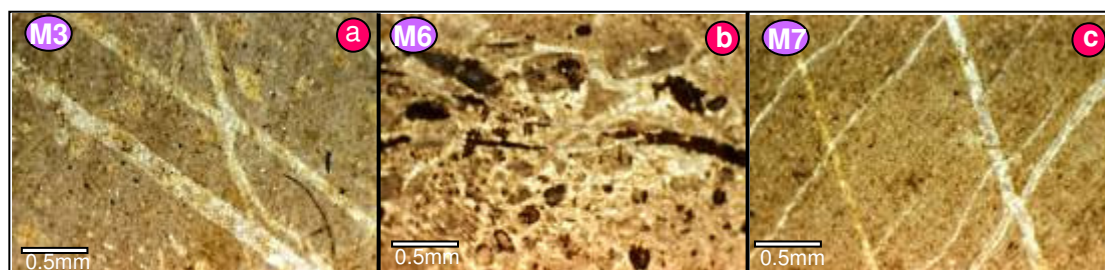


292
 293 **Fig. 6. Photomicrographs of Malikhore Formation of the study area. Sample numbers**
 294 **are marked on top left.**
 295

296 4.2 Dimension Stone

297 The limestones of Malikhore Formation are famous for its durability and archetypal
 298 appearance. Its versatility in colour and texture makes it suitable for floor tiles, facing stone
 299 and window sills. In the study area, it is mined from different localities of the Lasbela and
 300 Khuzdar districts. Majority of extracted stones are processed in Marble City Gadani,
 301 Balochistan, where 130 processing units are in working. Monolama and diamond saws are
 302 used to cut irregular blocks into large slabs (Fig. 7a). These blocks are mainly exported to
 303 China and Saudi Arabia. Slabs are further cut into demanded sizes by small cutters into tiles,
 304 tabletops and kitchen tops etc. (Fig. 7b).

306 A single unit in the Marble City is capable to produce annually 9,600 tons dimension stone.
 307 Presently 130 units are fully operative in the Marble City. Per ton expenses include, mining
 308 US\$ 42, logistics US\$ 16, and cutting and other require US\$ 8.5. The net expenditure on
 309 one ton dimension stone is US\$ 66.5. These blocks are being exported at a rate of 120-
 310 130US\$ per ton. It estimates generation of approximately 100US million \$ per annum from
 311 Marble City, Gadani.

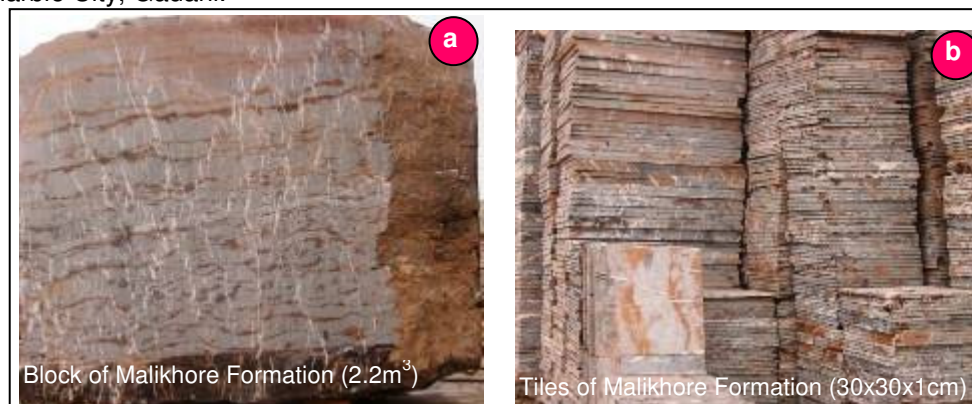

312
 313
 314 **Fig. 7. Block and tiles of the Malikhore Formation.**
 315

5. CONCLUSION

Malikhore Formation of Jurassic age is exposed in the Lasbela and Khuzdar areas, Balochistan. These rocks are widely used to fulfill the local demand for building and road constructions as well as dimension stones which have good export potential abroad. The average specific gravity (SSD) of Malikhore Formation is 2.74, which classified it as normal-weight aggregate. It also has low water absorption capacity (av. 0.28%). The distribution of different sizes of the crushed material showed that the average gradation curve is within the ASTM specification and can be classified as open-dense graded. The size is good enough for durable and high strength concrete and convenient to bear freeze-thaw damages. The Los Angeles abrasion loss (23%) and unconfined compressive strength (6,179psi) designate it as suitable material to bear load. The mean value of soundness test of present study is 1.29, much lower than ASTM recommended value (12%). The samples of Malikhore Formation have low estimated silica (Sc) and reactivity (Rc) potential and are plotted within the domain of innocuous material. It is safe to use for cement concrete and asphalt with no hazard of expansion. Clay lumps and friable particles are very low (av. 0.26%). Rodded density of aggregate indicates compactness nearly 115%. The amount of flat and elongated particles is 6.83 and 5.89% respectively. The petrographic study revealed micrite/biomictite type of texture with numerous veins filled with calcite and iron oxides. All the above geotechnical properties are within the ASTM specified limits and are suitable material for concrete, asphalt and dimension stones. Tiles and blocks of Malikhore Formation have good demand in the local and foreign markets as dimension stone. This sector approximately earns US\$ 100 million per annum from the export.

REFERENCES

- [1] Burke F, Azam M, Huda SN, Hamza S, Haque Q. Quality of Life and Cause & Effect Relationship with Resources and Facilities- Case Study of Selected Towns in Karachi. Pak. J. Soc. Sci. 2008;5(3): 268-279. ISSN: 1683-8831.
- [2] Koloski JW, Schwarz SD, Tubbs DW. Geotechnical Properties of Geologic Materials. Engineering Geology in Washington: Washington Division of Geology and Earth Resources Bulletin. 1989;1(78). Available: Geotech\Geotechnical Properties of Geologic Materials.htm
- [3] Harries R, Saxton B, Coventry K. The geological and geotechnical properties of earth material from central devon in relation to its suitability for building in 'cob'. Annual Conference of the Ussher Society, 1995.
- [4] Millogo Y, Morel JC, Traoré K, Ouedraogo R. Microstructure, geotechnical and mechanical characteristics of quicklime-lateritic gravels mixtures used in road construction. Construction and Building Materials. 2012;26(1):663-669. DOI: 10.1016/j.conbuildmat.2011.06.069.
- [5] Zaigham NA, Mallick KA. Sub surface continuation of the ophiolites in the Bela Plain of Balochistan, Pakistan. Ofioliti. 1994;19: 269-278.
- [6] Naseem S, Naseem S, Sheikh SA. Geochemical evaluation of depositional environment of Parh Limestone, Southern Pab Range, Balochistan, Pakistan. Proceeding of SPE/PAPG Annual Technical Conference, Islamabad, 2005:104-111
- [7] Gnos E, Immenhauser A, Peters TJ. Late Cretaceous/early Tertiary convergence between Indian and Arabian plates recorded in ophiolites and related sediments. Tectonophysics. 1997;271: 1-19.
- [8] Shah SMI. Stratigraphy of Pakistan. Memoir GSP, Quetta. 2009;22:381.
- [9] Fatmi AN, Hyderi IH, Anwar M, Mengal JM, Hafeez A, Khan MA. Stratigraphy of Mesozoic rocks of Southern Balochistan, Pakistan. GSP, Rec. 1990;85.

- 369 [10] Shah SMI. 2002. Lithostratigraphic Units of the Sulaiman and Kirthar Provinces, Lower
370 Indus Basin, Pakistan. GSP Rec. Quetta, 2002;107: 62.
- 371 [11] Ahsan SN, Malick KA, Khan A. Litho-Microlithofacies of Loralai Formation, Kharrari Nai
372 Section, Lasbela District Balochistan, Pakistan. Karachi Univ. Jour. Science. 2000;28(2):
373 89-107.
- 374 [12] Kazmi AH, Abbasi IA. Stratigraphy and Historical Geology of Pakistan. National Centre
375 of Excellence in Geology: University of Peshwar; 2008.
- 376 [13] Williams MD. Stratigraphy of the Lower Indus Basin, West Pakistan. World Petroleum
377 Cong., 5th, New York 1959;1(19):77-390.
- 378 [14] Woodward JE. Stratigraphy of the Jurassic System, Indus Basin. Stand. Vacuum Oil Co.
379 1959;2-13 (unpubl. rept.)
- 380 [15] ASTM Subcommittee D4.30. Standard Practice for Sampling Aggregates (D 75).
381 Developed by; Annual book of ASTM standards. 2009;4.03.
- 382 [16] ASTM Subcommittee C09.20. Standard Test Method for Density, Relative Density
383 (Specific Gravity), and Absorption of Coarse Aggregate (C127). Annual book of ASTM
384 standards. 2012;4.02.
- 385 [17] National Highway Authority, Pakistan. Surface courses, Item No. 305-1, NHA General
386 Specifications, 1998.
- 387 [18] Roberts FL, Kandhal PS, Brown ER, Lee DY, Kennedy TW. Hot Mix Asphalt Materials,
388 Mixture Design, and Construction. National Asphalt Paving Association Education
389 Foundation. Lanham, MD. 1996.
- 390 [19] Fuller WB, Thompson SE. The laws of proportioning concrete. Transactions of the
391 ASCE, ASCE. 1907;59:6-143.
- 392 [20] ASTM Subcommittee C09.20. Standard Test Method for Resistance to Degradation of
393 Small-Size Coarse Aggregate by Abrasion and Impact in the Los Angeles Machine (C
394 131). Annual book of ASTM standards. 2006;4.02.
- 395 [21] Romana M, Vásárhelyi B. A Discussion on the Decrease of Unconfined Compressive
396 Strength between Saturated and Dry Rock Samples. Polytechnic University of Valencia,
397 Spain; 2007.
- 398 [22] Roxborough FF. The role of some basic rock properties in assessing cuttability. Seminar
399 on Tunnels –Wholly Engineered Structures, Australian Federation of Civil Celebrants
400 (Institution of Engineers Australia: Canberra), 1987;1-21.
- 401 [23] Adebayo B. Evaluation of Cuttability of Selected Rocks in South-Western Nigeria. AU
402 J.T. 2008;12(2):126-129.
- 403 [24] ASTM Subcommittee D18.12. Standard Test Method for Compressive Strength and
404 Elastic Moduli of Intact Rock Core Specimens under Varying States of Stress and
405 Temperatures (D 7012). Annual book of ASTM standards. 2010;4.09.
- 406 [25] Hoek E. Strength of jointed rock masses. Géotechnique. 1983;23(3): 187-223.
- 407 [26] ASTM Subcommittee C09.20. Standard Test Method for Soundness of Aggregates by
408 Use of Sodium Sulfate or Magnesium Sulfate(C 88). Developed by; Annual book of
409 ASTM standards. 2005;4.02.
- 410 [27] Ferraris CF. Alkali-Silica Reaction and High Performance Concrete. Building and Fire
411 Research Laboratory: National Institute of Standards and Technology Gaithersburg, MD
412 20899:1995.
- 413 [28] Chatterji S, Thaulow N. Some Fundamental Aspects of Alkali-Silica Reaction. 11th
414 International Conference on Alkali-aggregate reaction, Quebec, Canada. 2000;21-29.
- 415 [29] American Association of State and Highway Transportation Officials. 2004. Standard
416 Method of Test for Clay Lumps and Friable Particles in Aggregate (AASHTO T 112).
417 2004.
- 418 [30] ASTM Subcommittee C09.20. Standard Test Method for Clay Lumps and Friable
419 Particles in Aggregates (C142). Annual book of ASTM standards. 2010;4.02.

- 420 [31] Aschenbrener TB. Bailey Method for Gradation Selection in Hot-Mix Asphalt Mixture
421 Design. Transportation Research e-circular E-C044, Transportation Research Board,
422 Washington, DC 20001; 2002. ISSN 0097-8515.
- 423 [32] ACI Committee E-701. Aggregates for concrete. ACI Education Bulletin E1-99 Series,
424 Farmington Hills, Michigan: American Concrete Institute;1999.
- 425 [33] ASTM Subcommittee C09.20. Standard Test Method for Bulk Density (Unit Weight) and
426 Voids in Aggregate (C 29). Annual book of ASTM standards. 2009;4.02.
- 427 [34] WAPA. 2002. Material-aggregate, Washington asphalt pavement association,
428 Available: Inc. file:///H:/los%20angeles/3_2%20Materials%20-%20Aggregate.htm.
- 429 [35] Basyigit C. The physical and mechanical properties of heavyweight concretes used in
430 radiation shielding. Journal of Applied Sciences. 2006;6(46):762–766.
- 431 [36] Maerz NH. Technical and computational aspects of the measurement of aggregate
432 shape by digital image analysis. Journal of Computing in Civil Engineering, ASCE.
433 2004;18(1):10-18.
- 434 [37] Masad E, Olcott D, White T, Tashman L. Correlation of fine aggregate imaging shape
435 indices with asphalt mixture performance. Transportation Research Record, No. 1757,
436 TRB, National Research Council, Washington D.C., 2001;148-156.
- 437 [38] Naidu D, Adishesu PS. Influence of Coarse Aggregate Shape Factors on Bituminous
438 Mixtures. IJERA. 2011;1(4): 2013-2024.
- 439 [39] Briesen H. Aggregate Structure Evolution for Size-Dependent Aggregation by Means of
440 Monte Carlo Simulations. KONA. 2007;25:180-189.
- 441 [40] ASTM Subcommittee C09.65. C 295. 2012. Standard Guide for Petrographic
442 Examination of Aggregates for Concrete (C295). Annual book of ASTM standards.
443 2012;4.02.
- 444 [41] New York State Department of Transportation Materials Bureau. Aggregate Source
445 Acceptance Procedure (7.42-1). Materials Method NY 29; Albany, Ny 12232; 2007.
- 446 [42] Shrimmer FH. Engineering Geology of Aggregates British Columbia. 2001. Accessed
447 March 2013.
448 Available:[http://www.empr.gov.bc.ca/Mining/Geoscience/PublicationsCatalogue/Papers/
449 Documents/P2004-2-20.pdf](http://www.empr.gov.bc.ca/Mining/Geoscience/PublicationsCatalogue/Papers/Documents/P2004-2-20.pdf)