

AISI 300-series alloys and modified versions of these alloys. Such alloys, which are based on type 304 stainless steel, generally contain 16 to 26% Cr, 8 to 22% Ni, and small amounts of other alloying elements such as molybdenum, titanium, niobium, and nitrogen [2]. The role of Cr is to passivate. Even though Cr is generally a less noble metal than iron, this passivation converts the steel from being a 'normal', active alloy that fits within the electrochemical series, to a passive alloy with a vastly improved corrosion resistance [3].

Many researchers have worked on stainless steels. Tanimu [4] investigated the effects of welding and heat treatment on mechanical properties of duplex stainless steel using GMAW and SMAW processes. He found out that welding and heat treatment really affected the mechanical properties of the alloy. Loto, et al [5] investigated the resistance and susceptibility of austenitic stainless steel, Type 304, exposed to strong tetraoxosulphate (VI) acids (2 and 5M concentrations) contaminated with sodium chloride at ambient temperatures. The results obtained showed the weak corrosion resistance/appreciable corrosion susceptibility of the stainless steel alloy to the test environments. Hence, it is therefore pertinent to investigate the influence of some welding parameters on the corrosion behavior of austenitic stainless steel in alkaline medium.

This research is aimed at investigating the corrosion behaviour of a welded ASS immersed in an alkaline sodium hydroxide medium.

Materials and experimental procedure

Materials/equipment

ASS was locally sourced for at Kakuri Market in Kaduna State, Nigeria, and its chemical composition was analyzed in National Metallurgical Development Centre, Jos as shown in table 4. Other materials that were used are: stainless steel electrode wire of 0.9mm, acetone, distilled water and paper grit of 340, 400, 600 and 800 and the selected medium; sodium hydroxide (NaOH). The equipment were; Gas Metal Arc Welding machine, Digital Weighing Balance, Grinding Machine and Phenom ProX Scanning Electron Microscope.

Experimental procedure

A 120mm x 15mm x 3mm dimension of ASS was used for this analysis. The sample was cut to produce a plain face sample for butt welding, with a root opening of 2mm. The butt welding

method was used as shown below in figure 1. The number of passes used was one on the specimen according to Omiogbemi, et al [6]. Specimens were cleaned of dirt and oil using paper grit (340, 400, 600 and 800) and acetone. Grinding machine was used to grind their surfaces prior to and after welding.

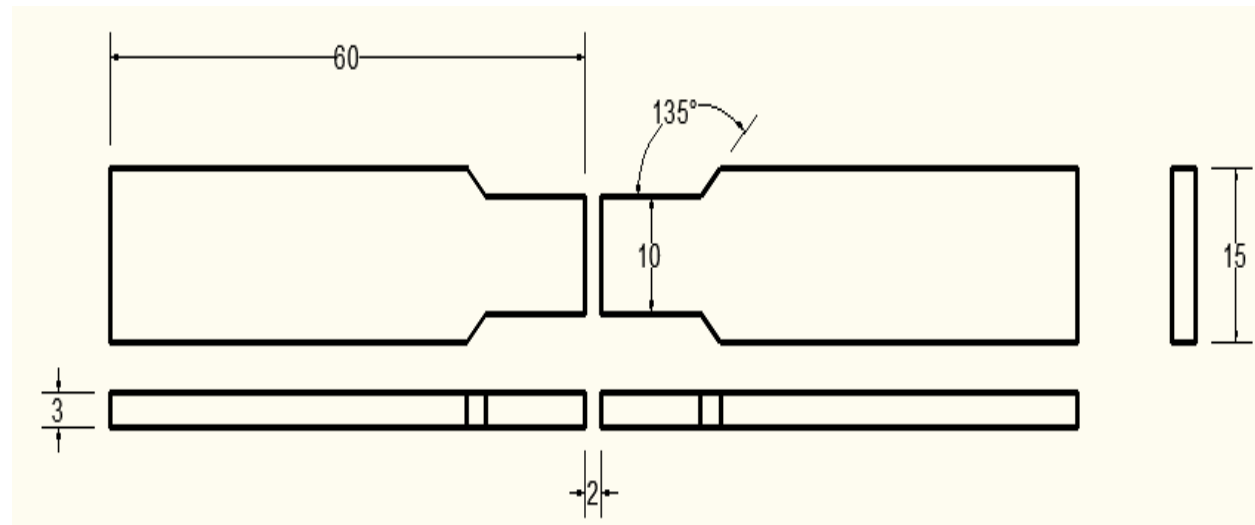


Figure 1: Standard Joint Preparations for plain face sample for welding

Factorial design of experiment for the welding parameters

Three factors were selected to investigate the corrosion behaviour of welded ASS in sodium hydroxide medium. Speed (S), Current (I) and constant Voltage (E) which are represented as A, B and C respectively are the parameters. The corrosion behaviour was investigated by varying these factors at two levels (2^2), high (+1) and low (-1) with a centre point (0) in the experimental runs (Tables 1 and 2). The interactions between these factors were studied and optimization was done using three dimensional plots and cube plots according to Okibe [7]. Design Expert software 6.0.6 was used to generate the experimental runs and for the statistical analysis of weight loss in milligram of the ASS in the NaOH in an interval of eight (8) for forty (40) days as shown in figure 3 and figure 4

Table 1: Factors and levels used in the factorial design for the welding parameters;

Welding	Symbol	Unit	Factor Levels
---------	--------	------	---------------

parameters			Low (-)	Centre (0)	High (+)
Speed	S	cm/min	20	30	40
Voltage	E	Volts	230	230	230
Current	I	Amp	90	100	110

Table 2: Design matrix for the welding parameters of the welded ASS

Std	Run	A: Speed (cm/min)	B: Current (Amp)	C: Voltage (volts)
1	1	20	90	230
3	2	20	110	230
5	3	30	100	230
4	4	40	110	230
2	5	40	90	230
6	6	30	100	230

Weight loss measurement

The samples of ASS were immersed in 1dm³ of volumetric flask containing solution of 20.89 cm³ of NaOH as prepared in accordance with Yawas [9] for 40 days. The test specimens were taken out of the alkaline medium after every 8 days, wash with distilled water and acetone, air dried and re-weighed. The digital weight balance machine of sensitivity of 0.0001g was used to assessed the weight loss of the samples.

Sample labeling

Table 3: Sample Labeling.

Sample C	Control sample not welded and not immersed (As received)
Sample C ₁	Sample welded with 20cm/min speed and 90A current at constant voltage of 230V
Sample C ₂	Sample welded with 20cm/min speed and 110A current at constant voltage of 230V
Sample C ₃	Sample welded with 30cm/min speed and 100A current at constant voltage of 230V
Sample C ₄	Sample welded with 40cm/min speed and 110A current at constant voltage of 230V
Sample C ₅	Sample welded with 40cm/min speed and 90A current at constant voltage of 230V

Results and discussion

Chemical composition of research material.

103 The actual chemical composition of the research material was determined using X-ray
104 florescence test.

105 Table 4: Chemical Composition (wt %) of ASS sample

Element	C	Si	Mn	P	S	Cr	Ni	Mo	Cu	Fe
Wt %	0.12	0.54	1.36	0.03	0.01	20.120	8.34	0.18	0.25	Bal
	2	0	0	0	9		0	8	7	

106
107 The result in table 4 shows that the material is an austenitic stainless steel type 304. This is due
108 to the presence of high percentage of chromium (Cr) and nickel (Ni) as major alloying elements,
109 low percentages of Carbon (C) and other elements in accordance with the AISI standard grade.

110 Results of factorial design

111 Table 5: ANOVA for the factorial model for speed and current at a constant voltage for NaOH

Source	Sum of Squares	DF	Mean Square	F Value	Prob>F	Remark
Model	2.163X10 ⁻⁵	3	7.209X10 ⁻⁶	50.44	0.0195	Significant
A	5.063X10 ⁻⁶	1	5.063X10 ⁻⁶	35.42	0.0271	Significant
B	1.056X10 ⁻⁵	1	1.056X10 ⁻⁵	73.91	0.0133	Significant
AB	6.002X10 ⁻⁶	1	6.002X10 ⁻⁶	42.00	0.0230	Significant
Residual	2.858X10 ⁻⁷	2	1.083X10 ⁻⁷			
Lack of Fit	4.083X10 ⁻⁸	1	4.083X10 ⁻⁸	0.17	0.7532	Not Significant
Pure Error	2.450X10 ⁻⁷	1	2.450X10 ⁻⁷			
Cor Total	2.191X10 ⁻⁵	5				

112
113 The analysis of variance (ANOVA) is presented in table 5. From the results of the ANOVA,
114 model F-value of 50.44 implies that the model is significant. There is only a 1.95% chance that a
115 "Model F-Value" could occur due to noise. Values of "Prob > F" less than 0.0500 indicate model
116 terms are significant. Since model terms A, B and AB are all less than 0.0500, it therefore means
117 that they are all significant model terms.

118


119

120 Table 6: Design matrix and responses of welding parameters of ASS in NaOH environment

Std	Run	A: Speed	B:Current	C:Voltage	WL ₈	WL ₁₆	WL ₂₄	WL ₃₂	WL ₄₀
-----	-----	----------	-----------	-----------	-----------------	------------------	------------------	------------------	------------------


		(cm/min)	(Amp)	(volts)	(mg)	(mg)	(mg)	(mg)	(mg)
1	1	20	90	230	0.0024	0.0012	0.0024	0.0016	0.0035
3	2	20	110	230	0.0009	0.0004	0.0011	0.0012	0.0037
5	3	30	100	230	0.0020	0.0021	0.0018	0.0017	0.0028
4	4	40	110	230	0.0008	0.0002	0.0006	0.0004	0.0020
2	5	40	90	230	0.0016	0.0059	0.0053	0.0040	0.0094
6	6	30	100	230	0.0009	0.0014	0.0010	0.0024	0.0034

121
 122 Presented in Table 6 is the variation of the selected welding parameters (factors) affecting the
 123 behaviour of ASS in 0.5M concentration of sodium hydroxide medium and the corresponding
 124 weight loss in milligrams obtained after each experimental run was performed on the welded
 125 ASS immersed for 40 days in an interval of 8 days. The results show that experimental run four
 126 (4) gave the least weight loss values for eight (8) days and forty (40) days as 0.0008mg and
 127 0.0020mg respectively at a welding speed of 40cm/min, welding current of 110 Amperes at a
 128 constant voltage of 230 volts. This implies that experimental run four (4) gave the minimal
 129 weight loss value. This shows a good corrosion resistance of the steel to the environment since
 130 the least weight loss was observed with it.

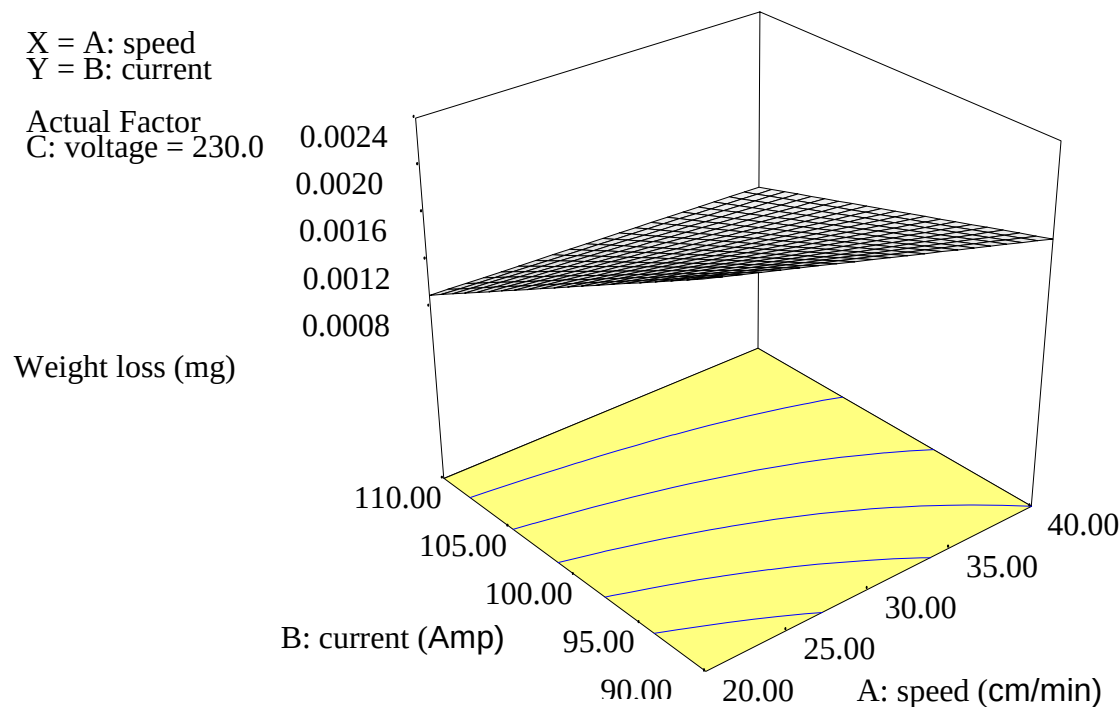

131

132 Figure 2: Response surface plot for ASS immersed in NaOH for 8 days

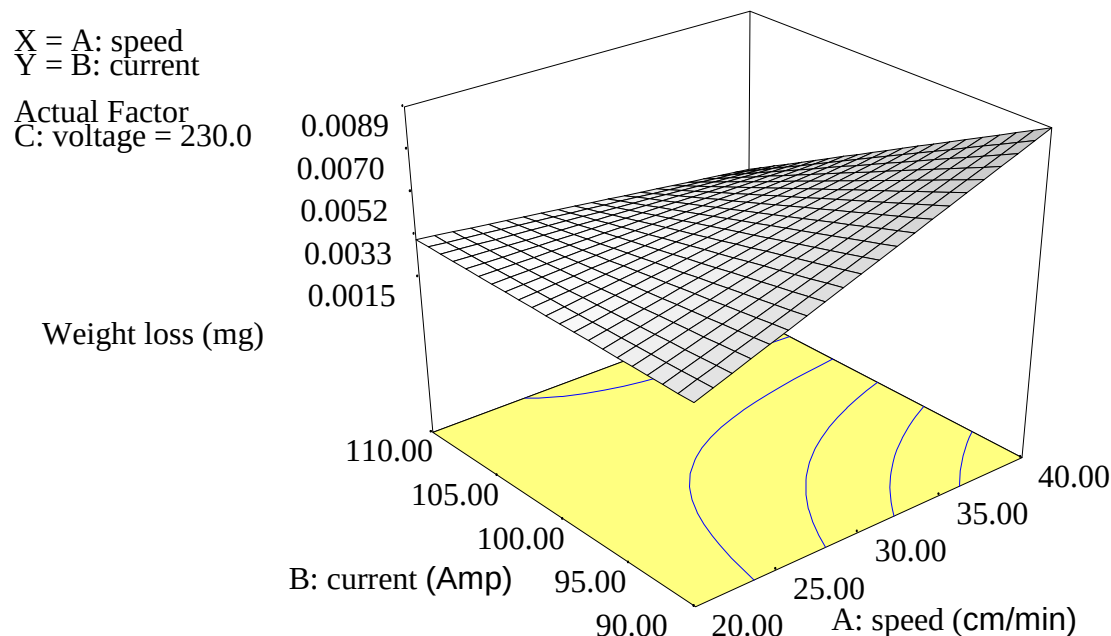


133

134 Figure 3: Response surface plot for ASS immersed in NaOH for 40 days


135 Figures 2 – 3 are the response surface plots to show the interactions between the speed and
 136 current at constant voltage on the ASS immersed in 0.5M concentration of NaOH for eight (8)
 137 days and forty (40) days. From the results obtained, the interactions of these two variables on the
 138 ASS were clearly shown. Increase in welding current and welding speed at constant voltage gave
 139 the optimum performance of the ASS in the environment (that is, at speed of 40cm/min and
 140 current of 110Amp). The least weight loss values for eight (8) days and forty (40) days were
 141 0.0008mg and 0.0015mg at a welding speed of 40cm/min and welding current of 110 Amperes at
 142 a constant voltage of 230 volts as shown in figures 2 and 3 respectively. These substantiate the
 143 best welding parameters' values to obtaining an optimum performance of an ASS occurs when
 144 the current and the speed were moderately high.

145

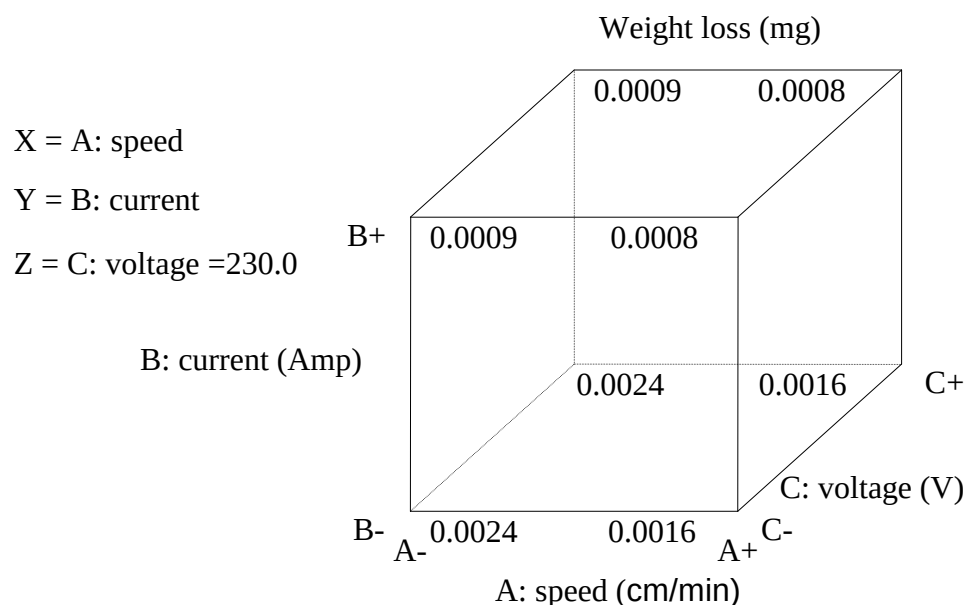

146

147 Figure 4: Cube plot for ASS in NaOH for 8 days

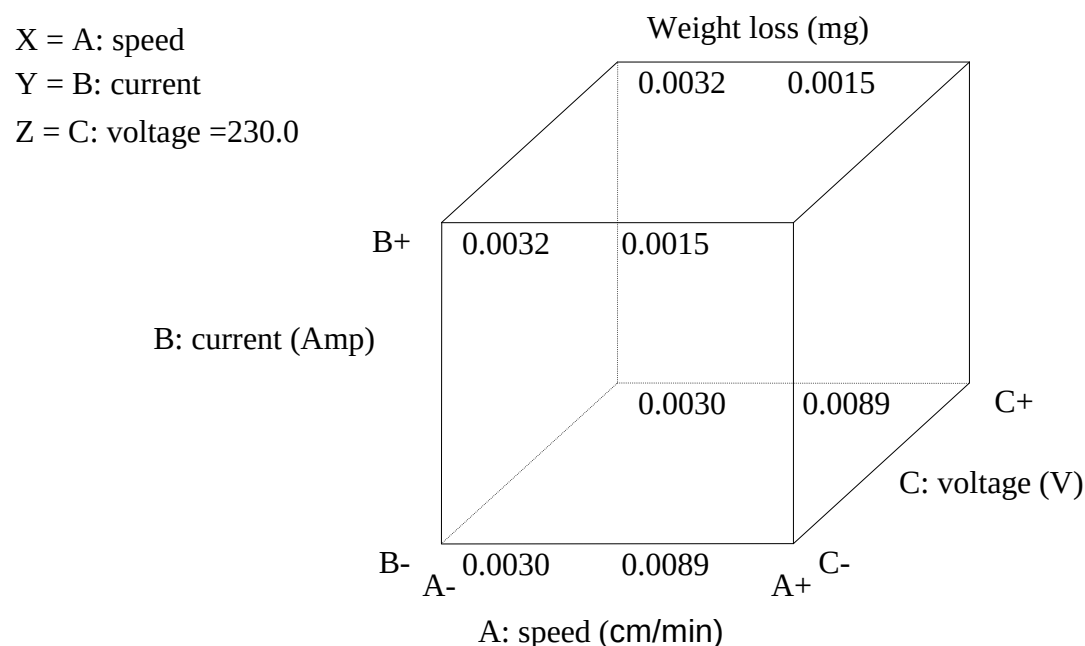

148

149 Figure 5: Cube plot for ASS immersed in NaOH for 40 days

150 Shown in figures 4 – 5 are the cube plots of the effect of the interactions of current, speed and
 151 constant voltage on corrosion behaviour of the ASS immersed in 0.5M concentration of NaOH
 152 for eight (8) days and forty (40) days. In application, an ASS has a high corrosion resistance in
 153 an alkali medium because ASSs exhibit active-passive behaviour in sodium hydroxide solution.

At room temperature and concentration up to 50%, sodium hydroxide exhibit low uniform corrosion rate as posited by Khatak and Balev [10]. The results show that at constant voltage of 230V, a varied speed from 20cm/min to 40cm/min and a varied current from 90Amp to 110Amp, weight losses for eight (8) days and forty (40) days were obtained as follows;

For eight (8) days are; 16% (C+, B-, A+), 0.08% (C+, B+, A+), 0.24% (C+, B-, A-) and 0.09% (C+, B+, A-) while for forty (40) days are; 0.89% (C+, B-, A+), 0.15% (C+, B+, A+), 0.30% (C+, B-, A-) and 0.32% (C+, B+, A-). It was observed at the end of this analysis that ASS has a strong corrosion resistance in an alkali environment since the percentages of deterioration for the days observed for the corrosion process was non-uniform and it was minimal. This clearly shows that NaOH solution causes stress corrosion cracking (SCC) on ASS since the rate of deterioration is gradual as established by Prawoto, et al [11].

The equations that defines each of the responses obtained in the factorial design for speed and current at a constant voltage for NaOH medium for forty (40) days are given by Equation 1 to 5 below; [That is, the weight loss (WL) for eight (8) days, sixteen (16) days, twenty-four (24) days, thirty-two (32) days and forty (40) days];

$$WL_8 = +0.013108 + 1.97500 \times 10^{-4}A - 1.10000 \times 10^{-4}B + 1.75000 \times 10^{-6}AB \dots\dots\dots 1$$

$$WL_{16} = -0.022008 + 1.33750 \times 10^{-3}A + 2.05000 \times 10^{-4}B - 1.22500 \times 10^{-5}AB \dots\dots\dots 2$$

$$WL_{24} = -0.010267 + 9.10000 \times 10^{-4}A + 1.05000 \times 10^{-4}B - 8.50000 \times 10^{-6}AB \dots\dots\dots 3$$

$$WL_{32} = -0.013317 + 8.40000 \times 10^{-4}A + 1.40000 \times 10^{-4}B - 8.00000 \times 10^{-6}AB \dots\dots\dots 4$$

$$WL_{40} = -0.038017 + 2.00500 \times 10^{-3}A + 3.90000 \times 10^{-4}B - 1.90000 \times 10^{-5}AB \dots\dots\dots 5$$


Where;

A Represents Speed (cm/min).

B Represents Current (Amperes).


Scanning electron micrograph of the samples

The micrographs of the samples, as taken by scanning electron microscope, are presented in figures 6 to 8

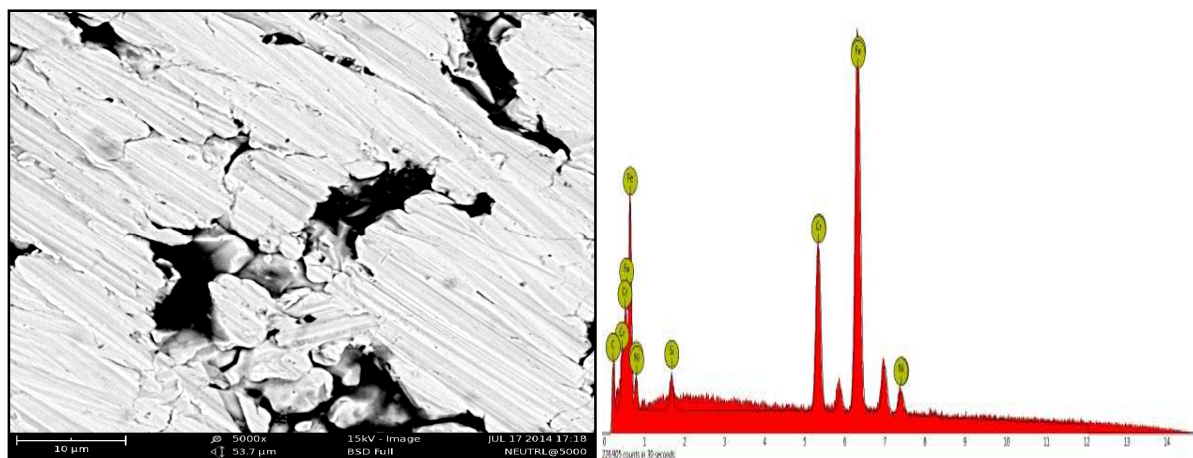


182

183 Figure 6: Micrograph of the control sample (as received) with EDS profile.

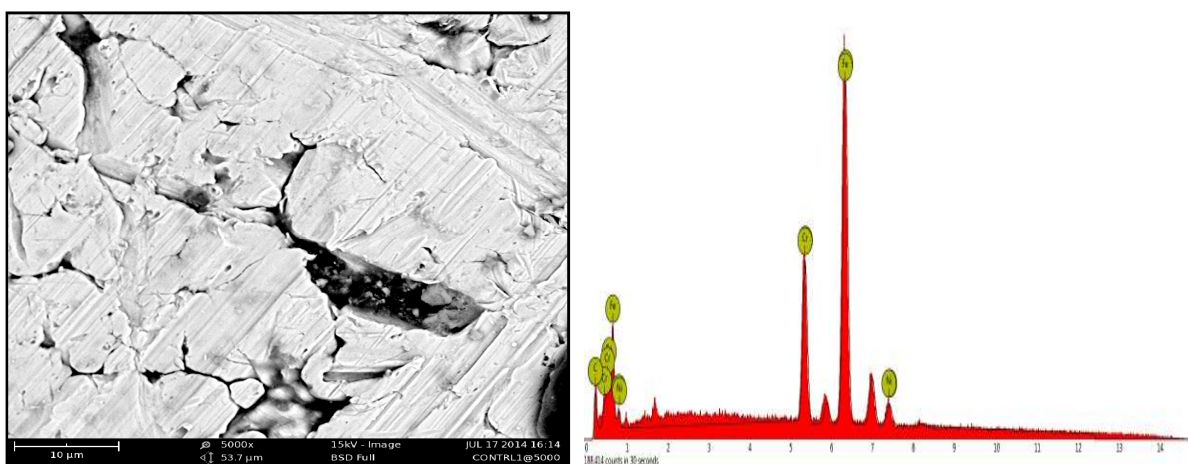

184

185 Figure 7: Micrograph of the control sample immersed in NaOH for 40 days with EDS profile

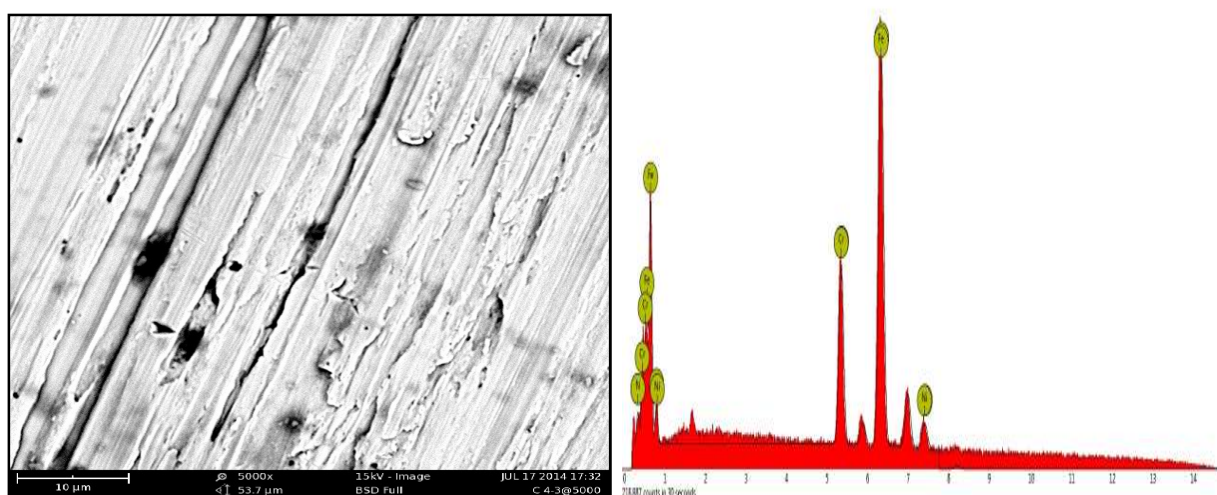

186

187 Figure 8: Micrograph of FZ C₄ welded and immersed in NaOH for 24 days with EDS profile

SEM was used to study the microstructure of the welded and as received samples. Figures 6 to 8 show the SEM micrographs of the samples with their respective EDS profiles indicating iron to have the highest percentage as the base metal followed by chromium as the highest alloy element. Figure 6 shows the SEM micrograph of as received sample of ASS. It is observed that the microstructure clearly shows a fine grain boundary and is an indication of a better blending of parent material and the alloying elements. Also, figure 7 shows the SEM micrographs of unwelded ASS sample immersed in 0.5M of NaOH for 40 days indicating uniform corrosion of the metallic structure. While figure 8 shows a good weldment of ASS immersed in 0.5M of NaOH for 24 days indicating a high integrity weldment that has less corrosion attack on the structure.

Tensile properties of the samples

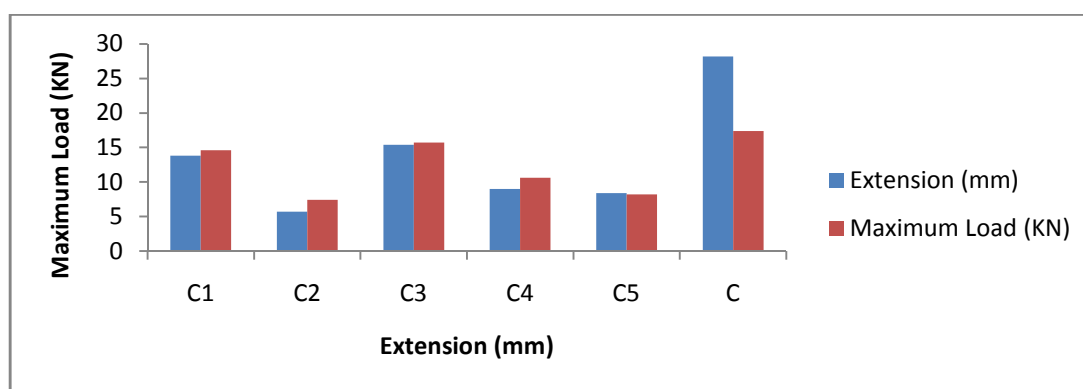


Figure 9: Load-Extension of tensile test on ASS immersed in NaOH medium.

From figure 9, it can be seen that for samples immersed in 0.5M of NaOH the parameters has a significant role in the tensile strength of the welded ASS joint. The variation on the maximum load and extension is a function of the weld parameter and it is observed that the highest values are obtained at weld parameter C_3 which is current, $I = 100A$, speed = 30mm/s followed closely by weld parameter C_1 . It is seen that the immersion of the metal in 0.5M of NaOH has a sizable deteriorative effect on the steel which in turn affects the tensile strength when compared to the control which also shows its susceptibility to stress corrosion cracking as posited by Prawoto et al [11].

Conclusions

In conclusion, corrosion susceptibility of ASS in sodium hydroxide medium during the exposure time period studied is due to the aggressiveness of the hydroxyl ion (OH^-). Also, surface

passivation of ASS observed in sodium hydroxide is attributed to film stability in the compound. The interaction effect of speed and current at constant voltage on ASS immersed in sodium hydroxide medium evaluated using factorial design of experiments shows that at moderately high speed and current, a lower corrosion rate of the material is experienced in the alkaline environment. The materials' susceptibility to stress corrosion cracking was conspicuous after a successful corrosion analysis in the medium with a tensile test results.

REFERENCES

- [1]. Plaut, L. R., Herrera, C., Maribel, E. D., Rios, R. P., Padilha F. A. A short review on wrought austenitic stainless steels at high temperatures: processing, microstructure, properties and performance. *Mat. Res. vol.10 no.4, 2007, 1980-5373*
- [2]. Internet link: Introduction to Stainless Steels.ASM International, Materials Park, Ohio, USA www.asminternational.org (Retrieved 21st October, 2015).
- [3]. Claus, Q.J. (2011). Stainless steel and corrosion. First edition, *Damstahl*. Retrieved on 26th October, 2014 from <http://www.damstahl.com/Files/Billeder/2011/PDF/BOOK/book.pdf>.Pp 81-84.
- [4]. Tanimu, I. (2013). Effects of welding and heat treatment on the mechanical properties of duplex stainless steels. Published *M.Sc thesis in mechanical engineering department, ahmadu bello university, zaria, nigeria*.pp 1-25.
- [5]. Loto, R. T., Loto, C. A., Popoola, A. P. I., Ranyaoa, M. Corrosion resistance of austenitic stainless steel in sulphuric acid. *International journal of physical sciences* Vol. 7(10), 2012. pp. 1677 – 1688. (www.academicjournals.org/IJPS).
- [6]. Omiogbemi, I.M.B., Yawas, D.S., Dagwa, I. M., Okibe, F.G. Effects of gas metal parameters on the corrosion behaviour of austenitic stainless steel in acidic medium. *International journal of scientific and engineering research. Vol.6, issue 9 September, 2015, 1327-1335*
- [8]. Okibe, F.G.. Preparation and characterization of activated carbons from brachystegia eurycoma and prosopis africana seed hulls for solid phase adsorption of dyes. *Ph.D Dissertation, chemistry department, abu, zaria, nigeria, 2014.*

- 241 [9]. Yawas, D.S. Suitability assessment of some plant extracts and fatty acid vegetable oil as
 242 corrosive inhibitors. *Ph.D Dissertation, mechanical engineering department, abu, zaria,*
 243 *nigeria, 2005.*
- 244 [10]. Khatak, H.S. and Balev, R. (2002). Corrosion of austenitic stainless steels: mechanism,
 245 mitigation and monitoring. Woodhead publishing, elsevier. Retrieved on 20th august, 2014
 246 from http://books.google.com.ng/books?id=f_4qdx8f_tac&source=gbs_navlinks.
- 247 [11]. Prawoto, Y., Sumeru, K. and Wan Nik, W. B. Stress corrosion cracking of steel and
 248 aluminum in sodium hydroxide: field failure and laboratory test. *Advances in materials*
 249 *science and engineering, 2012.* Article ID 235028, pp1-8. Retrieved on 21st August, 2014
 250 from <http://www.hindawi.com/journals/amse/2012/235028/>