

Silver nanoparticles as inhibition agent of cooling tower microorganisms

ABSTRACT

Silver nanoparticles are widely studied and the antibacterial activity is well-known. Although several methods of synthesis have been described, this article reports simplest procedure using low cost reagents and low consumption of energy, where silver nitrate is reduced by nitrate ions in aqueous solution from pH 10.60 to 11.02. A relatively controlled dispersion of sizes was achieved and particles presented sizes between 49 and 76 nm dependent on pH. Solutions of these particles were used to incubate a mixture of *Pseudomonas* spp. ATCC and *Pseudomonas* spp. recovered from a water well. All the particles were effective against inhibition of these bacteria after 3 hours of incubation. Specifically, 49 nm particles reached suitable efficiency after 120 min even diluted 50 or 10%, whereas particles with 65 nm demonstrate to have an efficient inhibitory effect on *Pseudomonas* spp. at 10 or 100% of concentration after 140 min of incubation. Results obtained with both sizes proving that the contact time (140 min) to reduce the colony forming units (CFU) per milliliter ($\times 10^5$) to values lower than 1 is an adequate time for applications in water treatments of cooling towers. Additionally, the procedure here followed with low cost and low energy facilitates the design of advanced antimicrobial treatments for cooling towers at industrial levels.

Keywords: Silver; nanoparticles; cooling tower; *Pseudomonas*; biocide.

1. INTRODUCTION

Cooling towers are semi-open systems where water continuously circulates and some amount of mass is lost by evaporation, therefore, water must be fed to recover this loss of mass.

Some problems in cooling towers are associated to the water such as corrosion and growth of biofilm (i.e. microorganisms). Biofilms are formed because cooling towers are open circuit permanently exposed to microorganisms like algae, fungi and bacteria, which are transported through the water stream during the cooling process [1,2] and this produces a technical problem because microorganisms could form a bio film capable to retain organic matter from and inorganic powders (like sand and dust) from the atmosphere, thus limiting the flow rate of circulating water or reducing the heat transfer from the metallic tubes to the water due to the isolating character of biofilms [2-4].

On the other hand, the large volume of water flowing is in contact with the air and the temperature of water is maintained between 25°C y 35°C, this provides a suitable environment to promote the fast growth of microorganisms, which receive nutrients from the atmosphere [3]. Among the large list of microorganisms detected in cooling towers, *Pseudomonas* spp. is a human pathogen group. This bacteria is responsible for producing diseases and is considered as a public health problem. In cooling towers, *Pseudomonas* spp. has been clearly identified [4].

In order to control microbial action in cooling towers, biocide agents are added to water and these are classified as oxidizing and non-oxidants [5]. The former oxidize organic matter like cell walls, enzymes and proteins in relatively low concentrations (representative oxidizing agents are chlorine gas, calcium hypochlorite, bromide and potassium permanganate), however, these biocides produce side effects in the towers such as corrosion and they have dependence on pH [6]. On the other side, the non-oxidizing agents interfere in cell metabolism pathways. Examples of these products are pentachlorophenolate, sodium hypochlorite, copper salts and quaternary ammonium compounds. Generally, high concentrations of these agents are needed to eliminate microorganisms [6], thus environmental side effects are also involved. In several cases, a special combination of biocides must be considered in water treatments of cooling towers, but significant issues to take into account are the environmental risks as well as the toxicity for workers handling these compounds. Besides, the evaluation of costs is required, therefore alternative biocides overcoming these problems are needed.

Silver nanoparticles have emerged as a suitable alternative biocide. Even that silver was empirically used as a water purifier by Greek civilizations [7], the first scientific report demonstrating the antiseptic effect was Credé in 1881 and 1901 [8]. Recent investigations revealed that silver possesses a biocide effect, which is increased when dimensions of the particles are in the nanometric scale due to the large surface/volume ratio. Further, the biocide effect of the metallic form -found in nanoparticles- is more efficient than the Ag^+ salt forms [7,9], and this biocide effect covers Gram positive and negative bacteria, as well as viruses [8].

The aim of this work was to prepare silver nanoparticles with uniform size and to evaluate the efficiency to control the growth of *Pseudomonas* spp., which are of interests in cooling towers maintenance.

2. MATERIAL AND METHODS

2.1 SYNTHESIS OF SILVER NANOPARTICLES

Analytical grade reagents were used without special purification to prepare the following solutions: 6×10^{-4} M ascorbic acid, 3×10^{-3} M potassium citrate, 0.10 M sodium hydroxide and 0.10 M silver nitrate.

Silver nanoparticles were prepared by reducing silver nitrate with ascorbic acid in an aqueous medium [10] where citrate ions were added as passivating agents as follows: 50 mL of ascorbic acid solution were mixed with 50 mL of potassium citrate, and sodium hydroxide was added to adjust the pH value between 10 and 11. The resulting solution was heated in a water bath to keep the temperature at 35 °C, and then, 1.0 mL of silver nitrate was added at the rate of one drop per minute. Finally the mixture was kept at 35 °C for 15 minutes under stirring. Thereafter, the resulting colored solutions were stored in dark sealed plastic flasks.

In order to verify changes influenced by pH, solutions were adjusted to pH values equal to 10.60, 10.65, 10.71, 10.82 and 11.02. These values were used as labels to discuss experimental data.

Characterization of nanoparticles were conducted by UV-vis spectroscopy, dynamic light scattering (DLS), by transferring silver nanoparticles solutions to the quartz cell of the ThermoScientific UV-Vis spectrometer, model GENESYS, and the Malvern equipment, model Zetasizer Nano ZS. Transmission electron microscopy (TEM) images were obtained with a JEOL JEM1010 microscope, and the powder XRD pattern of the particles was obtained in a PANalytical Empyrean diffractometer.

2.2 Biocide assays

Strains of *Pseudomonas* spp. from ATCC and *Pseudomonas* spp. extracted from well water were grown separately in tryptic soy broth (TSB; BD) at 37 °C from 14 to 18 h. Thereafter, 100 µL hundred microliters of each culture was transferred to screw-cap tubes containing 10 mL of TSB, incubated at 37 °C for 4 to 6 h and then transferred again to a fresh tube with TSB, and incubated at 37 °C for 16 to 18 h. These cultures were then concentrated by centrifuging at 4 °C at 4,506.6 g for 10 min by using a refrigerated centrifuge. The pellet was resuspended in 1 mL of TSB. These suspensions were used to prepare one inoculum with a mixture of both *Pseudomonas* spp. strains.


To examine the bactericidal effect of silver nanoparticles on Gram negative bacteria, approximately 3×10^9 colony forming units per mL (CFU/ mL) of a mixture of *Pseudomonas* spp. strains were used to analyze different concentrations of silver nanoparticles freshly synthesized the same day when the antibacterial analyses were conducted. The analyses started with 1 mL of the mixed bacterial suspension inoculated into silver nanoparticles solution (10 mL) at concentrations of 10, 50, 100 % and incubated at room temperature between 0 to 140 min. The negative control was prepared with the bacterial mixture incubated in phosphate saline buffer. After 1, 30, 60, 80, 100, 120 and 140 min of incubation 100 µL of suspensions were plated on trypticase soy agar and grown at 37 °C between 14 and 18 h, then the numbers of colonies were counted.

3. RESULTS AND DISCUSSION

3.1 Nanoparticles characterization

Solutions of silver NPs presented higher turbidity and darker color at lower pH values, whereas the solution prepared at the higher value (pH = 11.02) resulted in a translucent dark yellow solution (Figure 1). The nominal content of silver in these solutions was calculated by relating the mass of

silver in the AgNO_3 solution and final volume of the reaction solution. This value is 0.108 mg/mL and this content is also referred as 100% in the antibacterial assays. UV-vis spectra of these solutions are depicted in Figure 1 and there a clear and intense absorption band in the visible region is detected. This signal is well-known and undoubtedly associated to the surface plasmon resonance (SPR) of silver nanoparticles, which is dependent on the size and morphology [11]. For particles with spheroid shape, the visible absorption is near 414 nm, as it occurs in the spectrum here obtained at pH 11.02. Conversely, nanoparticles with cubic or pyramidal shapes absorb visible light at higher values and the absorption is higher for more defined (sharper) edges [11]. In our experiment, reactions between pH 10.60 and 10.82 absorb between 424 and 437 nm (see Figure 1 and Table 1).

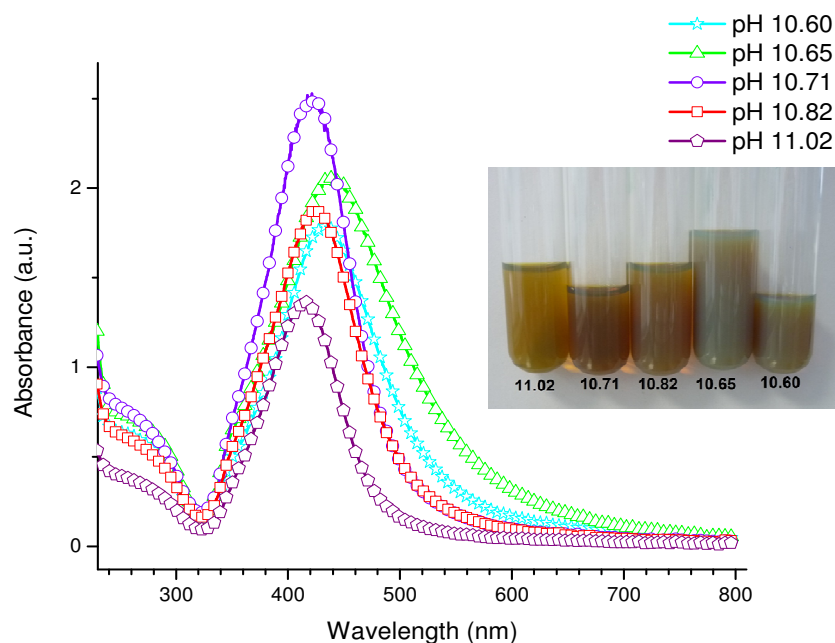

Figure

1. UV-vis spectra of silver nanoparticle solutions obtained at different pH values. The inset shows the typical color of these solutions.

Table 1. Relationship between pH of synthesis, maximum absorption wavelength and size of silver nanoparticles.


pH	Maximum absorbance peak (nm)	Diámetro (nm)
10.60	432	64
10.65	437	76
10.71	421	49
10.82	424	65

11.02	414	64
-------	-----	----

111

112 Although the increment in the wavelength can be associated to higher particle diameter [11,12] or to
 113 higher elongation (i.e. increase in the length to diameter ratio) [13], edges also promote this such
 114 shift. In order to identify if the SPR shift to the 424 and 437 nm range is due to particle changes or
 115 appearance of edges, a particle size analysis was conducted and revealed that diameters are
 116 between 49 and 76 nm (see Figure 2 and Table 1).

117

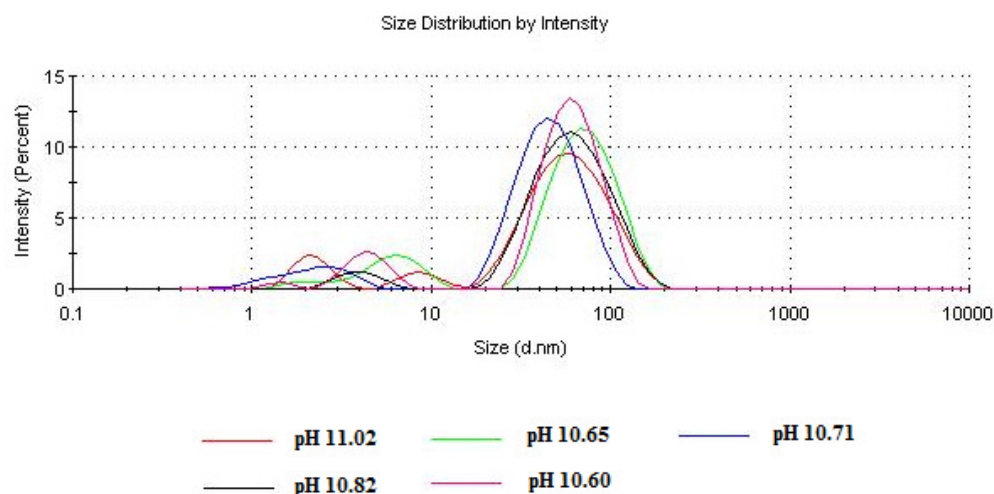

118

119 **Figure 2. Size distribution of silver nanoparticles synthesized at different pH values.**

120 If the particle size caused the SPR shift the to the lowest absorption wavelength in the sample
 121 prepared at pH = 11.02, the particle size should be the lowest, however, this sample contains
 122 particles with 64 nm in size, which are larger than those prepared at pH 10.71 (with lower particle
 123 size: 49 nm); furthermore, this size is similar to the samples prepared at pH 10.60 and 10.82.

124 Then, the appearance or definition of edges in silver nanoparticles could be the reason to promote the
 125 shift to the 424 and 437 nm range. To clarify this, the sample with the highest SPR (at 437 nm) was
 126 analyzed by TEM. The micrograph of this sample (Figure 3) presents aggregates of particles, which
 127 have elongated morphology and defined edges, and this can contribute to increase the SPR
 128 wavelength. Besides, the length to diameter ratio is larger than 2, and this elongation could also
 129 contribute to increase the absorption wavelength. On the other hand, the X-ray diffraction analysis
 130 indicated that the obtained pattern is in agreement with a silver lattice recorded in the IDCC card
 131 number 04-0783 (Figure 3).

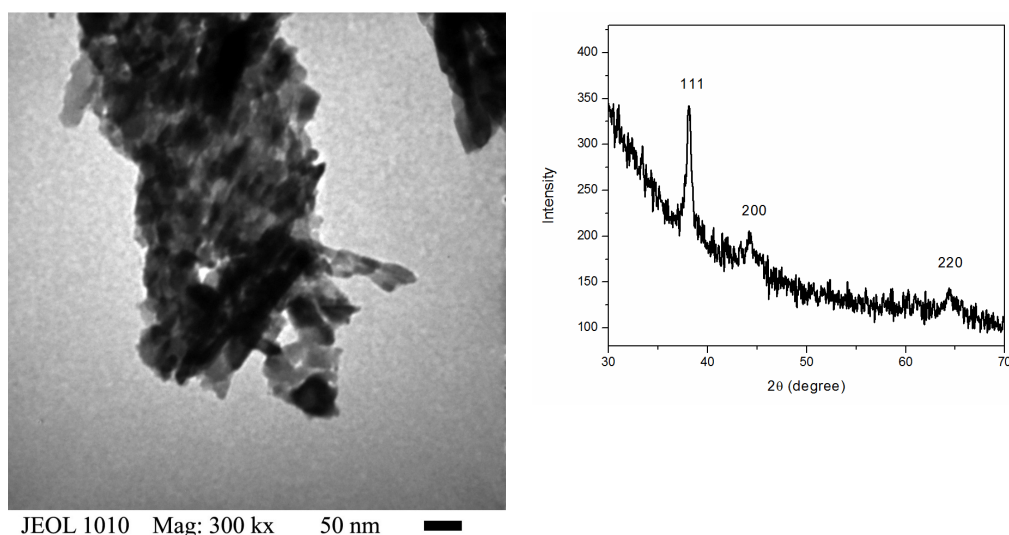


Figure 3. TEM micrograph and powder X-ray diffraction pattern of silver nanoparticles synthesized at pH= 10.65.

Despite the samples presented maximum absorption at different wavelengths, the values were not much different and procedure here followed to reduce the silver salts does produce silver particles with nanometric size.

3.2 Biocide assays

Antibacterial tests were performed against the Gram negative bacterium *Pseudomona spp.* on tripticase soy agar plates after their incubation in different concentrations of silver nanoparticles. Figure 4 shows the number of bacterial colonies grown on in the agar plates as a function of concentration and the size (related to the synthesis pH) of silver nanoparticles.

A previous experiment using solutions with 100% of nanoparticles (equal to 0.108 mg/mL) with size of 65 nm (prepared at pH = 10.82) provoked total inhibition of bacterial growth at 3 h of incubation. This effect was detected even when nanoparticles were diluted to 50 or 10% -due to this, the subsequent experiments were conducted at lower periods of incubation as recorded in Figure 4-, additionally, considering that the PBS negative control did not affect the bacterial growth after 3 h of incubation, the antibacterial activity can be associated directly to silver nanoparticles.


The antibacterial effect from silver nanoparticles has been related with their size [14], in this way small nanoparticles would have more efficient antibacterial activity, therefore the nanoparticles selected for this assessment were those with size near to 65 nm (obtained at pH 10.60, 10.82 and 11.02 as presented in Table 1) and 49 nm (obtained at pH = 10.71).

Results in Figure 4 showed that 1 h of incubation significantly reduces the growth with 49 nm particles, whereas those of 65 nm has a lower effect. Solution with 49 nm particles is generally the best with concentrations of 100 and 50%, however, after 120 min h the 10% solution present the same observed at 50 and 100%. This is an important result considering that a industrial level, if these particles were applied in cooling towers, the economic factor determines the usability. Regarding particles with 65 nm in size, a significant effect was observed after 100 min with 50% concentration, and the 10% concentration is only effective after 140 min.

The overall observation is that the smaller particles presented higher inhibition efficiency in a shorter time, however, the 65 nm particles -the larger particles studied- presented suitable antibacterial activity after 140 min, which is a suitable residence time for particles in cooling towers; additionally, this size can be obtained at diverse pH values as presented in Table 1. Then, particles prepared at

any pH between 10.60 and 11.02 are capable to act as efficient biocide after 140 min at any concentration between 10 and 100%.

166

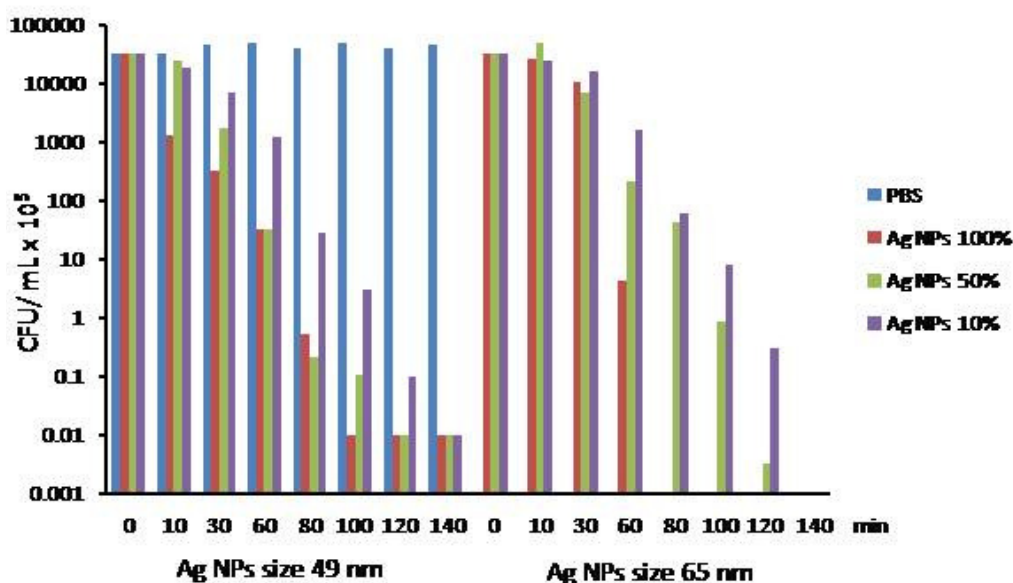

167

Figure 4. Colony forming units counted as function of nanoparticles size, concentration and incubation time.

170

4. CONCLUSION

171

172

Reduction of silver nitrate by citrate in aqueous solution between pH 10.60 and 11.02 produced particles ranging from 49 to 76 nm. The most recurrent size obtained in our experiment is near to 65 nm; these particles demonstrate to have an efficient inhibitory effect on *Pseudomonas spp.* at 10 or 100% of concentration after 140 min of incubation. Although particles with lower size reach a high efficiency in a shorter time (120 min), the time observed for 65 nm particles is more than enough for applications as inhibitory agent of *Pseudomonas spp.* in cooling towers. Therefore, the easy and fast synthesis of silver nanoparticles here reported is suitable to design advanced antimicrobial treatments for cooling towers.

180

181 **CONSENT (WHERE EVER APPLICABLE)**

182
183 Not applicable

186 **ETHICAL APPROVAL (WHERE EVER APPLICABLE)**

187
188 Not applicable.

190 **REFERENCES**

- 191
192 1. Turetgen I. Reduction of microbial biofilm formation using hydrophobic nano-silica coating on
193 cooling tower fill material. *Water SA*. 2015;41(3):295-99.
- 194 2. Doğruöz N, Minnos B, İlhan-Sungur E, Çotuk A. Biofilm formation on copper and galvanized
195 steel surfaces in a cooling-water system. *IUFS J Biol*. 2009;68(2):105-11.
- 196 3. Liu Y, Zhang W, Sileika T, Warta R, Cianciotto NP, Packman AI. Disinfection of bacterial
197 biofilms in pilot-scale cooling tower systems. *Biofouling*. 2011;27(4):393-402.
- 198 4. Aruliah R, Ting Y-P. Characterization of corrosive bacterial consortia isolated from water in a
199 cooling tower. *ISRN Corros*. 2014;Article ID 803219: 11 pages.
- 200 5. Boal A. Alternative to bromine improves cooling water microbial control and overall treatment.
201 2015 Cooling Technology Institute Annual Conference. New Orleans: Cooling Technology Institute;
202 2015. p. Paper Number TP13-09. [Available from: [http://www.miox.com/news-press/press-](http://www.miox.com/news-press/press-releases/alternative-to-bromine-improves-cooling-water-microbial-control-and-overall)
203 [releases/alternative-to-bromine-improves-cooling-water-microbial-control-and-overall](http://www.miox.com/news-press/press-releases/alternative-to-bromine-improves-cooling-water-microbial-control-and-overall)]
- 204 6. Verma P. Cooling water treatment frequently asked questions. 1st ed. Albatross Fine Chem
205 LTD. (Book Division); 2004.
- 206 7. Cruz Laitón J. Síntesis de nanopartículas de plata funcionalizadas con péptidos análogos de
207 lactoferrina con potencial antibiótico contra *Escherichia coli* 0157:H7. Master thesis. Universidad
208 Industrial de Santander; 2012.
- 209 8. Núñez NVA. Nanopartículas de plata como microbicidas: actividad y mecanismos de acción
210 contra la infección por el virus de inmunodeficiencia humana (VIH) y diferentes bacterias resistentes a
211 antibióticos. Ph. D. thesis. Universidad Autónoma de Nuevo León; 2010.
- 212 9. Takeuchi N. Nanociencia y nanotecnología: La construcción de un nuevo mundo átomo por
213 átomo. 1st ed. Fondo de Cultura Económica; 2012.
- 214 10. M. Martinez F, Zuñiga G. E, Sanchez Lafarga AK. Método de síntesis de nanopartículas de
215 plata adaptable a laboratorios de docencia relacionados con la nanotecnología. *Mundo Nano*.
216 2013;6(10):101-8.
- 217 11. Rycenga M, Cobley CM, Zeng J, Li W, Moran CH, Zhang Q, et al. Controlling the synthesis
218 and assembly of silver nanostructures for plasmonic applications. *Chem Rev*. 2011;111(6):3669-712.
- 219 12. Venugopal N, Mitra A. Influence of temperature dependent morphology on localized surface
220 plasmon resonance in ultra-thin silver island films. *Appl Surf Sci*. 2013;285:357-72.
- 221 13. Lin VS. A Porous Silicon-Based Optical Interferometric Biosensor. *Science*.
222 1997;278(5339):840-3.
- 223 14. Morones JR, Elechiguerra JL, Camacho A, Holt K, Kouri JB, Ramírez JT, et al. The
224 bactericidal effect of silver nanoparticles. *Nanotechnology*. 2005;16(10):2346-53.