

Original Research Article

Investigating Effect of Zinc Content on the Mechanical and Corrosion Responses of Al6063-SiC Composite

Abstract

Corrosion susceptibility of Al6063-SiC based composites is attracting unceasing concerns among researchers. The motive of this work was to investigate the influence of zinc content on the corrosion resistance and mechanical response of Al6063-SiC composites. Zinc was incorporated into the composite at 2, 4, 6, 8 and 10% volume fractions using the Two-step stir casting method. Thereafter, mechanical responses, optical microscopy and corrosion tests were carried out. The hardness tests revealed a general decrease pattern in the Brinell Hardness Number (BHN) of Al6063-SiC-Zn composite as the percentage of zinc increased. However, the Impact and tensile strengths of Al6063-SiC-Zn composite increased as the volume fraction of Zn increased. The relative enhancement in the mechanical responses of Al6063-SiC-Zn composites can perhaps be attributed to the manifestation of thickened and dense grain lines observed in the micrographs as the concentration of zinc in the composite increased. Corrosion tests in both sulphuric and saline media revealed a good influence of zinc on the composite. Therefore, the choice of zinc alloying element has potential for enhancing corrosion resistance of Al6063-SiC-Zn composites in brine and acid based environments with satisfactory contributions to their mechanical behaviours.

Keywords: Mechanical response, Corrosion, Microstructure, Zinc and Aluminium 6063

1.0 Introduction

The unprecedented research interests in the development and characterisation of Metal Matrix Composites (MMCs) with special focus on Aluminium Metal Matrix Composites (AMCs) is gaining prominence due to its high strength-to-weight ratio and the overall improvement in mechanical properties. This is equally responsible for the quantum leap in the choice of AMCs as potential composite material for engineering critical components, equipment and structures in industries (aerospace, oil and gas, automobiles, telecommunication, transportation, e.t.c).

Aluminium 6063 (Al6063) is one of the leading alloy materials for industrial applications. It has eight alloying elements namely: Silicon (Si), Iron (Fe), Copper (Cu), Manganese (Mn), Magnesium (Mg), Zinc (Zn), Chromium (Cr), Titanium (Ti) and finally the base metal, Aluminium (Al). When Silicon carbide is embedded in aluminium, the composite becomes a potential structural material for high temperature and aerospace applications due to its ability to increase service temperature and specific mechanical properties. Prominent example of

aluminium-silicon carbide (Al/SiC) based composites application is its use in automobile engine components (Aribo *et al*, 2011) such as valves, camshafts, gear parts, suspension arms e.t.c.

Laudable efforts have been made on the characterisation of mechanical properties of Al6063-SiC composites and the outcomes of researchers' studies have been tremendously promising. Aravindan (2014) examined the mechanical properties of Al6063-SiC by varying weight fractions of SiC. It was reported that the tensile strength and ultimate break load increased with rising weight fraction of SiC reinforcement. A study on the evaluation of the mechanical properties of coconut shell ash reinforced aluminium alloy composites was carried out by Daramola *et al* (2015). The incorporation of coconut shell ash in the composites was found to significantly improve its hardness and ultimate tensile strength properties. Hindi (2015) characterised mechanical behaviour of stir cast Al6063-SiC reinforced composites. While addition of SiC was found to increase hardness and tensile strength, ductility experienced a significant decrease. Experimental analysis of mechanical properties of Al6063-SiC composite carried out by Yadav *et al* (2015) showed noteworthy improvement in hardness and tensile strength of the composites as the volume fraction of SiC reinforcement increases. Mechanical behaviour of Al6063-SiC was studied by Pavani and Venkaiah (2015). Experimental results obtained showed that impact strength, hardness, shear and tensile strengths attained maximum value at 15% SiC. The increase in addition of SiC as reinforcement particles in Al6063 based metal matrix composites was observed to influence its hardness and tensile strength (Sandeep and Ashutosh, 2016).

Although Al6063-SiC is a good choice of material in several applications, major limitation has been attributed to its high corrosion susceptibility as the volume fraction of SiC content increases. Except on few instances where the incorporation of SiC promotes corrosion resistance of aluminium based composites (Aravindan and Balamurugan, 2016; Avdesh, 2011 and Ashok, 2015), it has been generally observed to affect AMCs corrosion behaviours immeasurably (Pinto *et al*, 2009; Singh *et al*, 2012; Kumar *et al*, 2012; Jamaludin *et al*, 2014 and Abbass *et al*, 2015). AMCs tend to corrode in a localized manner. Possible mechanisms for this include micro-galvanic coupling between the matrix and reinforcement or between the matrix and inter-metallic atoms as well as failure of the protective oxide film due to micro segregation of the alloying elements or micro crevices at the matrix reinforcement interface. Several additional research works have been conducted on the corrosion challenges of using

SiC as reinforcement particles in Al6063 composites. Nunes and Ramanathan (1995) examined the corrosion behaviour of silicon carbide metal matrix composites in sodium chloride solutions. Their experimental data revealed a monumental loss in weight of composites resulting in formation of deeper pits and microcrevices at higher volume fraction of SiC. The influence of SiC volume fraction on the corrosion behaviour of Al6063 and its monolithic alloy in NaCl solution was studied by Alaneme (2011). Results obtained showed clearly that the corrosion susceptibility of Al6063-SiC_p composites was much higher than the monolithic alloy. Bodunrin *et al* (2012) investigated the corrosion behaviour of Al6063-SiC in NaCl and H₂SO₄ media. Results obtained prior to solution heat treatment revealed that corrosion rates were more aggravated in both media at higher exposure time. However, thermomechanical treatment of the composites manifested enormous corrosion resistance ability in H₂SO₄ environment. The corrosion behaviour of hybrid reinforcement of silicon carbide and groundnut shell particles in Al-Mg-Si alloy matrix was investigated in salt and acid solutions (Alaneme *et al*, 2015). It was found that hybrid ratio with much higher silicon carbide showed a very low corrosion resistance in the media when compared to ratio with higher content of groundnut shell ash. In another work of Alaneme *et al* (2015), the high corrosion susceptibility of SiC as reinforcement was found to be slightly subdued by the incorporation of corn-cob ash as hybrid reinforcement in Al-Mg-Si composite.

The adoption of zinc as alloying element has been found to be beneficial to the corrosion resistance characteristics of non-ferrous based alloys (most especially magnesium based alloys). The effect of zinc concentration on the corrosion behaviour of Mg-Zn-Mn alloys was investigated by Yin (2008). The outcome of the study showed that zinc content enhances the anti-corrosion property of the alloy. The best anti-corrosion property was achieved with 1% Zn. Cai *et al* (2012) studied the influence of zinc on the corrosion behaviour of Mg-Zn alloys. Results indicated significant improvement on the mechanical properties and corrosion resistance at 5% weight fraction. Zinc was observed to form a protective film on the surface of the alloys thus exhibiting anti-corrosion property. The influence of zinc content on corrosion behaviour of ternary alloy Mg-Zn-Ca in a body fluid was examined by Geng *et al* (2012). Results showed that the Mg-Zn-Ca alloy with 4% zinc content has the best corrosion resistance when compared to the alloy at no or lower zinc volume fraction.

Sequel to the foregoing, this work was an attempt to investigate the effect of zinc addition on the corrosion resistance ability of Al6063-SiC composite without compromising its

mechanical properties. The choice of zinc as a reinforcing alloying element was motivated from the fact that it is unaffected by dry air; its excellent corrosion resisting characteristics and satisfactory potentials for improving tensile strength properties of non-ferrous alloys.

2.0 Methods and Materials

2.1 Composite production

Aluminium 6063 alloy was used as the matrix metal for the composite. The chemical composition analysis showed that the alloy has Si(0.4806%), Fe(0.2907%), Cu (0.008%), Mn(0.168%), Mg(0.4741%), Zn (0.001%), Cr(0.0005%), Ti(0.003%) and finally the base metal, Al(98.58%). The volume percentage by weight of Silicon carbide was 10% for all samples. Zinc was incorporated into Al6063-SiC composite at levels of 2, 4, 6, and 10% using the liquid metallurgy route (Two-Step Stir Casting technique) to produce Al6063-SiC-Zn composite. The Aluminium 6063 alloy having 82, 84, 86, 88 and 90 percents by weight, according to charge calculations were initially heated to 300°C for 45 minutes to aid the wettability of the alloy. The silicon carbide powder particles were also preheated to 1100°C and the zinc powder was preheated to 250°C further aid wettability of the alloy. Thereafter, the Al6063 particles were charged into a furnace at a temperature of 780°C and allowed to dissipate heat till the alloy was in a semi-solid state at about 600°C. During the semi-solid phase of the Al6063 alloy, the already preheated Silicon Carbide powder particles and Zinc powder particles were introduced into the alloy and it was stirred manually for 5 minutes.

2.2 Mechanical Testing

Brinell hardness test

The various specimens of the composite Al6063-SiC-Zn were reduced to cylindrical shapes with a length of 30 mm and diameter 8 mm. A Brinell hardness tester was used to determine the hardness of the specimens.

Tensile strength test

The tensile strength test was carried out using a tensometer. A lathe machine was used to machine the specimen, thereafter it was shaped into the standard test piece size, a cylindrical shape of diameter 5 mm and length 30 mm with dog bone-shaped ends. The initial length (L_0) and the initial diameter (d_0) of the specimen were measured before the test began. Thereafter,

the fractured specimens were arranged together and the final length (L_f) and diameter (d_f) of each specimen were measured.

Impact strength test

The Impact Strength of the various samples was determined using a pendulum-type Impact strength testing machine. Each specimen was cut and reduced to a standard test piece size of diameter 10 mm and length 120 mm. A groove of 2 mm was notched on each specimen to help the specimen fit into the machine.

2.3 Metallographic Test

The samples were grinded, polished and etched. Silicon Carbide paper of different grades used in the order 220, 320, 400 and 600 (i.e. coarse grade to fine grade) were placed on the grinding machine. A polishing cloth (selvt cloth) was swamped with a solution containing one micron of Silicon Carbide. Final polishing was performed by swamping the selvt cloth with 0.5 micron of Silicon Carbide until a mirror-like surface was attained. The mirror-like polished surface was etched in a solution containing 2% sodium hydroxide for 45 seconds.

The samples were viewed using an Accuscope microscope coupled with camera (Serial no. 0524011, Maker: Princeton, US) with magnification 400x.

2.4 Corrosion Test

The corrosion test was carried out in 3.5wt% NaCl (pH 6.7) and 0.3M H_2SO_4 (pH 0.71) solutions which were prepared following standard procedures. The specimens for the test were machined to a cylindrical shape with a diameter of 3 mm and height 8.2 mm and then mechanically polished with emery paper. The samples were then degreased with acetone and thereafter rinsed in distilled water. Finally, they were immersed into the prepared solution. The samples were exposed in the acidic and salt water environments for 30 days during which the pH, temperature and weight of each sample was recorded severally and systematically during the 30-day period. A pH meter having a thermometer was used to take the pH and temperature simultaneously. Mass loss was evaluated for each sample in

156 accordance with standard recommended practice ASTM G31 using a 4-digit accuracy
157 weighing balance.

158 **3.0 Results and Discussion**

159 ***3.1 Hardness Test and***

160 As shown in Figure 1, the composite Al6063-SiC-Zn had the highest hardness number of
161 26.2 on the Brinell Hardness Machine when it contained 2% zinc. With increasing percentage
162 of Zinc in the composite, the hardness number reduced to a minimum value of 20.8.
163 Interestingly, the composite hardness number rate turned positive at 8% zinc and

164 ***3.2 Impact Strength Test***

165 Figure 2 shows that as the percentage of zinc in the composite increased, the impact strength
166 also increased. Initially, when no zinc was added it had an Impact Strength of 7.888 Joules,
167 but had the lowest Impact Strength of 6.732 Joules when it contained 2% zinc. The Impact
168 Strength kept increasing till it peaked at a value of 9.52 Joules when it contained 8% zinc,
169 and then decreased again at 10% zinc.

170 ***3.3 Ultimate Tensile Strength Test***

171 Figure 3 shows the effect of increasing percentages of zinc on the tensile strength of the
172 composite. A close look at Figure 3 reveals that generally the Ultimate Tensile Strength
173 (UTS) increased with increasing percentage of zinc in the composite. However, when the
174 composite contained 6-8% zinc, the tensile strength remained the same. This further goes to
175 confirm previous reports that zinc does in fact increase the tensile strength of aluminium
176 alloy. The maximum UTS was reached when the composite contained 10% zinc with a value
177 of 110 MPa.

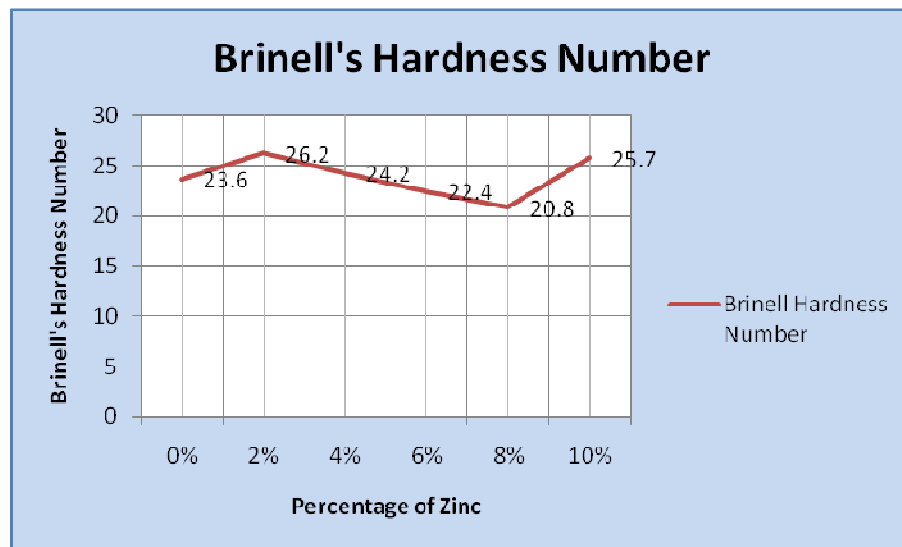


Fig.1: Relationship between the percentage of Zinc in Al6063-SiC-Zn and the Brinell's Hardness Number of the composite.

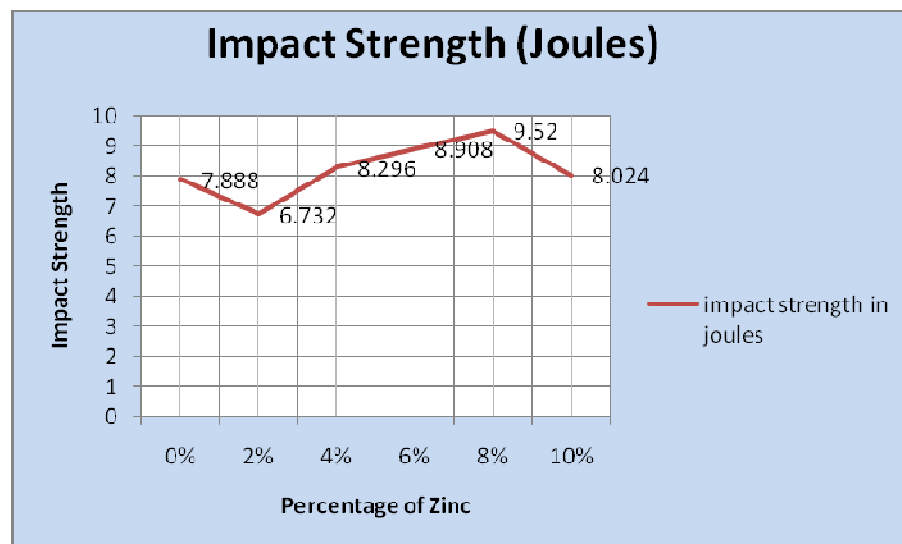


Fig.2: Relationship between the percentage of Zinc in Al6063-SiC-Zn and the Impact Strength of the composite.

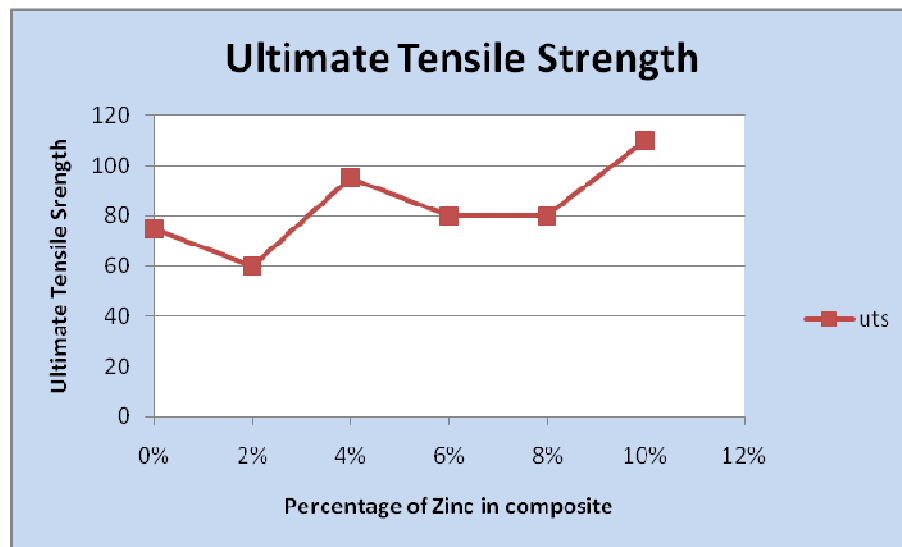


Fig.3: Relationship between the percentage of Zinc in Al6063-SiC-Zn and the Tensile Strength of the composite.


3.4 Metallographic Examination

Figure 4 shows the micrograph of Al6063-SiC composite containing no zinc; the microstructural studies revealed a fairly uniform distribution of SiC particles and slight macro-segregation of particles in some places. Figure 5 shows the micrograph of Al6063-SiC composite containing 2% Zinc. A close look at the microstructure revealed the presence of agglomerated particles of SiC in the composite. These clusters of SiC are likely to be responsible for the increased hardness in the composite containing 2% Zinc. The impact strength was lowest at this percentage and the UTS was lowest at this point also due to the agglomeration of the SiC particles.

Figure 6 shows the micrograph of Al6063-SiC composite containing 4% Zinc. The microstructure revealed the presence of rather thick grain boundary lines. The agglomeration of SiC is not as pronounced as the samples containing 2% Zinc. Generally, the sample showed good mixability of the matrix and the fibres added. Perhaps, the proper incorporation of zinc at this percentage is accountable for the reduced hardness as zinc is a soft metal. Figure 7 shows the micrograph of Al6063-SiC composite containing 6% zinc. Clearly observed from the micrograph is the good spread of zinc and SiC along the matrix. A This

205 implied that increasing the percentage of zinc reduces hardness while increasing impact
206 strength. The UTS was also found to increase tremendously.


207 Figure 8 shows the micrograph of Al6063-SiC composite containing 8% Zinc. A very good
208 incorporation of the reinforcement particles into the matrix was observed. Only a small
209 portion showed a ring of agglomeration. The Hardness further reduced at this percentage
210 while impact strength reached a maximum value at this point. Figure 9 presents the
211 micrograph of Al6063-SiC composite containing 10% Zinc. Formation of thick grain lines
212 and a thick agglomeration of the reinforcement particles were observed. At this percentage,
213 the mechanical properties took a different turn. The hardness began to increase while the
214 impact strength reduced at this percentage. However, the ultimate tensile strength kept
215 increasing and had a maximum value at this point. This observed reversal of trends could be
216 due to the oversaturation of the composite at this percentage with reinforcement particles as
217 strong agglomerations was formed rather than being dispersed evenly.

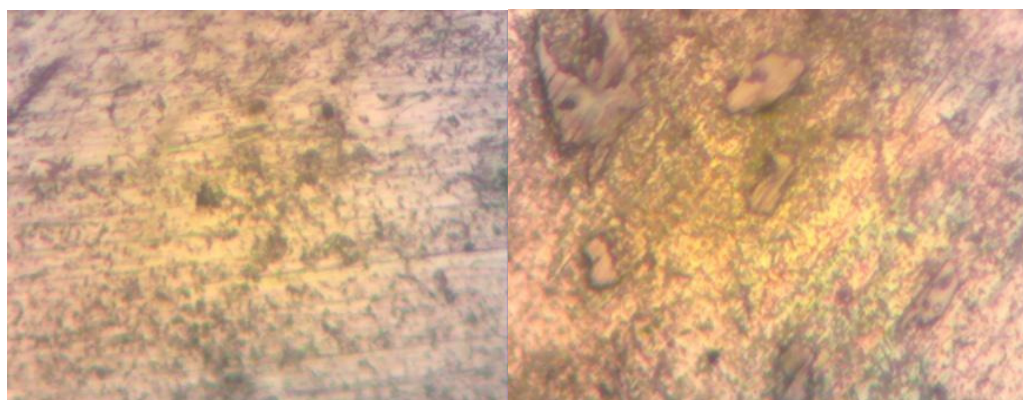

218

219 ***Fig.4: Al6063-SiC (no Zinc)***

Fig.5: Al6063-SiC (2% Zinc)

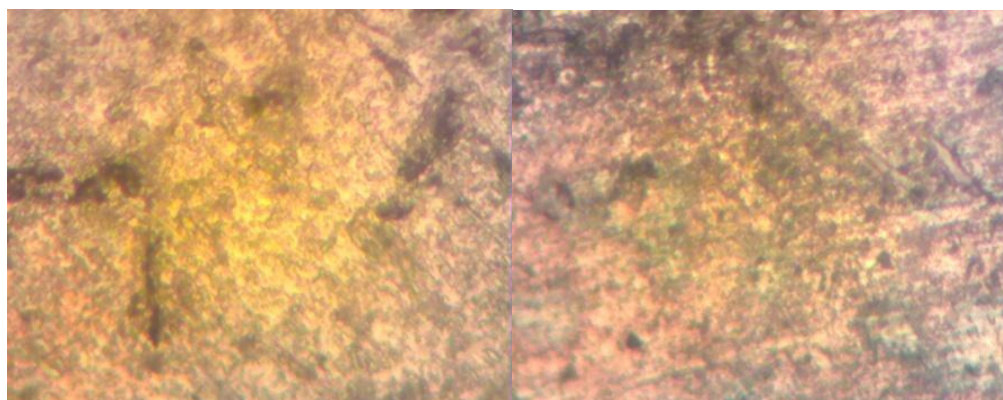

220

Fig. 6: Al6063-SiC (4% Zinc)

Fig. 7: Al6063-SiC (6% Zinc)

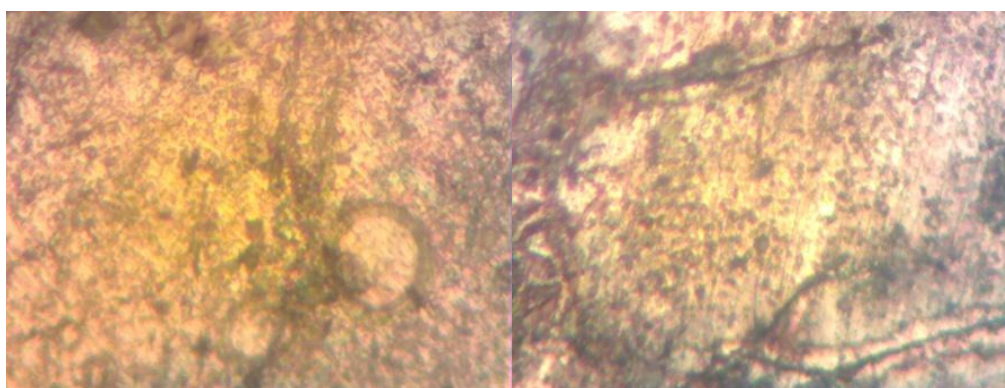


Fig. 8: Al6063-SiC (8% Zinc)

Fig. 9: Al6063-SiC (10% Zinc)

3.5 Corrosion Test

Fig.10. shows the results of the corrosion test both in an acidic medium. In the acidic medium for all samples containing increasing percentages of zinc, the Corrosion Penetration rate (CPR) initially increased and peaked at a point before gradually reducing. The corrosion penetration rate was highest in the sample containing 2% Zinc with a CPR of 0.005 mm/yr, while the sample with the least CPR was the sample containing 10% Zinc with a CPR of 0.0019 mm/yr. The results indicated that Zinc does reduce the rate of corrosion in Al6063-SiC composite. Pitting was the major form of corrosion in all samples immersed in the acidic solution.

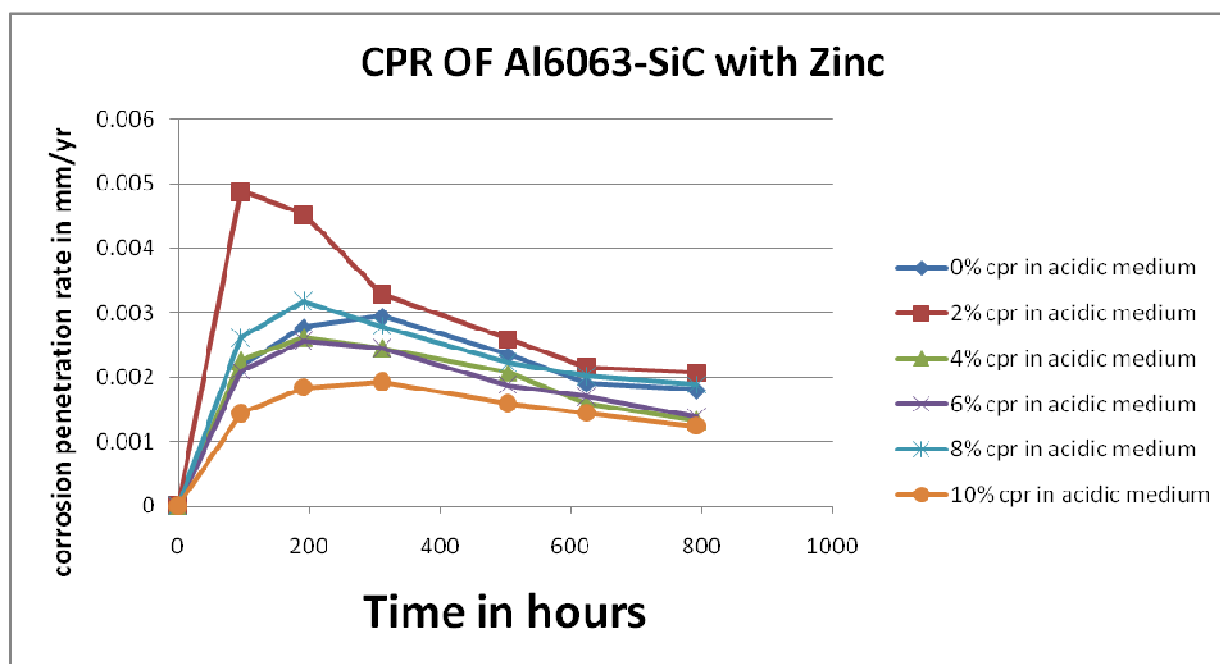


Fig.10: Corrosion Penetration Rate of Al6063-SiC composite with Zinc in an acidic medium



Fig.11. Pitting corrosion of sample in acidic medium

However, the samples in the salt water medium experienced a negative CPR. This was because rather than lose weight, all samples gained considerable weight during the period of the test. The weight gain was most pronounced in the sample containing no Zinc. Weight gain during corrosion test could be due to the formation of a thin film of salt on the samples.

These results again indicate that generally, the addition of Zinc in Al6063-SiC composite does not cause harm due to corrosion in a saline solution.

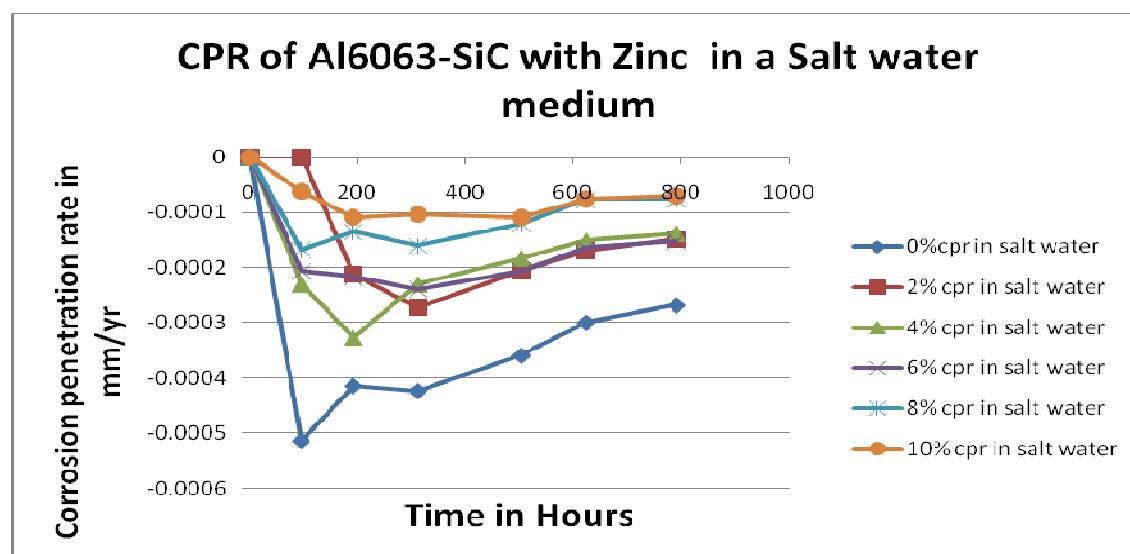


Fig.12: Corrosion Penetration Rate of Al6063-SiC composite with Zinc in an acidic medium

4.0 Conclusions

In this investigative study, the following conclusions can be drawn:

- When Zinc is added to Al6063-SiC composite, the hardness of the composite reduces from 2%-8% with increasing percentage of zinc but increases from 8%.
- The Impact Strength of Al6063-SiC composite is improved when zinc is added and it increases with increasing percentage of Zinc.
- The tensile strength of Al6063-SiC composite increases as the percentage of zinc added to it increases.
- Corrosion tests showed that increasing the percentage of zinc in Al6063-SiC composite improved the corrosion resistance in an acidic medium while in the Salt water medium there was no mass loss due to corrosion.

264 References

- 265 1. Abass, M.K., Hassan,K.S. and Alwan,A.S.2015.Study of corrosion resistance of aluminium
266 alloy 6061/SiC composites in 3.5% NaCl solution. International of Journal of Materials,
267 Mechanics and Manufacturing 3(1):31-35.
- 268 2. Alaname, K.K. 2011. Corrosion behaviour of heat-treated Al6063/SiCp composites
269 immersed in 5wt% NaCl solution. Leonardo Journal of Science 18:55-64.
- 270 3. Alaneme, K.K. and Fatunwase, B.A., Omotoyinbo, J.A., Borode,J.O. and Bodunrin,
271 M.O.2015. Corrosion and wear behaviour of stir cast aluminium based hybrid composites
272 reinforced with silicon carbide and corn cob ash. African Corrosion Journal 1(2):1-8.
- 273 4. Alaneme, K.K., Eze , H.I and Bodunrin, M.O.2015. Corrosion behaviour of groundnut shell
274 and silicon carbide hybrid reinforced Al-Mg-Si alloy matrix composites in 3.5% NaCl and
275 0.3 M H₂SO₄ solutions. Leonardo Electronic Journal of Practices and Technologies 26:129-
276 146.
- 277 5. Aravindan M.K. , Balamurugan K. and Murali G. 2014. Effect of reinforcement of Al6063
278 with SiC on mechanical behaviour and microstructure of metal matrix composites. Carbon-
279 Science and Technology 6(2):388-394.
- 280 6. Aravindan, M.K. and Balamurugan, K. 2016. Tribological and corrosion behaviour of
281 Al6063/SiC metal matrix composites. International Journal of Advanced Engineering
282 Technology III(II):1-6.
- 283 7. Aribio, S., Omotoyinbo, J.A. and Folorunso, D.O. 2011. High temperature Mechanical
284 Properties of Silicon Carbide Particulate Reinforced Cast Aluminium Alloy Composite.
285 Leonardo Electronic Journal of Practices and Technology. 18: 9-16.
- 286 8. Ashok, D., Mamatha, G.P., Venkatesha, T.V., Pruthviraj, R.D. and Krupakara, P.V. 2015.
287 Corrosion characterisation of aluminium-7075/silicon carbide metal matrix composites.
288 International Journal of Advanced Research in Chemical Science 2(1):24-29.
- 289 9. Avdesh, A.2011.Corrosion behaviour of aluminium based metal matrix composites
290 reinforced with SiC and Zircon Sand. A thesis submitted in partial fulfilment of the
291 requirement for the award of degree of Master of Engineering in Production and Industrial,
292 Department of Mechanical Engineering, Tharpar University, India 1:102.
- 293 10. Cai, S., Lei,T., Li, N. and Feing, F. 2012. Effect of Zn on microstructure, mechanical
294 properties and corrosion behaviour of Mg-Zn alloys. Materials Science and Engineering C
295 38(8):2570-2577.

- 296 11. Daramola, O.O., Adediran, A.A. and Fadumiye, A.T.2015. Evaluation of the mechanical
297 property and corrosion behaviour of coconut shell ash reinforced aluminium (6063) alloy
298 composites. Leonardo Electronic Journal of Practices and Technologies 27:107-119.
- 299 12. Geng, L., Song,Y. and Zhang, Y.2012. Effect of zinc content on corrosion behaviour of
300 biological ternary alloy Mg-Zn-Ca in Hank's simulated body fluid. School of Materials and
301 Metallurgy. Inner Mongolia University of Science and Technology, Baotou, China 1
- 302 13. Hindi, J.,Kini, U.A., Sharma, S.S., Gurumurthy, B.M. and Shankar, M.C.G.2015.
303 Mechanical characterization of stir cast Al6063 matrix SiC reinforced metal matrix
304 composites, 5th International Conference on Automotive, Mechanical and Materials
305 Engineering , August 16-17.
- 306 14. Jamaludin S.B., Yusuff, Z. And Ahmed, K.R.2008. Comparative study of corrosion
307 behaviour of AA2014/15Vol%Al₂O₃p and AA2009/20Vol%Al₂O₃p. Portugaliae
308 Electrochemica Acta 26:291-301.
- 309 15. Kumar, S.M.S., Rao,K.P. and Girish, D.P.2012.Corrosion rate and tensile strength of
310 aluminium/SiC metal matrix composites in seawater. International Journal of Advanced
311 Engineering Research and Studies 1:313-315.
- 312 16. Nunes, P.C.R. and Ramanathan, L.V. 1995. Corrosion behaviour of alumina-aluminum and
313 silicon carbide-aluminium metal matrix composites. Corrosion: The Journal of Science and
314 Engineering 51(8):1
- 315 17. Pavani, M.A. and Venkaiah, M.2015. Preparation and mechanical behaviour of Al6063-SiC
316 MMC by using stir casting technique. International Journal of Innovative Science,
317 Engineering and Technology 2 (8): 375-386.
- 318 18. Pinto,G.M.,Nayak,J. and Shetty, A.N.2009. Corrosion behaviour of 6061 Al-
319 15%Vol.Pct.SiC composite and its base alloy in a mixture of 1:1 hydrochloric and sulphuric
320 acid medium. International Journal of Electrochemical Science 4:1452-1468.
- 321 19. Sandeep, K. and Ashutosh, D.2016. Mechanical properties of aluminium 6063 alloy based
322 graphite particle reinforced metal matrix composite material. Journal of Emerging
323 Technologies and Innovative Research 3 (10):152-160.
- 324 20. Singh,I.B., Singh,M.,Das,S. and Gupta,A.K.2012. Comparative corrosion studies of LM13
325 alloy, LM13-10%SiC_p composite and cast iron in NaCl solution. Indian Journal of
326 Chemical Technology 19:385-391.

- 327 21. Yadav, M.K., Sanni, B. and Yadav, A.2015. Experimental analysis of mechanical
328 properties of Al6063 and SiC composite. International Journal of Mechanical and Industrial
329 Technology 3(1):221-227.
- 330 22. Yin, D., Zhang, E. and Zeng, S. 2008. Effect of Zn on the mechanical property and
331 corrosion property of extruded Mg-Zn-Mn alloy. Transaction of Nonferrous Metals Society
332 of China 18: 763-768.