

# Fuel and Physiochemical properties of Cashew (Anarcadium 1 Occidentale) Nut Oil, its Biodiesel and Blends with Diesel.

## ABSTRACT

The aim of this study is to measure the fuel and physiochemical properties of cashew nut oil, its biodiesel and blends with diesel fuel. The oil was extracted by soxhlet extraction method and transesterified with methanol using sodium hydroxide as catalyst. The resulting biodiesel was washed, dried and blended 20% (B20) and 10% (B10) with diesel. They were characterized following the ASTM and EN protocols and the fatty acid profile was determined by chromatography analyzer. The result obtained shows that the properties of the biodiesel are close to those of diesel and can thus be used as alternative fuel for diesel engines.

E.I.Bello<sup>1\*</sup>, F. Otu<sup>1</sup>, T.J.Owoyemi<sup>2</sup>

<sup>1</sup>Department of Mechanical Engineering. The Federal University of Technology, Akure. Nigeria.

<sup>2</sup>Department of Mechanical Engineering. Federal University of Agriculture, Abeokuta. Nigeria.

*Keywords: cashew nut oil, biodiesel, blend, physiochemical properties.*

## INTRODUCTION

Cashew nut is one of the possible feed stocks that can be commercially exploited in Nigeria as it has been ascertained by the Food and Agricultural Organisation of United Nations – Economic and Social Department (FAO, 2008), that Nigeria is the second largest cashew nut (with shell) producers in the world, producing 660 000 tonnes per year. It is extensively cultivation in south America, India and Africa, helped by the fact that cashew tree will tolerate a wide range of conditions including drought and poor soil. It cannot however, withstand cold frost but would quickly recover after a bush fire. Cashew nut yields two “oils”, one of them obtained, between the seed coat (or, pericarp) and the nuts called the Cashew Nut Shell Liquid (CNSL). CNSL is not a triglyceride hence cannot be converted to biodiesel but contains a high proportion of phenolic compound and can be polymerized in a variety of ways which makes it a versatile industrial raw material with diverse uses in friction linings, paints and varnishes, laminating and epoxy resins, foundry chemicals and as an intermediary of chemicals. It is however, toxic and corrosive to the skin.

The second product cashew nut oil (CNO) obtained from the nut contains triglyceride and therefore a potentials and abundant source of feedstock for the production of the biodiesel. It is also used for manufacturing wood preservatives, coatings and friction materials (Alexander, 2008).

cashew tree is high yielding in Nigeria and a five years old cashew tree can produce up to 500 nuts per annum. However, the full benefit of the tree is not exploited as on a typical plantation, the fruits are allowed to fall and decay to release the nut that are then picked up. Sometimes they are eaten fruits and nuts raw by cows and other animals. Some studies have been done on the uses of cashew nut oil (Achal, 2002, Akinhanmi et al., 2008, Akinwale,2000, Aremu et al., 2007, Frankel, 1991,Rosengarten, 1984,Gibbon and Pain, 1981,Winterhatter et al., 1991) but not much work has been done on the measurement of the physiochemical properties of Nigeria's cashew nut oil hence the aim of this study is to characterize the fuel and physiochemical properties of cashew nut oil, its biodiesel and 10% (B10) and 20% (B20) blends with diesel fuel. Biodiesel has been defined as the mono alkyl ester of vegetable oils and animal fats [NBB, 1997]. It is biodegradable, nontoxic, environment friendly and has agricultural origin hence renewable (Ma and Hanna,

1999, Canakci and Van Gerpen, 1999, Darado et al., 2002, Van Gerpen et al., 2004, Canakci and Van Gerpen, 2001).

The fuel properties of biodiesels are to a large extent dependent on feed stocks, which vary not only with the species but also with place of production (Ramadhas et al., 2005). The fuel standards for biodiesel, which are evolved from fossil fuel standards, ensures quality assurance by limiting the amount of impurities in the fuel such as triglycerides, monoglycerides, diglycerides, water, free fatty acid, soap and residual alcohol. These impurities need to be limited in biodiesel because their presence can lead to fuel deterioration during storage which can cause significant operational problems. Presently Nigeria has a biodiesel policy and standards are being developed to ensure uniformity of properties.

## 2.0 MATERIALS AND METHODS

### 2.1 Oil extraction

Cashew nut was planted in the backyard garden in 2010 and it yielded fruits after 15 months. 2 kg of the nuts was harvested and dried in the sun for five days at 35°C to reduce moisture content to about 7% (Ebewere et al., 2010) and decorticated manually to remove the kernel from the shell. The nuts which measured 5 mm diameter on the average, were milled to reduce diameter to about 1.16 mm and expose more area for higher oil extraction (Goodrum and Kilgo, 1986, Sayyar et al., 2008). Analytical grade methanol, n-hexane and sodium hydroxide were procured from Finlab laboratory in Akure Nigeria. The oil was extracted in a soxhlet extractor with the n-hexane as the solvent. The oil was leached for 8 hours at 60°C and the hexane in the mixture was removed by using a rotary vacuum evaporator operating at 75°C. The oil obtained was weighed and the percentage oil yield was calculated by equation 1.

$$\% \text{ Oil yield} = \frac{\text{Weight of oil extracted}}{\text{Total weight of cashew nuts used}} \times 100 \quad 1.$$

### 2.2 Characterization of the oil.

The properties of the oil were first measured to determine if pretreatment was necessary or not before alkaline transesterification. It was found that the free fatty acid value (FFA) of the oil was 23.68 mg KOH/g which is high for direct alkaline transesterification as it can react with the catalyst to form soap which can inhibit methyl ester yield (Van Gerpen et al., 2004). The water content was 10% which is a little bit too high for uninhibited transesterification hence the oil was heated to 110°C and held constant for 30 minutes to allow some of the water to evaporate.

### 2.3 Transesterification procedure

Transesterification was carried out using a laboratory scale biodiesel processor in chemistry laboratory of the Federal University of Technology, Akure, Nigeria. Methanol was used as the reagent because it is a low cost and short-chain alcohol that reacts fast. The oil was first pretreated using sulfuric acid as catalyst to convert some of the fatty acids to ester before alkaline transesterification using anhydrous methanol at a molar ratio of 6 to 1 and 3g/litre of sodium hydroxide as catalyst. The processor was stirred at 600 rpm. at a temperature of 60°C for 2 hours, after which the mixture was poured into a decanter and allowed to settle for 12 hours so that the reaction can be driven to completion and for the mixture to separate into two layers of biodiesel and glycerol which was at the bottom. The glycerol was drained off by gravity and the excess methanol in the biodiesel was removed in a flash evaporator. To remove any impurity, the biodiesel was washed in distilled and deionized water of volume

ratio 3 to 1 three times. Finally, the washed biodiesel was dried by passing it through anhydrous sodium sulphate (Na<sub>2</sub>SO<sub>4</sub>) (Schinas et al., 2009). The biodiesel produced and the glycerol was weighed and percentage yield calculated using equation 2.

$$\text{Biodiesel yield \%} = \frac{\text{Weight of biodiesel}}{\text{Weight of biodiesel} + \text{weight of glycerol}} \quad 2$$

## 2.4 Fatty acid profile

The fatty acid compositions of the cashew seed oil, the methyl ester and blends with diesel (B10 and B20) and the standard sample of free fatty acid were determined by chromatography analyzer following the modified AOAC 965.49 and AOAC 996.06 official methods. The fatty acid methyl esters were separated using HP 6890 Gas Chromatography analyzer powered by HP ChemStation Rev A 09.11 [1206] software and equipped with a Flame Ionization Detector (FID) and HP INNOWax column (30 m x 0.25 mm x 0.20 µm film thickness). The carrier gas was nitrogen and the oven initial temperature then was at 60 °C. The first ramping was at 10 °C/min for 20 min and maintained for 4 minutes. The second ramping was at 15 °C/min for 4 minutes and maintained for 10 minutes. The detector temperature was 320 °C while hydrogen and compressed air pressures were 22 and 35 psi respectively. The proportion of the various fatty acids is shown in Table 1.

## 2.5 Determination of fuel and physiochemical properties

The fuel and physiochemical properties of the cashew seed oil, the biodiesel and blends were determined following ASTM, EN and AOCs methods and undertaken in McDonald laboratory in Warri, Delta state and the chemistry laboratory of the Federal University of Technology, Akure, Nigeria. The biodiesel and diesel were blended using a rotary blender in the ratio 10% and 20% (vol/vol).

**2.6 Density and relative density** The density and relative density were measured using hydrometer to IP-160/ASTM D-1298. The measurements were made three times and then averaged.

**2.7 Cold flow properties** In measuring the Pour point, a 45 ml sample initially at 45°C was cooled in Herzog HCP852 at specified rate and examined at interval of 3°C to check if the sample is still flowing.

The cloud point was determined by a cloud point meter which comprises of a waveguide sensor of a total-reflection type, the wave guide sensor including a wave guide having an incidence channel, an emergency channel and a detection surface all formed on a substrate, the incidence and emergency channels intersecting along the detection surface, an incidence optical fiber connected to the entrance of the incidence channel, and an emergency optical fiber connected to the exit of the emergence channel; and a cooling/heating means in contact with the waveguide sensor for cooling/heating the waveguide sensor within a desired temperature range.

The cold filter plug apparatus model MC840 with 0.7 micron filter was used to test 60 ml of each sample. It involves chilling the biodiesel to a predetermined point and then reheating to room temperature. The chilling and reheating process resulted into the formation of mushy crystal like material called sterols which does not blend with the biodiesel and can clog the fuel filter.

**2.8 Kinematic and dynamic viscosities:** The kinematic viscosity was determined with a Herzog GmbH MP-480 that involves measuring the time for a fixed volume of the fuel to flow under gravity through a capillary at temperature of 40°C.

Kinematic viscosity = Calibration constant (mm<sup>2</sup>/s) x mean time of flow (s). The Brookfield viscometer model LV-DV11 was used to measure the dynamic viscosity at a temperature of 40°C.

**2.9 Flash point** Flash point measurements were done according to method ASTM D6751 using Kehler Model K-16270 (Pensky-Martens Closed Flash Tester).

**2.10 Higher and lower heating values** The lower heating value was obtained using the oxygen bomb calorimeter (Parr Instrument Company, US.) following the ASTM D240 method.

**2.11 Calculated cetane index** The cetane number of the biodiesel was calculated using equation 3 (Willard, 1976).

$$CI = -420.34 + 0.016G^2 + 0.192G(\log T_{50}) + 65.01(\log T_{50})^2 - 0.0001809T_{50}^2 \quad 3$$

where G is the API (American Petroleum Institute) specific gravity and  $T_{50}$  is the distillation temperature as 50 vol.% fuel sample distilled and condensed in a unit of °F.

**2.12 Iodine and peroxide values** The iodine and peroxide values were analyzed, based on the methods of the American Oil Chemists' Society (AOCS cd8, 1980) by titrating with 0.01 N sodium thiosulfate for the mixture of tested fuel and chemical reagents until they were light blue and light yellow, respectively. The iodine value and peroxide value were then calculated by equations (2) and (3).

$$\text{Iodine value} = \frac{(B-T) \times C \times 0.001269}{Y} \quad 4.$$

$$\text{Peroxide value} = \frac{(T-B) \times C \times 1000}{Y} \quad 5.$$

where B and T are denoted as the amounts (in mL) of sodium thiosulfate titrated for the blank sample and tested sample, respectively. C is the molar concentration (in mol/L) of sodium thiosulfate and Y is the weight (in g) of the tested sample.

**2.13 Acidic number** The acid number, which is the amount of KOH required to neutralize 1 g of fat and expressed as mg KOH/g, was determined by titrating with 0.01 N potassium hydroxide for the mixture of tested fuel and chemical reagents until the appearance of the color pink.

**2.14 Oxidative stability** A glass ware apparatus for ASTM D 2274 was used for the oxidation stability test. The fuel was made to degrade by heating and oxygenating the sample in a shorter period of induction time. Oxygen was bubbled for 16 hours while the fuel was held at 95 °C. Thereafter, the fuel sample was filtered to measure the amount of any insoluble that was formed. Finally, the amount of time that the fuel could be stored before deterioration by forming acids was then estimated.

## 2.15 Soap content

For soap content measurement of the oil, the AOCS method cc 17-79, (soap in oil) was used. 5 g of each sample was titrated with 0.1N solution of HCL acid to the phenolphthalein end point. 1 ml of bromophenol blue indicator was added and the titration was continued until the bromophenol changed from blue to yellow.

## 2.16 Saponification value

This was determined using equation 6.

$$\text{Saponification value} = \frac{(B - T) \times 28.5}{\text{Weight of sample}}$$

### 2.17 Moisture content

The moisture content was measured by Karl-Fisher Method (ASTM D 6304) 831 KF Coulometer (Metrohm Company, Switzerland) using 5 ml of the samples.

**2.18 Water and sediment** Water and sediment content were obtained by centrifuge model HNS II by Thermo Electron Corp, US. 100 ml of each sample was poured into a centrifuge tube and spun at 800 rev/min for 10 minutes. After centrifuging, the volume of water and sediment which settled into the tip of the centrifuge tube was read to the nearest 0.005 ml and recorded as the volumetric percentage water and sediment. by centrifuge.

**2.19 Carbon residue** Carbon residue was determined by heating a sample to 500 °C in nitrogen filled chamber at controlled rate to ensure that the sample cokes and does not combust. The formed volatile compounds were flushed from the chamber by nitrogen, and the mass of the remaining coke determined. The test is to simulate the formation of carbon deposits in the engine by the fuel.

**2.20 Sulfated ash** Isotemp muffle furnace was used for ash analysis. The residue was allowed to cool down and thereafter treated with sulfuric acid and heated to 750 °C until oxidation of carbon was complete. The ash was then cooled, retreated with sulfuric acid and heated to 750 °C to constant weight. To obtain the sulfated ash content of the samples, the final weight was divided by the initial weight and then multiplied by 100 to express as percentage.

**2.21 Glycerine content** The wet Chemical AOCS method for determining glycerol, methanol, AOCS Official method Ca 14-56 entitled "Total, free and combined glycerol Iodometric-periodic Acid method as well as methanol Content was used. It is similar to the method prescribed in the ASTM standard but easier to perform. It was also used for the determination of monoglycerides, diglycerides and triglycerides

**2.22 Copper Strip corrosion test** Copper strip corrosion test was conducted according to ASTM D130 protocol. A polish copper strip was immersed in 50 ml sample of the oil and methyl ester for 3 hours at 50°C. At the expiration of the duration each strip was washed in a standard solvent and the result were compared with standard description of tarnished and corrosion.

**2.23 Distillation temperatures** During the vacuum distillation test, the system pressure was set at between 1 kpa and 83 kPa. and were made to correspond to 5 to 95 vol % in a step of 5 vol % of the liquid fuel distilled and condensed.

**2.24 Metal analysis** For metal analysis 50 ml of samples were prepared by diluting 1:10 with kerosine. The dilution was to eliminate possible viscosity effect that may affect accuracy. The Teledyne fuelpro biodiesel metal analyzer was calibrated with standards prepared by diluting plasma pure biodiesel stock standards. The standard concentrations were 0.00, 10.00, 20.00, 30.00, 40.00 ppm of Na, K, Ca, Mg, P and S.

**2.24 Colour** The colours of the oil, biodiesel and blends were observed visually.

## 3.0 RESULTS AND DISCUSSION

The Oil yield was 32% and biodiesel yield 87%.

Table 1 shows that the fatty acid profile of CNO is 63% unsaturated consisting mainly of 20.97% linolenic acid with triple bond, 34.48% oleic acid with single bond and 28.87% palmitic saturated fatty acid. Many properties vary with chain length, number of bonds and degree of unsaturation (Laza and Bereczky, 2010). It was reported that methyl esters of saturated acids have a higher cloud point, cetane number and better stability (Knothe, 2005). The results obtained for the fuel and physiochemical properties are shown in Tables 2 to 5. There are significant differences in the fatty acid profile of B100, B20 and B10 compared with CNO because transesterification chemically breaks down the molecules of the vegetable oil during which the glycerol from the triglycerides are removed and replaced with radicals from the alcohol used which changes the structure and hence the properties of transesterified oils (Bello, et al., 2011).

**Table 1. Fatty acid profile of cashew nut oil and its biodiesel.**

| Fatty Acid           | Form  | Oil   | B100  |
|----------------------|-------|-------|-------|
| Capric               | C10:0 | 1.37  | 2.23  |
| Lauric               | C12:0 | 1.83  | 2.98  |
| Myristic             | C14:0 | 0.59  | 0.96  |
| Palmitic             | C16:0 | 28.87 | 23.13 |
| Palmitoleic          | C16:1 | 3.16  | 5.16  |
| Stearic              | C18:0 | 4.06  | 5.57  |
| Oleic                | C18:1 | 34.48 | 31.65 |
| Linoleic             | C18:2 | 4.67  | 7.62  |
| Linolenic            | C18:3 | 20.97 | 20.71 |
| Total Saturation %   |       | 36.71 | 34.87 |
| Total unsaturation % |       | 63.28 | 65.13 |

### 3.1 Density and relative density

The density of biodiesel is generally higher than those of fossil diesel fuel and the value depend on their fatty acid composition as well as on its purity. CNO density of 902 kg/m<sup>3</sup> reduced to 874, 856 and 854 for the B100, B20 and B10 respectively. The relative density of CNAME is within the limits for biodiesel and higher than diesel except for B20.

### 3.2 Cloud and pour points

Cold temperature behaviour of biodiesel is an important quality criterion, as frozen fuel may cause blockage of the fuel lines and filters and starve the engine of fuel. The two most important criteria are the cloud and pour points. The cloud, pour and cold filter plugging points are all a little bit above zero which limits their application in cold regions.

### 3.3 Flash point

The flash point of pure biodiesels is usually higher than the ASTM limits, but fall rapidly with increasing amount of methanol. CNO has a flash point of 167 °C, the value for CNAME is 136°C while the values for B10 and B20 are 82 °C and 89 °C respectively and which although are below the minimum for biodiesel, are higher than that for diesel fuel. High flash point can prevent auto ignition and reduced fire hazards at high temperatures during transportation and storage periods. It is hence a measure of flammability of fuels and an important safety criterion.

### 3.4 Viscosity

Kinematic velocity is the dynamic viscosity/relative density. The dynamic and kinematic viscosities of the CNO are 49.62 cts and 54.92 mm<sup>2</sup>/s respectively. Those of CNOME and the blends are within the limits for biodiesel. Viscosity is an important property of biodiesel since it affects the operation of fuel injection equipment, particularly at low temperatures when the increase in viscosity affects the fluidity of the fuel or leakage at high temperature when too thin. Dynamic viscosity is of interest in relation to the settling rates of contaminants, and kinematic velocity in respect of pumping and atomization.

### 3.5 Higher and lower heating values

Heating value is the enthalpy released after the complete combustion reaction of fuel at a constant pressure or volume. Fuels having higher the heating value, will consumption lower fuel to obtain the same engine power output. Monyem and Van Gerpen (2001) found that a biodiesel had a heating value lower than that of ASTM No. 2D diesel by about 12.7–14.7%. The higher and lower heating values for CNO are 40 MJ/kg and 37.30 MJ/kg, 44.00 MJ/kg and 37.20 MJ/kg for CNOME respectively and are slightly less than that of diesel fuel which is consistent with the trend for biodiesel. The heating values increases after transesterification because the glycerol removed from the oil has lower heating values and it also increases with the amount of diesel in the blend because diesel has higher heating values.

### 3.6 Calculated cetane Index

Biodiesel has a higher cetane index than diesel fuel because of its oxygen content (Knothe, 2005) and also because the fatty acids present in the fuel have very high cetane index. Cetane index increases with increasing length of both fatty acid chain and ester groups, while it is inversely related to the number of double bonds. The calculated cetane index of the CNO of 49.28 increased to 60.83 for the CNOME 47.75 and 46.22 for B20 and B10 respectively. That of CNOME is above the minimum limit for biodiesel but reduces with blending because diesel has lower cetane number.

### 3.7 Water content and sediment

CNO contains 10% water by volume. This falls drastically after transesterification. The moisture content was 3420 and reduced to 221 after transesterification. Free water promotes microbial growth in the oil leading to sludge and slime formation, which can cause blockage of fuel filters and fuel lines. Moreover, high water contents are also associated with hydrolysis reactions, partly converting biodiesel to free fatty acids.

### 3.8 Cold soak filtration

This is a measure of the time in seconds it takes for cold soaked biodiesel to pass through two 0.8 micron filters. It an indicator of the amount of particulate matter collected on the filter. The test is to prevent the precipitation of solid materials in inferior biodiesel during cold weather. The cold soak filtration is 310 for CNO and falls to 230, 77 and 95 for the CNOME and the B10 and B20 blends respectively.

### 3.9 Iodine values

Iodine number is a measure of the total unsaturation within a mixture of fatty acids, and is expressed in grams of iodine which react with 100 grams of biodiesel. Unsaturation can lead to deposit formation and storage stability problems with biodiesel. Fuels with higher iodine number tend to polymerize and form deposits on injector nozzles and piston when heated. The iodine values for the CNO, CNOME, B10 and B20 are below the maximum for biodiesel. The value for CNOME is 85.28 and 82.75 for CNOME The iodine values are all

below the maximum for biodiesel and reduces further with blending. Iodine value is an indication of the drying quality of the oil.

### **3.10 Peroxide value**

Peroxide value is generally used to determine the extent of fuel oxidation. It is an indicator of oil auto ignition and high value is an indication of high degree of rancidity. The peroxide value of an oil increases with its oxidization level. Cherng-Yuan and Rong-Ji, (2009) shows that marine fish-oil biodiesel had a peroxide value much lower than that of the commercial biodiesel, primarily due to its larger content of saturated fatty acids and thus higher oxidation stability, A peroxide value of 21.70 for the biodiesel is high compared to common vegetable oils.

### **3.11 Oxidation stability**

Biodiesel ages because of their nature origin and aging properties vary with method of production, raw materials used, exposure to sunlight high temperature and oxygen. This can lead to the formation of insoluble sediments and gums, which are associated with fuel filter blocking and deposits within the injection system and the combustion chamber. It leads to increased viscosity and acid value. The oxidative stability of CNO at 110°C was 19 hr, 9 hours for CNAME, 27 and 18 for B10 and B20 respectively. It reduces after transesterification but increases with blending and in all case higher than diesel.

### **3.12 Acid number and free fatty acid**

This is the quantity of base required to titrate a sample to a specified end point. It is a measure of free fatty acid in biodiesel. Excessive free fatty acid in the fuel can be corrosive and may be a symptom of water in the fuel or poor production or subjected to oxidative degradation. Excessive free fatty acid in the fuel can inhibit the transesterification process and lead to soap formation. The free fatty acid and acid values of the oil are 2.29 mgKOH/g and 4.56 mgKOH/g respectively. The acid value reduced after transesterification but increased with increasing amount of diesel on the blends.

### **3.14 Saponification values**

Saponification is the chemical reaction between the CNO and NaOH and resulted in the production of soap and glycerin. Water is also present, but it does not enter into the chemical reaction. High value can inhibit the transesterification process. The Saponification value of the oil is 117.11 for the oil and is within the range for most vegetable oils (Alatise and Akinhanmi, 2009, Mittelbach and Remschmidt, 2004). It would be suitable for the production of soap and shampoo.

### **3.15 Soap content**

Soap in biodiesel is as a result of poor transesterification process and tends to reduce biodiesel yield. It makes the fuel more viscous, reduces flammability and hence must be regulated. The soap content for CNO was zero but increased to 4 for CNAME as a result of transesterification. It reduced further with blending.

### **3.16 Refractive index**

The refractive index was 1.466 and reduced to 1.334 after transesterification but increases to 1.481 after blending. Reflective index value is a measure of purity of the fuel.

### **3.17 Carbon residue**

The carbon residue test gives the remaining part when a sample of biodiesel has been subjected to thermal decomposition and hence an indication of coking tendency of the fuel. The most common cause of excessive carbon residue in biodiesel is the excessive level of

total glycerin soaps and other organic impurities. The carbon residue is 0.07 (mol/mol) CNAME and below the maximum ASTM D4530 limits for biodiesel of 0.05%.

412

### 413 **3.18 sulfated ash**

414 This is a measure of the mineral ash residue when a fuel is burned. It is an important test for  
415 biodiesel because it is an indicator of the quantity of residue metals in the fuel that came  
416 from the catalyst used in the transesterification process. It is limited by ASTM D874 and EN  
417 ISO 3987. The sulfated ashes for B100 are 0.03 % (mol/mol) and lower than the 0.05 ASTM  
418 maximum limits.

419

### 420 **3.19 Total glycerol**

421 Total glycerol is the sum of the concentrations of free glycerol and glycerol bound in the form  
422 of mono-, di- and triglycerides. The concentration depends on the production process and  
423 high value may originate from complete transesterification or inadequate washing. Free  
424 glycerol can separate from the biodiesel when stored and accumulate at the bottom of the  
425 tank, where it can mix with other polar components from sediments in the fuel tank. High  
426 level of glycerol can result into injector coking and affect a wide range of fuel properties,  
427 which can affect operational efficiency and engine durability hence the need for its  
428 regulation. It is limited by ASTM D6584 and EN 14105/14106 (McCormick and Westbrook,  
429 2007) Table 3. Shows all the glyceride contents.

430

### 431 **3.20 Distillation temperature, 90% recovered, maximum**

432 This parameter is related with the boiling point of a liquid fuel and affects the combustion  
433 characteristics of diesel engines and commonly used to determine the cetane number. The  
434 vacuum distillation end point is below the 360°C maximum at 90% distillation of EN  
435 D1160. The distillation temperature increases with the amount of methyl ester in the blend  
436 this result was also noted by (Alptekin and Canakci, 2009). The result is shown in Figure 1.

437

### 438 **3.21 Alkaline and metal components**

439 The origin of alkaline metallic elements in the fuel is from the catalysts used during  
440 transesterification while earth metal ions that emanates from the hard water used for  
441 washing in the fuel. They are deposited on engine components after combustion as  
442 incombustible ash and can react with metallic components of fuel systems and should hence  
443 be limited to recommended values to reduce deposits on engine components, injectors and  
444 catalytic system. All the metals levels are high for the oil but below the limit for biodiesel for  
445 B100. Sulfur however increases with blending since the diesel used contains sulfur. The  
446 result is shown in Table 3.

447

### 448 **3.22 Phosphorous content**

449 Phosphorus in biodiesel originates from phospholipids (animal and vegetable material) and  
450 inorganic salts contained in the feedstock. Phosphorus has adverse effect on long term  
451 activity of exhaust emission catalytic systems and therefore limited by specification. The  
452 value for the oil is less than the maximum of 10 mg/kg specified by EN standard.

453

454 **3.23 Colour** Table 5 shows the colours of the tested fuels. The colours changed with  
455 transesterification but become darker with blending with diesel.

456

457 **Table 2. Properties of cashew nut oil, its biodiesel and blends to ASTM D6751-02 and**  
458 **EN 14214**

| 459 <b>Property</b>                    | <b>CNO</b> | <b>B100</b> | <b>B10</b> | <b>B20</b> | <b>Diesel</b> | <b>ASTM Limits</b> | <b>EN 14214</b> |
|----------------------------------------|------------|-------------|------------|------------|---------------|--------------------|-----------------|
| 460 Density kg/m <sup>3</sup>          | 902        | 874         | 854        | 856        | 850           |                    | 860-900         |
| 461 at 15°C                            |            |             |            |            |               |                    |                 |
| 462 Relative density kg/m <sup>3</sup> | 0.914      | 0.875       | 0.855      | 0.857      | 0.852         |                    |                 |

|     |                           |        |        |        |        |        |           |            |
|-----|---------------------------|--------|--------|--------|--------|--------|-----------|------------|
| 463 | at 15°C                   |        |        |        |        |        |           |            |
| 464 | Cloud point °C            | 20     | 6      | 7      | 9      | -12    |           |            |
| 465 | Pour point °C             | 13     | 1      | 5      | 5      | -20    |           |            |
| 466 | Cold filter plug point °C | 15     | 4      | 6      | 7      | -15    |           |            |
| 467 | Flash point °C            | 167    | 136    | 82     | 89     | 68     | 93        | 120 min    |
| 468 | Dynamic viscosity cts     | 49.62  | 4.21   | 2.46   | 2.67   | 2.23   |           |            |
| 469 | at 40°C                   |        |        |        |        |        |           |            |
| 470 | Kinematic viscosity       | 54.92  | 4.81   | 2.88   | 3.12   | 2.62   | 1.9-6.0   | 3.5-5.0    |
| 471 | mm <sup>2</sup> /s 40°C   |        |        |        |        |        |           |            |
| 472 | Lower heating             | 37.30  | 37.20  | 42.80  | 42.20  | 43.40  |           |            |
| 473 | Value KJ/kg               |        |        |        |        |        |           |            |
| 474 | Higher heating value      | 40     | 40.40  | 45.30  | 44.85  | 45.90  |           |            |
| 475 | KJ/kg                     |        |        |        |        |        |           |            |
| 476 | Calculated cetane         | 49.28  | 60.83  | 46.22  | 47.75  |        | 47 min    | 51 min     |
| 477 | number (ASTM D4737)       |        |        |        |        |        |           |            |
| 478 | Free fatty acid %         | 2.29   | 0.188  | 0.188  | 0.225  |        |           |            |
| 479 | Acid value mgKOH/g        | 4.56   | 0.374  | 0.45   | 0.37   |        | 0.80 max  | 0.05 max   |
| 480 | Iodine value gI2/100g     | 85.28  | 82.74  | 16.24  | 23.65  | 8.63   |           | 120 max    |
| 481 | Peroxide value gI2/100g   | 21.70  | 27.00  | 17.30  | 16.30  | 15.00  |           |            |
| 482 | Oxidation stability       | 19     | 9      | 27     | 18     |        | 3 min     | 6 min      |
| 483 | (hours) 110°C             |        |        |        |        |        |           |            |
| 484 | Saponification value      | 117.11 | 187.94 | 162.69 | 165.50 | 159.89 | 120 max   | 159.89 max |
| 485 | mgKOH/g                   |        |        |        |        |        |           |            |
| 486 | Soap content %            | 0      | 4      | 0.5    | 1.0    |        |           |            |
| 487 | Cold soak filtration °C   | 310    | 230    | 77     | 95     |        |           |            |
| 488 | Water and sediments       | 10.00  | 0.02   | 0.002  | 0.004  |        |           | 500 max    |
| 489 | % (vol/vol)               |        |        |        |        |        |           |            |
| 490 | Moisture content ppm      | 3420.  | 221.0  | 24     | 48     |        |           |            |
| 491 | Refractive index          | 1.47   | 1.34   | 1.48   | 1.48   | 1.48   |           |            |
| 492 | at 15°C                   |        |        |        |        |        |           |            |
| 493 | Sulfated ash              | 0.60   | 0.03   | 0.01   | 0.01   |        | 0.020 max | 0.02 max   |
| 494 | % (mol/mol)               |        |        |        |        |        |           |            |
| 495 | Carbon residue            | 0.17   | 0.07   | 0.03   | 0.02   |        | 0.050 max | 0.30 max   |
| 496 | % (mol/mol)               |        |        |        |        |        |           |            |
| 497 | Copper strip corrosion    | 4      | 2      | 1      | 1      |        | No.3 max  | 1          |
| 498 | test (3h, 50°C)           |        |        |        |        |        |           |            |
| 499 | Distillation temperature  | 355    | 350    | 320    | 322    |        | 360 max   |            |
| 500 | 90% °C                    |        |        |        |        |        |           |            |

501  
502  
503  
504  
505  
506  
507  
508  
509  
510  
511  
512  
513  
514  
515

**Table 3. Glycerine contents**

| Property                     | CNO    | B100  | B10   | B20   | ASTM Limits | EN 14214 |
|------------------------------|--------|-------|-------|-------|-------------|----------|
| Methanol Content % (mol/mol) | 0.003  | 0.096 | 0.011 | 0.021 |             | 0.20 max |
| Free Glycerol % (mol/mol)    | 0.960  | 0.011 | 0.002 | 0.003 | 0.020 max   | 0.02     |
| Monoglycerine % (mol/mol)    | 0.002  | 0.150 | 0.018 | 0.032 |             | 0.80     |
| Diglycerine % (mol/mol)      | 0.001  | 0.009 | 0.002 | 0.003 |             | 0.20     |
| Triglyceride % (mol/mol)     | 98.752 | 0.005 | 0.003 | 0.005 |             | 0.20     |
| Total Bounded glycerol       | 98.755 | 0.164 | 0.023 | 0.040 |             |          |
| Total Glycerol               | 99.715 | 0.175 | 0.025 | 0.043 | 0.240 max   | 0.025    |

|     |                                        |             |          |       |      |       |      |        |          |  |
|-----|----------------------------------------|-------------|----------|-------|------|-------|------|--------|----------|--|
| 516 | <b>Table 4. Metal content (mg/kg).</b> |             |          |       |      |       |      |        |          |  |
| 517 | Metal                                  | Detection   | Spike    | CNSO  | B100 | B20   | B10  | ASTM   | EN       |  |
| 518 |                                        | Limit (ppm) | recovery |       |      |       |      |        |          |  |
| 519 |                                        |             |          |       |      |       |      |        |          |  |
| 520 | Sodium                                 | 0.0193      | 100.9    | 4.50  | 2.50 | 0.03  | 0.02 |        | 5.0 max  |  |
| 521 | Na 589.592r                            | 80          |          |       |      |       |      |        |          |  |
| 522 | Potassium                              | 0.0704      | 101.1    | 2.80  | 1.00 | 0.08  | 0.04 |        | 5.0 max  |  |
| 523 | K766.491r                              | 40          |          |       |      |       |      |        |          |  |
| 524 | Calcium                                | 0.0029      | 101.6    | 3.40  | 0.50 | 0.01  | 0.06 |        | 5.0 max  |  |
| 525 | Ca317.933r                             | 2           |          |       |      |       |      |        |          |  |
| 526 | Magnesium                              | 0.0009      | 99.1     | 28.50 | 0.70 | 0.15  | 0.08 |        | 5.0 max  |  |
| 527 | Mg285.213r                             | 0.20        |          |       |      |       |      |        |          |  |
| 528 | Phosphorous                            | 0.0227      | 99.1     | 40.60 | 5.20 | 7.50  | 3.60 | 10 max | 10.0 max |  |
| 529 | P213.618r                              | 5           |          |       |      |       |      |        |          |  |
| 530 | Sulphur                                | 0.114       | 98.7     | 21.00 | 9.20 | 27.50 | 26.9 | 15/500 | 10.0 max |  |
| 531 | S180.731r                              | 15          |          |       |      |       |      |        |          |  |

532

533

534

535 **Table 5. State of cashew nut oil, methyl ester and blends.**

536

|     |                |                                  |               |
|-----|----------------|----------------------------------|---------------|
| 537 | Fuel           | State at room temperature (25°C) | Colour        |
| 538 | Cashew nut oil | Liquid                           | Dark brown    |
| 539 | B100           | Liquid                           | Golden yellow |
| 540 | B20            | Liquid                           | Dark brown    |
| 541 | B10            | Liquid                           | Dark brown    |
| 542 | Diesel         | Liquid                           | Dark brown    |

543

544

545

546

547

548

549

550

551

552

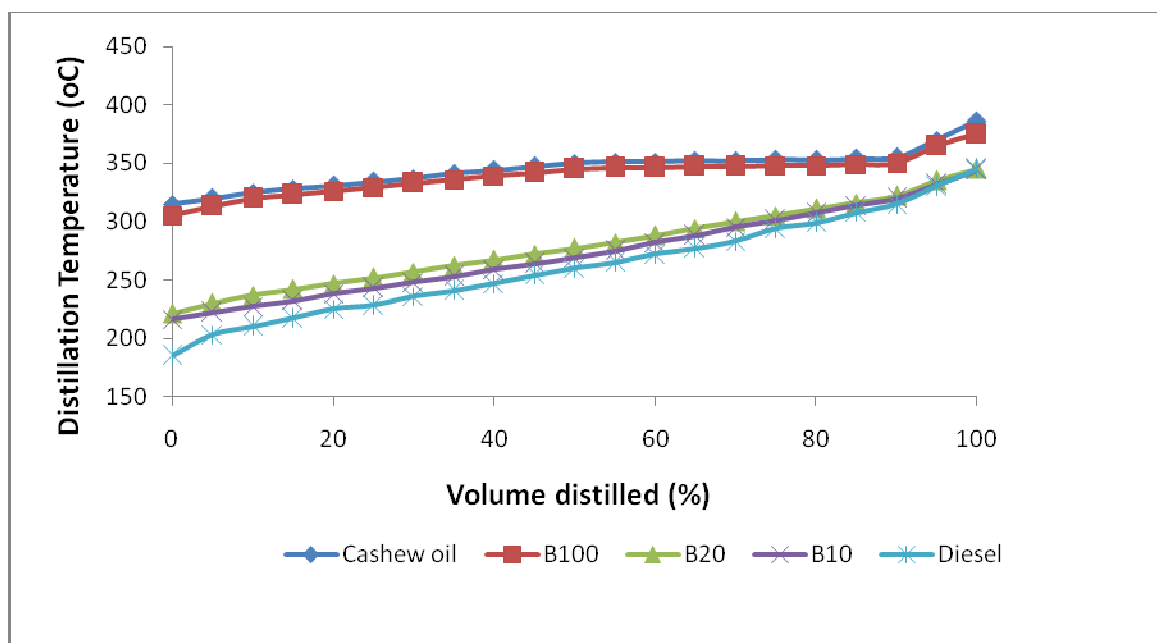


Fig.1. Distillation curves for cashew nut oil, methyl ester and blends.

#### 4.0. CONCLUSIONS AND RECOMMENDATIONS

Cashew nut has oil content of 32% and the biodiesel yield was 87%. Cashew nut oil biodiesel contains 23.74% oleic, 37.9% linoleic, 15.160% linolenic, 19.32 palmitic and 3.876 stearic acids. It is 76.80% unsaturation. The fatty acid value was very high and it required pretreatment with sulphuric acid before alkaline transesterification. Most of the properties of the biodiesel are within the limits for biodiesel and can hence be used as alternative fuel for diesel engines

#### REFERENCES

- Achal (2002) Cashew: Nutrition and medicinal value. Colorado state University pp: 159-165.
- .Akinhanmi, T. F., Atasie, V. N., and Akintokun, P. O. (2008) Chemical composition and physicochemical properties Of cashew nut (*Anacardium occidentale*) oil and cashew nut Shell Liquid, Journal of Agricultural, Food, and Environmental Sciences, Volume 2 Issue 1.
- Akinwale, T. O. (2000) Cashew apple juice: its use in fortifying the nutritional quality of some tropical fruits. Eur. Food Res Technology 211, 205-207.
- Alatise, V.N., Akinhanmi, T.F. (2009). Extraction, composition studies and physiochemical characteristics of palm kernel Oil. Pak. J. Nutri. 8(6): 800-803.
- Alexander, H. T. (2008) A Nutty chemical. Chemical and Engineering News 86 (36): 26-27.
- Alptekin, A., Canakci, M. (2009) Characterization of the key properties of methyl ester-diesel fuel blends. Fuels 88(1):75-80.
- Aremu, M.O., Ogunlade, I., Olonisakin, A. (2007) Fatty acid and amino composition of protein concentrate from cashew nut, Pakistan Journal of Nutrition 6 (5): 419-423.

586

587 Bello, E.I., Agge M., Mogaji T.S. (2011) Effects Transesterification on Selected Fuel Properties of  
 588 Three Vegetable Oils. Journals of Mech. Eng. Research, Vol.3(7):218-225.

589

590 Canakci, M., Van Gerpen, J. (1999). Biodiesel production via acid catalysis. 302  
 591 Transactions of the ASAE, 42(5): 1203-1210.

592

593 Canakci, M., Van Gerpen. J. (2001) Biodiesel production from oils and fats with high free  
 594 Fatty acids. Transactions of ASAE, 44(6): 1429-1436.

595

596 Cherng-Yuan, L., Rong-Ji, L. (2009) Fuel properties of biodiesel produced from the crude  
 597 fish oil from the soapstock of marine fish. Fuel Processing Technology, Volume 90(1):130-  
 598 136.

599 Dorado, M.P., Arnal, J.M., Gomex, J., Gill, A., Lopez, F.J. (2002). The effects of a waste  
 600 vegetable oil blend with diesel fuel on engine performance. Transactions of ASAE Vol.  
 601 45(3): 519 – 523.

602

603 Ebewere, R.O., Iyayi, A.F., Hymore, F.K. (2010) Considerations of the extraction process  
 604 and potential technical applications of Nigerian rubber seed oil. Int. J. of the physical Sci.  
 605 5(6): 826- 831.

606

607 Food and Agricultural Organization of United Nations: Economic and Social Department:  
 608 The Statistical Division (FAO UNEA, 2008) Top Ten Cashew Nuts(with shell) Producers.

609

610 Frankel, E. (1991). Poison ivy, Poison oak, Poison sumac and their relative pistachios:  
 611 Mangoes and Cashew. The Boxwood Press pacific Grove CA 2, 15-16.

612

613 Ghadge, S.V., Raheman, H. (2006) Process optimization for biodiesel production from  
 614 mahua (mahuca indica) Oil using response surface technology. Bioresource technology  
 615 93(3), 379-384.

616

617 Gibbon, D., Pain, A. (1981). Crops of the drier regions of the tropics. Longman Singapore  
 618 publications Ltd, pp 66-67.

619

620 Goodrum, J.W., Kilgo, M.D., (1986). Peanut extraction using compressed carbon dioxide.  
 621 Eng. In. Agric. 8: 265-271.

622

623 Knothe, G. (2005) Dependence of biodiesel fuel properties on the structure of fatty acid alkyl  
 624 esters, Fuel process Technol 88:1059-1070.

625

626 Laza, T., Bereczky, C. (2010) Basic fuel properties of rapeseed oil-higher alcohol blends.  
 627 351 20(2):803-810.

628

629 Ma, F., Hanna, M.A. (1999). Biodiesel Production: a Review. Bioresource Technology  
 630 70(1):1-15.

631

632 McCormick,R.L., Westbrook, S.R. (2007) Biodiesel and Biodiesel blends. ASTM  
 633 standardization. News. April.

634

635 Mittelbach, M.P., Remschmidt. C. (2004). Biodiesel Comprehensive Handbook, Published by

636 Karl-Franzens-Universitst Graz, Graz, Austria.  
637  
638 Monyem, A., Van Gerpen, J.H. (2001) The effect of biodiesel oxidation on engine  
639 performance and emission, *Biomass and Bioenergy* 20: pp. 317–325.  
640  
641 National Biodiesel Board (1997). Facts on Biodiesel. National Biodiesel Board. Jefferson  
642 City, MO, USA.  
643  
644 Ramadhas, A.S., Jayaraj, S., Muraleedharan, C. (2005) Characterization and the effects of  
645 using rubber seed oil as fuel in the compression ignition engines. *Renewable Energy* 30(5):  
646 795- 803.  
647  
648 Rosengarten, F. (1984). The book of edible nuts (5th edition). Walker and Co New York, pp  
649 45.  
650  
651 Sahoo, P.K., Das, L.M., Babu, M.K.G., Naik, S.N. (2007) Biodiesel development 331 from  
652 high acid value polanga seed oil and performance evaluation in a CI engine. *Fuel*, 86(3):  
653 448-454.  
654  
655 Sayyar, S., Abidin, S.S., Yunus R, Muhammed A. (2008). Extraction of oil from jatropha  
656 seeds-Optimization and kinematics. *Am. J. App. Sci.* 6(7):1390-1395.  
657  
658 Schinas, P., Karavalakis, G., Davaris. C., Anastopoulos. G., Karonis. D., Zannikos, F.,  
659 Stournas, S., Lois, E. (2009) Pumpkin (*Cucurbita pepo* L.) seed oil as an alternative  
660 feedstock for the production of biodiesel in Greece. *Biomass and Bioenergy* 33:44-49.  
661  
662 Van Gerpen, J.C., Shanks, B., Pruszko, R. (2004) Clements, D. and Knothe, G. Biodiesel  
663 Production Technology. Contract No. DE-AC36-99-GO10337, National Renewable Energy  
664 Laboratory. US Department of Energy.  
665  
666 Van Gerpen, J.V. (2005). Biodiesel processing and production. *Fuel processing Technology*  
667 86 (10): 1097-1107.  
668  
669 Van Gerpen, J.C., Shanks, B., Pruszko, R. (2004) Clements, D. and Knothe, G. Biodiesel  
670 Production Technology. Contract No. DE-AC36-99-GO10337, National Renewable Energy  
671 Laboratory. US Department of Energy.  
672  
673 Willard, W.P. (1961) *Engineering Fundamentals of Internal Combustion Engines*. Prentice-  
674 Hall limited, Singapore, pp.323-325. 1961  
675  
676 Winterhatter, P., Mearse, H., Dekker, E. D. (1991). Fruits and volatile compounds in  
677 foods and beverages. New York, pp 389-409.  
678  
679  
680  
681  
682  
683  
684  
685