

A modified Poly(trimethylene terephthalate) used for Fused deposition modeling: Synthesis and Appliation

Abstract This paper presents the synthesis and appliation of a modified poly(trimethylene terephthalate) for Fused deposition modeling process. Five samples(S1-S5) of poly(trimethylene terephthalate-co-isophthalate-co-seacate) (PTTIS) were prepared by direct esterification and subsequent polycondensation of terephthalic acid(PTA), isophthalic acid(PIA) ($n_{PTA}/n_{PIA} = 7/3$), sebacic acid(SA) and 1,3-propanediol (PDO) with different mole percent(α_{SA}) of SA($\alpha_{SA}=0-4.8\text{mol}\%$). The samples were characterized by gel permeation chromatography (GPC), $^1\text{H-NMR}$ spectroscopy, and differential scanning calorimetry (DSC). The mechanical properties tests showed that the tensile strength, tensile modulus, and flexural strength values of the samples increase with increasing in α_{SA} up to $1\text{mol}\%$, and then decreases, while the elongation at break value the opposite, and the izod impact strength value increases with increasing in α_{SA} . The 3D printing materials which were prepared from S1-S5 were tested by a 3D printer to assess their suitability for Fused deposition modeling (FDM). The results showed that the PTTIS ($n_{PTA}/n_{PIA} = 7/3$) containing $1.0-3.8\text{mol}\%$ SA are suitable for FDM, and their anisotropy are better than that of ABS.

Key words: modified PTT, FDM, mechanical properties,3D printing, anisotropy

1. Introduction

The fused deposition modeling (FDM) is one of the most widely used rapid prototyping systems in the world due to its reliability, safe and simple fabrication process, and low cost of material. The FDM works as follow: the filamentous thermofusible plastic is melted, and the filament acts as a piston at the entrance of the liquefier head in FDM machine to force the molten material out of the nozzle, and then a solid three-dimensional object is obtained through the layer by layer deposition of the molten material [1]. The main use of the FDM

25 system is to optimize the product design, short the product development cycle, reduce
 26 development costs in aerospace, home appliances, automotive, medical, military, teaching
 27 and scientific research and other fields[2]. A number of feedstock materials are available for
 28 FDM, including an investment casting wax, thermo-plastic polyester-based elastomer,
 29 poly(acrylonitrile-butadiene-styrene) (ABS) copolymer, polycarbonate, and
 30 polyphenylsulfone. However, the greatest limitation to this technology is the lack of a variety
 31 of compatible materials, because most of the above materials do not possess the strength to
 32 produce fully functional parts using FDM, limiting the applicability of parts fabricated from
 33 FDM.

34 There are two ways to solve this problem: synthesis of new thermoplastics possessing
 35 high strength and improvement of the properties of the existing thermoplastics. Many works
 36 have been done by the second way [3-6]. A modified ABS including liquid crystal polymer
 37 (TLCP) fibers have been used in FDM system to fabricate prototype parts, and its tensile
 38 modulus and strength were about four times those of ABS [3]. The material consisting of iron
 39 particles in a nylon type matrix material have been used successfully in the unmodified FDM
 40 system for direct rapid tooling of injection moulding inserts [4]. However, few new materials
 41 for FDM system were synthesized by the first way. Poly (trimethylene terephthalate) (PTT), a
 42 new member of the thermoplastic polyester, possesses excellent mechanical properties such
 43 as high strength, good stability and abrasion resistance^[7-15]. However, it is not suitable for
 44 FDM because its melting point(~225°C) is too high. It is quite difficult to be heated to molten
 45 state for materials with high melting point in the nozzle, making FDM processing impossible.

46 In this paper, in order to solve the problem, PIA and SA are introduced into PTT to
 47 replace part of PTA, and five samples of poly(trimethylene terephthalate-co-isophthalate-co-
 48 seacate) (PTTIS) were prepared for FDM by direct esterification and subsequent

polycondensation with the constant mole ratio of PTA/PIA ($n_{\text{PTA}}/n_{\text{PIA}} = 7/3$) and different mole percent of SA ($\alpha_{\text{SA}} = 0-4.8 \text{ mol\%}$). The samples of PTTIS were characterized by gel permeation chromatography (GPC), $^1\text{H-NMR}$ spectroscopy, and differential scanning calorimetry (DSC). The effects of the content of SA on the mechanical properties of PTTIS were investigated. And the suitability of the 3D printing materials prepared from the samples were tested by a 3D printer.

2. Materials

Terephthalic acid (PTA), isophthalic acid (PIA), and sebacic acid (SA) were purchased from Shanghai Yetan Chemical Industry Co., Ltd (China), and 1,3-propanediol (1,3-PDO) was provided by Shanghai Haiyu Chemical Industry Co., Ltd (China). Tetrabutoxytitanium ($\text{Ti}(\text{OBU})_4$) was obtained from tetrabutyl titanate Shanghai Chemistry Reagent Company (China). Talc powder was provided by Shanghai huanyu Chemical co. Ltd (China). 2,5-dihexadecylhexanediamide was obtained from Shanghai Huayi Chemical Auxiliary Co., Ltd (China). Antioxygen 1076 was purchased from Zibo Xiangdong Chemical Co., Ltd (China).

3. Preparation of PTTIS

In this paper, five samples (S1, S2, S3, S4, and S5) of PTTIS were prepared by direct esterification and subsequent polycondensation from PTA, PIA, SA and 1,3-PDO, in the presence of $\text{Ti}(\text{OBU})_4$ as catalyst. Formulas for the preparation of PTTIS are shown in Table 1. The detailed preparation program was similar to that in elsewhere [16], and it was described briefly as follows: The mixture of TPA, PIA, SA, 1,3-PDO, and $\text{Ti}(\text{OBU})_4$ was put into a three-necked round-bottom flask equipped with a mechanical stirrer and a distillation column, and was continuously stirred and kept in the range of 170–215 °C until the solution becomes transparent. After esterification, the mixture was heated up to 255 °C and

kept for 2 h for polycondensation with reduced pressure (60-80Pa), thus the sample of PTTIS with various sebacic acid content could be prepared.

Table 1 Formulas for the Preparation of PTTIS

Sample	Feed ^a (mol%)		Copolyester composition ^b (mol%)	
	$\frac{n_{PTA}+n_{PIA}}{(n_{PTA}/n_{PIA})=7/3}$	SA	$\frac{n_{PTA}+n_{PIA}}{(n_{PTA}/n_{PIA})=7/3}$	SA
S1	100	0	100	0
S2	99	1	98.98	1.02
S3	97.6	2.4	97.57	2.43
S4	96.2	3.8	96.21	3.79
S5	95.2	4.8	95.19	4.81

^aMolar percent of PTA, PIA and SA fed in the polymerization

^bMeasured by ¹H-NMR spectroscopy

4. Characterization

4.1 Gel Permeation Chromatography (GPC)

The molecular weights (M_w, M_n) of the samples were determined by GPC(Waters 1515, USA) with refractometer 2414 as a detector at 25°C, using hexafluoroisopropanol as a solvent.

4.2 ¹H -NMR

The chemical compositions of the samples were analyzed by means of ¹H-NMR spectra (500 MHz NMR, Varian, MERCURY plus400) using the mixture of CDCl₃/CF₃COOD as a solvent.

4.3 Differential scanning calorimetry (DSC)

The glass transition temperature (T_g), the temperature of crystallizing peak (T_c) and the melting temperature (T_m) of the samples were determined by using a differential scanning calorimeter instrument (DSC1, METTLER TOLEDO, Switzerland) under a nitrogen atmosphere. The sample was first heated from 10°C to 220°C at a heating rate of 10°C/min

and maintained at 220°C for 5 minutes to erase the thermal history. The sample was cooled down to -10°C at a cooling rate of 70°C/min, and then heated again to 220°C at the heating rate of 10°C/min. The second heating curves were analyzed to obtain the value of T_g , T_c and T_m .

4.4 Viscosity testing

The melt viscosity of samples were measured using a Brookfield viscometer (DV-11 Pro) with a spindle (SC4-27) rotating at 15 rpm from 210°C to 230°C.

4.5 mechanical property

Tensile properties The specimens of the sample were tensile-tested in a Universal Testing Machine (SHIMADZU, AGS-X 500 N, Japan) equipped with extensometer at the room temperature according to ASTM D 638 standard. All the tests were performed with the cross-head speed of 50 mm/min. Three specimens were tested in each case, and the average value was recorded.

Izod impact properties The specimens of the sample were impact-tested in a cantilever beam impact testing machine according to GB/T1043-1992. All the tests were performed at a constant impact velocity of 3.5 m/s. Six specimens were tested in each case, and the average value was recorded.

Flexural properties The specimens of the sample were bend-tested in a bend testing machine (PT-307, Precise Test, Dongguan, China). The 2.5 kN load cell was applied for the measurements at a constant cross head speed of 1 mm/min. The mechanical testing was stopped when specimen was fractured. ten specimens were tested in each case, and the average value was recorded.

5. Results and discussion

5.1 The Molecular Weight and Chemical Composition of PTTIS

The molecular weights of S1-S5 determined by GPC were shown in Table 2. From Table 2, these samples have a similar range of molecular weights ($M_n = 72900 - 74900$ Da). The $^1\text{H-NMR}$ spectra of S1-S5 were measured and that of S3 was illustrated in Figure 1. From Figure 1, S3 shows the characteristic peaks at 7.83(a), 8.23(g), and 1.28 ppm (f), which are attributed to protons of PTA, PIA and SA, respectively. The molar ratio of the PTA, PIA, and SA units on the polymer backbone was calculated from integrations of their specific chemical shifts. The results are summarized in Table 1. The composition data in Table 1 indicates that almost all the PTA, PIA, and SA fed in the polymerization come into the resultant polymer.

Table 2. Molecular weight and distribution

Sample	Mw(Da)	Mn(Da)	Mw/Mn
S1	84600	73500	1.15
S2	86500	73900	1.17
S3	89200	74900	1.19
S4	87500	72900	1.20
S5	91300	74200	1.23

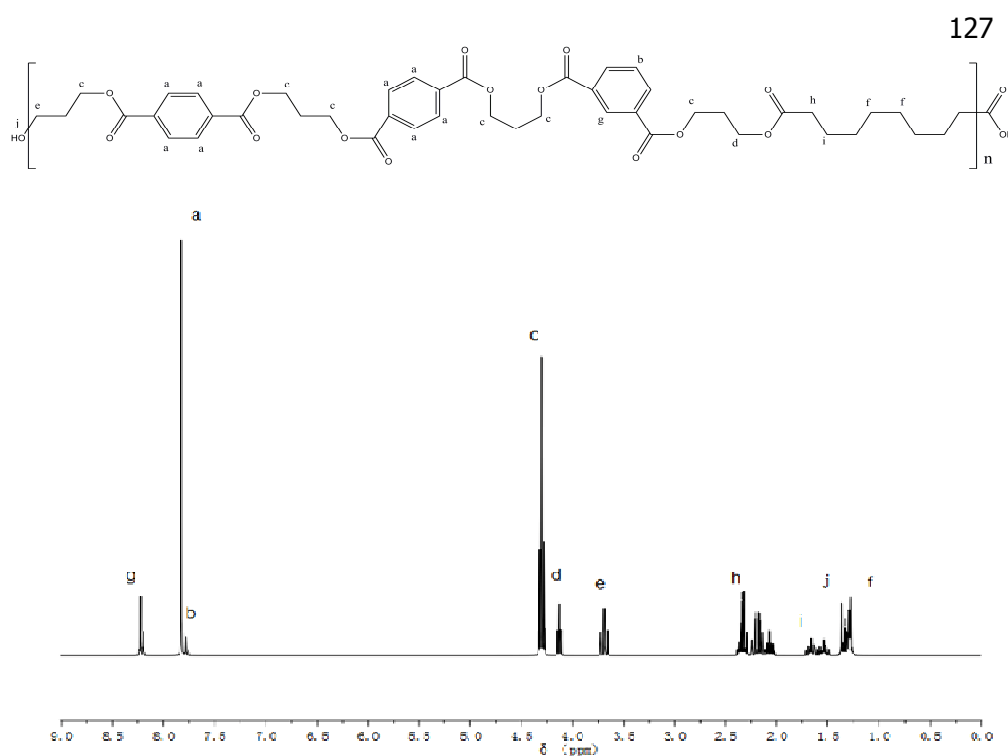


Fig 1. The ^1H -NMR spectra of S3

5.2 Thermal properties of PTTIS

Thermal properties of S1-S5 were measured by the procedure described in the above, and one of the DSC thermograms (S3) is shown in Figure 2. From the DSC thermograms, the values of T_g , T_c and T_m for the samples can be obtained and shown in Table 3. As we can seen from Table 3, the T_g values of PTTIS increases from 43.4°C to 45.9°C with increasing in α_{SA} up to 1mol%, and then decreases from 45.9°C to 35.6°C . Similarly, the T_m values of PTTIS increases from 182.8°C to 183.9°C with increasing in α_{SA} up to 1mol%, and then decreases from 183.4°C to 175.3°C . While the T_c value the opposite. The above phenomenon may be caused by the changes of crystalline properties of PTTIS. SA may play two roles in the crystallization of PTTIS: (1) it acts as a longer chain to facilitate crystallization and (2) as a third component disturbs the regularity of the co-polymer molecular chain to retard crystallization[17-19]. Therefore, from the above data, we could speculate that SA($\alpha_{\text{SA}} \leq 1\text{mol}\%$) can accelerate crystallization of PTTIS, and a lot of microcrystal can be formed in a short time to play a role similar to the "physical cross-linking point", which limits the movement of the chain segments in the non crystalline part[20] and then leads to the increase of T_g and T_m . However, the later will play its role when α_{SA} is greater than or equal to 2.4mol%.

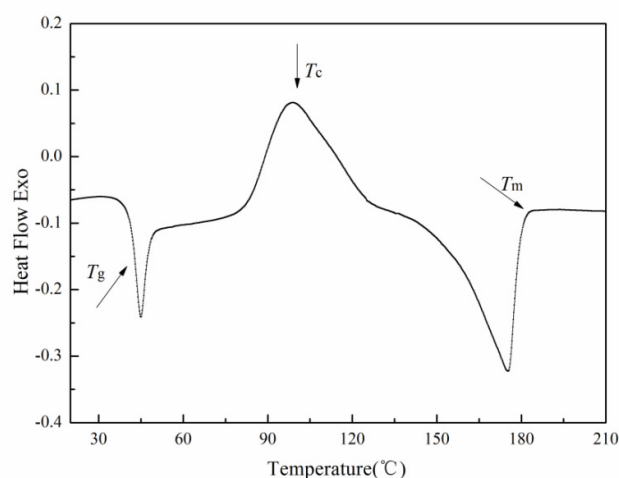


Fig 2. DSC thermograms of S3

Table 3. The values of T_g , T_c and T_m

Sample	T_g (°C)	T_c (°C)	T_m (°C)
S1	43.4	114	182.8
S2	45.9	107	183.9
S3	41.8	115	181.0
S4	40.3	118	178.6
S5	35.6	119	175.3

5.3 Mechanical properties of PTTIS

Based on the method described in the above, the results of tensile strength at peak, elongation at break, izod impact strength and flexural strength for S1-S5 were presented in Fig 3. From Fig 3, the tensile strength and flexural strength values of PTTIS increase with increasing in α_{SA} up to 1mol%, and then decreases, while the elongation at break value the opposite. These results may be also induced by the effect of SA on the crystalline properties of PTTIS.

On the other hand, the izod impact strength value increases with increasing in α_{SA} , indicating both the formation of microcrystal ($\alpha_{SA} \leq 1\text{mol\%}$) and the disturbances of the

173 regularity of the molecular chain ($\alpha_{SA} \geq 2.4\text{mol}\%$) are helpful to enhance the izod impact
174 strength.

175

176

177


178

179

180

181

182

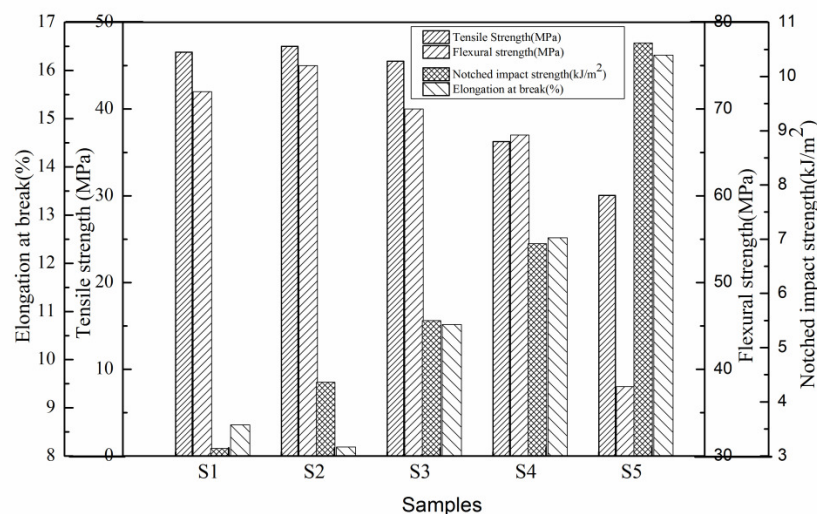

183

184 Fig 3. The values of tensile strength, flexural strength, izod impact strength and elongation at break.

185 5.4 Rheological properties of PTTIS

186 The melt viscosity values (η) of S1- S5 were measured from 210-230°C by the procedure

187 described above, and the results were shown in Table 4. From Table 4, the viscosities of

188 S2-S5 are one order of magnitude smaller than that of S1, indicating the introduction of SA

189 is beneficial to successful printing in FDM. The temperature dependency of viscosity is a

190 factor that should be considered for the practical utilization of the PTTIS, because low

191 viscosity at the time of application is a desirable attribute for its ability to be processed. The

192 relationship between η and the activation energy for flow (E) can be expressed by Equation

193 (1) and (2)

194

$$\eta = \eta_0 \exp(E / RT) \quad (1)$$

195

$$\ln \eta = E / RT + \ln \eta_0 \quad (2)$$

196 where R is the gas constant and η_0 is the pre-exponential factor. The plots of $\ln(\eta)$ versus $1/T$
 197 for the samples shown in Fig 4 are approximately linear. The E values for these samples are
 198 listed in Table 4.

199 Table 4. The melt viscosity values

Sample	melt viscosity(Pa·s)			E (kJ)
	210°C	220°C	230°C	
S1	1234	862	587	77.22
S2	174	112	78	83.35
S3	164	97	62	101.12
S4	163	102	73	83.56
S5	115	65	45	115.04

201

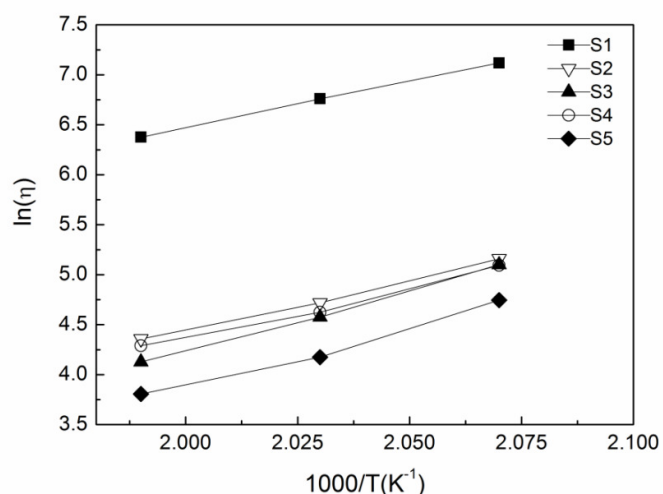


Fig 4. The plots of $\ln(\eta)$ versus $1/T$

214 5.5 Fabrication of filaments for FDM processing

215 The feedstock filaments need to be of specific size, strength and properties for
 216 successful FDM processing. In order to create such filaments from S1-S5, a desktop
 217 wiredrawing extruder (HXY-ZS, CHINA) equipped with a die diameter of 3.6mm was used.
 218 The polymer powder of S1-S5 containing talc powder as additive (1wt%), 2,5-
 219 dihexadecylhexanediamide as lubricant (0.5wt%) and antioxygen 1076 (0.5wt%) was added

to the feed hopper, and the powder material flows into the extruder barrel from the feed hopper by gravity.

During the extrusion process, die swell phenomenon occurs, and the molten material will swell when coming out of the die [21]. Because of swelling, the diameter of the filament will be bigger than that of the die. On the other hand, when the traction speed is bigger than the extrusion speed, the diameter of the filament will become smaller. Furthermore, the extrusion speed is related with the temperature of extruder barrel. In this work, the temperature of barrel heaters is generally 20°C lower than the melting point of the composite.

Since the barrel is stationary and the screw is rotating, the frictional forces will act on the material. As the material moves forward, it will heat up as result of frictional heat generated and conducted from the barrel heaters. When the temperature of the material exceeds the melting point, the melted material is simply pumped to the die. By adjusting extrusion speed and traction speed, the filaments with desired diameter are produced. After repeated test, uniform filaments have been made from S1-S5.

5.6 Printing process

The feedstock filaments made from S1-S5 were loaded into spool of a FDM machine (Panowin F3CL, Φ3mm, CHINA) and were fed into the nozzle for part fabrication. The results showed that the filaments made from S2- S4 can be printed fluently in the FDM machine in the temperature range of 210-230°C. However, the filaments made from S1 and S5 cannot be used to print parts due to nozzle clogging. The reasons for nozzle clogging may be the viscosity is too large (S1) or the bending strength is too low (S5). According to the data in Fig 3 and Table 4, the ratios (β) of bending strength to viscosity for S1-S5 at 210-230°C are listed in Table 5. From Table 5, the β values for S2-S4 are higher than that for S1 and S5 at the same temperature.

244 Table 5. The ratios (β) of bending strength to viscosity for S1-S5 at 210-230 °C

Sample	β		
	210°C	220°C	230°C
S1	0.06	0.08	0.12
S2	0.43	0.67	0.96
S3	0.43	0.72	1.13
S4	0.41	0.66	0.92
S5	0.33	0.58	0.84

245

246 **The anisotropy of UTS and elongation at break values for S2, S3 and S4**

247 Like other 3D printing methods, parts fabricated from FDM will exhibit physical property
 248 anisotropy. In most cases, the analysis of ultimate tensile strength can be used to observe the
 249 mechanical property anisotropy. For this reason, two sets of specimens were produced, one
 250 printed in the XYZ direction and the other printed in the ZXY direction(as shown in Fig 5)
 251 for each material type, and the percent difference(Δ_{UTS} and Δ_{EL} the difference in UTS values
 252 relative to the horizontally printed samples) was used to characterize the mechanical property
 253 anisotropy of the materials as follow:

254
$$\Delta_{UTS} = \frac{UTS_{(XYZ)} - UTS_{(ZXY)}}{UTS_{(XYZ)}} \times 100\% \quad (1)$$

255
$$\Delta_{EL} = \frac{EL_{(XYZ)} - EL_{(ZXY)}}{EL_{(XYZ)}} \times 100\% \quad (2)$$

256 Table 6 presented tensile test results of specimens built in different orientations. From Table
 257 6, we obtain that the values of Δ_{UTS} (23.2 – 26.7%) and Δ_{EL} (37.8 - 39.6%) for the
 258 modified PTT are lower than that for ABS ($\Delta_{UTS}=47.79\%$ and $\Delta_{EL}=75.92\%$,
 259 respectively)[22].

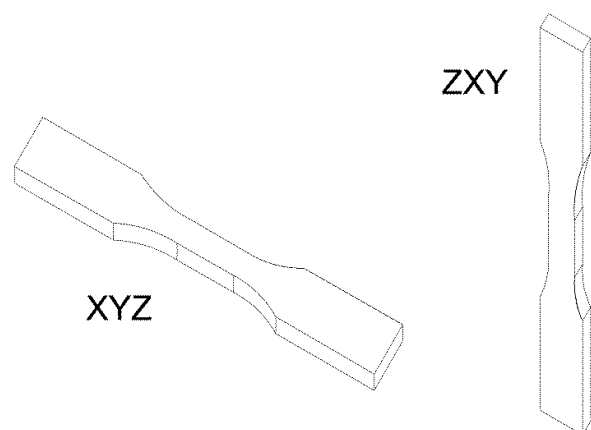


Fig 5. Specimens printed in the XYZ (horizontal) and ZXY (vertical) directions

Table 6. Tensile test results of specimens built in different orientations.

Samples	UTS(MPa)			EL (%)		
	XYZ	ZXY	$\Delta_{UTS}(\%)$	XYZ	ZXY	$\Delta_{EL}(\%)$
S2	47.22	36.26	23.2	8.19	5.13	37.8
S3	45.52	34.37	24.5	10.73	6.62	38.3
S4	36.25	26.57	26.7	12.53	7.57	39.6

6. Conclusions

The samples of PTTIS were prepared by introducing PIA ($n_{PTA}/n_{PIA} = 7/3$) and SA ($\alpha_{SA} = 0-4.8\text{mol}\%$) into PTT to replace part of PTA. The effects of α_{SA} on the mechanical properties of PTTIS were investigated, and the results showed that the tensile strength, tensile modulus, and flexural strength values of PTTIS increase with increasing in α_{SA} up to $1\text{mol}\%$, and then decreases, while the elongation at break value the opposite, and the izod impact strength value increases with increasing in α_{SA} . The 3D printing materials which were prepared from S1-S5 were tested by a 3D printer and the results showed that the PTTIS ($n_{PTA}/n_{PIA} = 7/3$) with $\alpha_{SA} = 1.0-3.8\text{mol}\%$ display desirable mechanical properties, and flexible filaments of S2-S4 can be printed fluently in the FDM machine.

278 References

- 279 [1] Yu DM. Process analysis and application for rapid prototyping based on fused deposition
280 modeling. Mach Design Manuf . 8 (2011) 65-67 (in Chinese).
- 281 [2] Chulilla Cano, J.L. The Cambrian Explosion of Popular 3D Printing. IJIMAI .4 (2011)
282 30-31.
- 283 [3] Gray RW, Baird DG, Jan Helge Bohn. Effects of processing conditions on short TLCP
284 fiber reinforced FDM parts. Rapid Prototyp J. 4 (1998) 14–25.
- 285 [4] S.H. Masood, W.Q. Song. Development of new metal/polymer materials for rapid tooling
286 using Fused deposition modeling. Mater Design. 25(2004) 587–594.
- 287 [5] M. L. Shofner, K. Lozano, F. J. Rodríguez-Macías, E. V. Barrera. Nanofiber-Reinforced
288 Polymers Prepared by Fused Deposition Modeling. J Appl Polym Sci .89(2003) 3081–
289 3090.
- 290 [6] M. Nikzad, S.H. Masood , I. Sbarski. Thermo-mechanical properties of a highly filled
291 polymeric composites for Fused Deposition Modeling. Mater Design. 32 (2011) 3448–
292 3456.
- 293 [7] Wu T, Li Y, Wu Q, Song L, Wu G. Thermal analysis of the melting process of
294 Poly (trimethylene terephthalate) using FTIR micro-spectroscopy. Eur Polym J.41 (2005)
295 2216-2223.
- 296 [8] Chen KQ, Tang XZ, Shen J, Zhou Y, Zhang B. Non-isothermal crystallization behavior of
297 poly(trimethylene terephthalate) synthesized with different catalysts. Macromol Mater
298 Eng. 289 (2004) 539-547.
- 299 [9] Sumod Kalakkunnath, Douglass S. Kalika. Dynamic mechanical and dielectric relaxation
300 characteristics of poly(trimethylene terephthalate). Polym. 47(2006) 7085-7094.
- 301 [10] Hoe H. Chuah. Orientation and Structure Development in Poly (trimethylene
302 terephthalate) Tensile Drawing. Macromolecules. 34(2001) 6985-6993.

- 303 [11] Bojie Wang, Christopher Y. Li, Jennifer Z. D. Cheng, Phillip H. Geil, Janusz Grebowicz,
304 Rong-Ming Ho. Poly(trimethylene terephthalate) crystal structure and morphology in
305 different length scales. *Polym.* 42 (2001) 7171-7180.
- 306 [12] Kurian J.V. A new polymer platform for the future-sorona from com derived 1,3-
307 propanediol. *J Polym Environ.*13(2005) 159-167.
- 308 [13] Y Xu, HB Jia, SR Ye, J Huang. Synthesis and crystallization behavior of
309 poly(trimethylene terephthalate) poly(ethylene glycol) segmented copolyesters. *J Mater*
310 *Sci.* 42(2007) 8381-8385.
- 311 [14] Jakeways R, Ward IM, Wilding MA, Hall IH, Desborough IJ, Pass MG. Crystal
312 deformation in aromatic polyesters. *J Polym Sci Polym Phys Ed.* 13(1975) 799-813.
- 313 [15] Ward IM, Wilding MA, Brody H. Mechanical-Properties and Structure of Poly (Meta-
314 Methylene Terephthalate) Fibers. *J Polym Sci Polym Phys Ed.* 14(1976) 263-274.
- 315 [16] Zhu WP, Gou PF. Synthesis, Extraction, and Adsorption Properties of Calix[4]arene-
316 poly(ethylene-glycol) Crosslinked Polymer. *J Appl Polym Sci.*109(2008) 1968–1973.
- 317 [17] Zou HT, Li G. Characterization and Crystallization Behavior of Poly(ethylene-co-
318 trimethylene-terephthalate) Copolymers. *Polym Eng Sci.*10 (2008) 511-518.
- 319 [18] George Z.P, Stavroula, GN. Synthesis and characterization of novel poly (propylene
320 terephthalate-co-adipate) biodegradable random copolyesters. *Polym Degrad Stabil.*
321 95(2010) 627-637.
- 322 [19] Zou HT, Li G. Characterization and Crystallization Behavior of Poly(ethylene-co-
323 trimethylene-terephthalate) Copolymers. *Polym Eng Sci.*10 (2008) 511-518.
- 324 [20] Liu YX, An J, Sun QY. Study on Crystallization Behavior of PET Copolyester. *Polym*
325 *Mater Sci Eng.* 4(1994) 79-84 (in Chinese).

- 326 [21] Rauwendaal C. Polymer extrusion. Munich: Hanser Publishers; 2001.
- 327 [22] Torrado, A.R., Shemelya, C.M., Wicker, R.B., Characterizing the effect of additives to
- 328 ABS on the mechanical property anisotropy of specimens fabricated by material
- 329 extrusion 3D printing, Additive Manufacturing. 6,(2015) 16-29.