

Original Research Article

Investigation of New Cooling Paints Based on Copolymers of N-Isopropylacrylamide with Butyl Acrylate and N,N-Dimethylacrylamide

ABSTRACT

New cooling paints were developed by exploiting the vaporization heat of water. These systems were prepared using various ratios of three copolymer components N-isopropylacrylamide (NIPAAm), butyl acrylate (BA), and N,N-dimethylacrylamide (DMAAm). The homopolymer of NIPAAm dissolves in water below about 32 °C (hydrophilic) and becomes insoluble above this temperature (hydrophobic). On the basis of the hydrophobic/hydrophilic switch of NIPAAm polymers, cooling paints consisting of copolymers of NIPAAm with coating materials were investigated. Copolymers of NIPAAm with BA (NIPAAm-co-BA) showed cooling effects; however, the hydrophobic/hydrophilic switch temperature decreased with the BA ratio. Copolymerization of NIPAAm-co-BA and DMAAm allowed us to adjust the switch temperature to about 30 °C. In addition, when the copolymers were pasted on the wall of a model house, at night (temperatures below approximately 30 °C), water molecules from the air were adsorbed on the materials, and when the outside temperature increased, the temperature of the room decreased. These new coating materials could cool the room on hot days without the need for electrical energy or labor.

Keywords: Cooling Paint, Vaporization Heat, Temperature Responsive Polymer, N-Isopropylacrylamide

1. INTRODUCTION

An enormous amount of energy is consumed by air conditioners, which are used to adjust room temperature especially in the summer. The demand for energy is expected to further increase with the increasing urban population in the world. Thus, there is an urgent need for materials that reduce energy consumption. In ancient times, in order to cool the atmosphere during hot days, people often used to sprinkle water on streets. More recently, wall and roof greening projects have been investigated, which can reduce the electrical energy consumption during summer; however, these approaches require electrical energy and labor for their functionality and for plant growth (e.g., water has to be pumped up to the roofs for roof greening). This energy loss is due to the use of water in the liquid state: if moisture can be converted to liquid water without the need for electrical energy, a considerable amount of energy can be saved.

We have previously proposed a new cooling system consisting of the temperature-responsive polymer, poly(N-isopropylacrylamide) (P(NIPAAm)) [1,2]. P(NIPAAm) has a lower critical solution temperature (LCST) of about 32 °C in aqueous solution [3]; it can dissolve in water at temperatures below the LCST (hydrophilic) and becomes insoluble above this temperature (hydrophobic). This hydrophilic/hydrophobic property change is proposed to occur via the coil-to-globule transition of the P(NIPAAm) main chains. At temperatures below the LCST, the polymer adopts a coiled conformation and solvent molecules can bind to the side chains of P(NIPAAm); in contrast, at higher temperatures, the polymers condense in solution [4-25]. This property is exploited in the investigation of drug delivery [26-31], separation techniques [32-38], thermoresponsive self-assembling micelles [39], etc. The behavior of P(NIPAAm) in solid state has been reported to be similar to that in solution: the polymer swollen in a small amount of water shows a phase transition at a temperature close to the LCST [1, 2, 40]. Two kinds of cooling systems can be obtained by using only temperature and humidity changes: (i) P(NIPAAm) included in mesoporous

materials [1] and (ii) NIPAAm (i.e., the monomer of P(NIPAAm)) copolymerized with coating materials [2]. At night (below 30 °C), both systems can adsorb water molecules from the air; and the water molecules are desorbed when the outer temperature rises. In addition, at temperatures < 30°C, P(NIPAAm) and the copolymers are hardly desorbed from each system into the water phase (water-proof). P(NIPAAm) in mesoporous materials can successfully decrease the temperature in a box by about 4°C with respect to the outside temperature [1]. However, only few constructions consist of mesoporous materials of nm size (some architectural materials have pores in the μm order); thus, application of this system to existing buildings is limited. In contrast, the later system (paints) has various applications, e.g., houses, trains, cars, etc. Cooling pastes have been obtained by copolymerization of NIPAAm with butyl acrylate (BA) which is a main component of commercial paints. The cooling effects of the copolymer, however, have been recorded for only 3 hours, whereas the homopolymer of P(NIPAAm) can cool the room for a day [2]. This unsatisfactory result is due to two factors: (i) the average temperature of hydrophilic/hydrophobic switch decreases with the BA ratio in the copolymer, and (ii) this switch temperature is distributed over the copolymer, i.e., in some areas of the copolymer it is about 28°C whereas in other areas it is about 25, 22, 19°C, etc. On the basis of this distribution, water molecules can be adsorbed on part of the copolymer in the summer nights, if the outer temperature is decreased to around 25°C. This distribution is caused by the homogeneous polymerization of NIPAAm with BA: because NIPAAm and BA monomers have similar behavior in radical reactions [2, 41], various chemical environments of NIPAAm are detected in the copolymer, e.g., -BA-NIPAAm-BA-, -BA-NIPAAm-NIPAAm-BA-, -BA-NIPAAm-NIPAAm-NIPAAm-BA-, etc. In order to be able to apply the cooling paints to vast areas of the world, it is important to control the temperature of hydrophilic/hydrophobic switch. In this study, we introduce N,N-dimethylacrylamide (DMAAm) to NIPAAm-co-BA, because BA and DMAAm can be classified into hydrophobic and hydrophilic polymers, respectively.

In addition, DMAAm is widely employed for the copolymerization with NIPAAm. Because DMAAm can adjust the LCST of P(NIPAAm) to approximately 40°C, which is slightly higher than normal human body temperature, the copolymers of NIPAAm with DMAAm (NIPAAm-co-DMAAm) have been used for drug delivery systems with various chemicals, including aminoethyl methacrylate, aspartic acid, dextran, glycolide, lactide, propylene, and succinimide [42-53]. NIPAAm-co-DMAAm can dissolve in water below the LCST; thus, a coating material is required in order to use this system outside of buildings (application of NIPAAm-co-DMAAm on the outside of a house on cool and rainy days is difficult).

In this work, we investigate new cooling paints based on copolymers of P(NIPAAm) with BA and DMAAm (the chemical structures are displayed in Fig. 1 and an image of this system is illustrated in Fig. 2). Because these new paints can be applied on many materials and provide cooling effects on hot days without the need for electrical energy or labor, they can find application in wide areas of the world, especially in Southeast Asia.

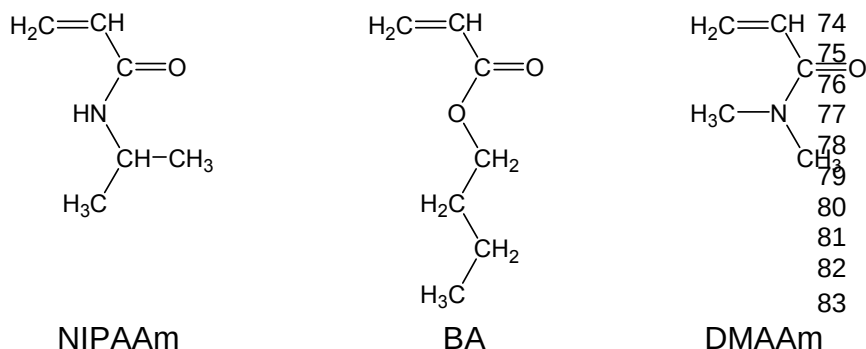


Fig. 1. Chemical structures of N-isopropylacrylamide (NIPAAm), butyl acrylate (BA), and N,N-dimethylacrylamide (DMAAm).

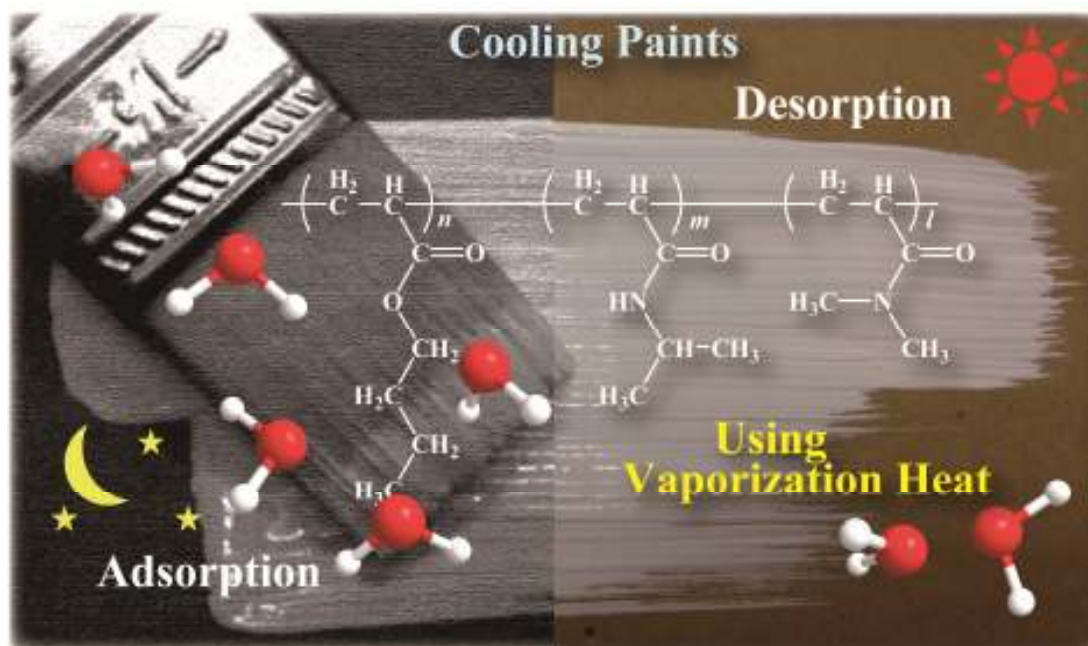


Fig. 2. Graphical abstract this study. Water molecules are adsorbed on NIPAAm-co-BA-co-DMAAm in night and desorbed from the copolymer on hot daytime. By the vaporization heat of water, rooms can be cooled. This system can actuate without the need for electrical energy or labor.

2. EXPERIMENTAL

Homopolymers of P(NIPAAm) and P(DMAAm) were prepared according to the procedures described in a previous report [2]. Copolymers of NIPAAm and DMAAm (NIPAAm-co-DMAAm), and NIPAAm, BA, and DMAAm (NIPAAm-co-BA-co-DMAAm) were obtained by the following procedure: NIPAAm, BA, and DMAA (monomers used in the ratios listed in Table 1) were dissolved in 56.6 mL of *tert*-butanol and radical polymerization was initiated by adding 0.136 g of α,α' -azobisisobutyronitrile (AIBN). The temperature of the solution was kept at 60 °C for 20 h, after which the copolymers were obtained. In this work, two notations are used to indicate the monomer ratios in the copolymers: mole ratios of NIPAAm:BA:DMAAm or NIPAAm:BA and mole% ratios of DMAAm to total amount of (NIPAAm + BA) for simple presentation of the component ratios and DMAAm ratios. The translation between the two notations is outlined in Table 1.

Differential scanning calorimetry (DSC) data were recorded on a Shimadzu DSC-60 calorimeter using Al_2O_3 as a reference material. The samples were heated from about 273 K at a rate of 3 K min^{-1} . The cooling effects of the copolymers were estimated on the basis of the following measurements: the copolymers were painted on different glass bottles with an outer diameter of 40 mm and a height of 120 mm. These bottles (sample) and blank (reference) were placed outside of a building, as shown in Fig. 3. The temperature inside the glass bottles was continuously recorded using data loggers of Sato Keiryu SK-L210T instrument.

Table 1. The mole ratios of NIPAAm, BA, and DMAAm.

NIPAAm-co-DMAAm				
DMAAm to NIPAAm	(NIPAAm : DMAAm)	NIPAAm / g		DMAAm / g
10 mol%	(0.91 : 0.09)	3.00		0.26
20 mol%	(0.73 : 0.17)	3.00		0.53
30 mol%	(0.77 : 0.23)	3.00		0.79

50 mol%	(0.67 : 0.33)	3.00		1.32
100 mol%	(0.50 : 0.50)	3.00		2.63
150 mol%	(0.40 : 0.60)	3.00		3.94
175 mol%	(0.36 : 0.64)	3.00		4.60
200 mol%	(0.33 : 0.67)	3.00		5.26
NIPAAm-co-BA-co-DMAA				
DMAAm ratios to (NIPAAm : BA)	(NIPAAm : BA : DMAAm)	NIPAAm / g	BA / mL	DMAAm / g
20 mol% (0.95 : 0.05)	(0.79 : 0.04: 0.17)	5.37	0.36	0.94
20 mol% (0.90 : 0.10)	(0.75 : 0.08: 0.17)	5.09	0.71	0.90
20 mol% (0.80 : 0.20)	(0.66 : 0.17: 0.17)	4.52	1.42	0.79
40 mol% (0.95 : 0.05)	(0.68 : 0.04: 0.28)	5.37	0.36	1.88
40 mol% (0.90 : 0.10)	(0.65 : 0.07: 0.28)	5.09	0.71	1.78
40 mol% (0.80 : 0.20)	(0.57 : 0.15: 0.28)	4.52	1.42	1.58
50 mol% (0.95 : 0.05)	(0.63 : 0.04: 0.33)	5.37	0.36	2.35
50 mol% (0.90 : 0.10)	(0.60 : 0.07: 0.33)	5.09	0.71	2.23
50 mol% (0.80 : 0.20)	(0.54 : 0.13: 0.33)	4.52	1.42	1.98

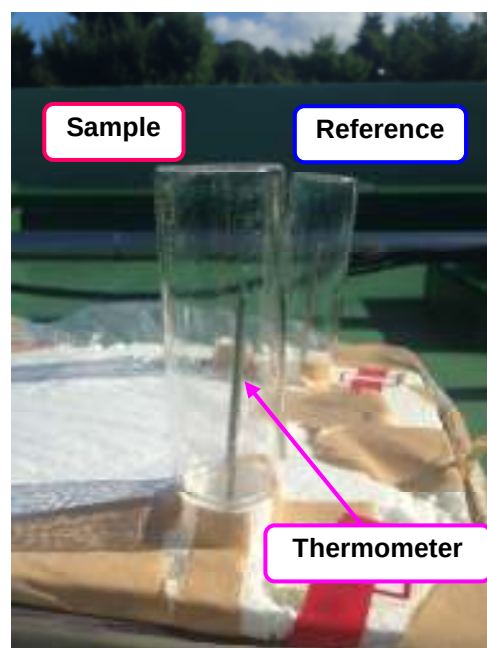


Fig. 3. Photograph of apparatus used for measuring temperatures in glass bottles outdoors.

3. RESULTS AND DISCUSSION

The introduction of DMAAm has been reported to increase the LCSTs of NIPAAm copolymers with various components [42-53]; thus, we prepared a copolymer of NIPAAm and DMAAm (NIPAAm-co-DMAAm) and we evaluated its hydrophilic effects before studying the three-component copolymer, NIPAAm-co-BA-co-DMAAm. In order to determine the hydrophobic/hydrophilic switch temperature of the copolymer, DSC measurements were performed after exposure to water vapor under ambient conditions. The DSC thermograms of the copolymers are displayed in Fig. 4. In order to confirm that the switch temperature corresponds to the LCST, a 532 nm laser light was employed. The solution can transmit the laser light below the LCST; in contrast, above the LCST, the solution becomes cloudy. The LCSTs

determined using laser irradiation are plotted in Fig. 5. Comparison of the switch temperatures (Fig. 4) with the LCSTs (Fig. 5) reveals that the LCST corresponds to the temperature obtained by DSC measurements (LCST is determined in aqueous solution, the samples studied in this work are in solid state). Our findings show that the switch temperature increased with increasing DMAAm concentration in the copolymer. This tendency is similar to that reported for copolymers formed by NIPAAm and DMAAm with various components [42-53]. In order to compare DMAAm with BA, the same measurement using laser light was performed for NIPAAm-co-BA in aqueous solution (Fig. 5). Because DMAAm and BA have opposite effects on the switch temperature of NIPAAm, we prepared three component copolymers

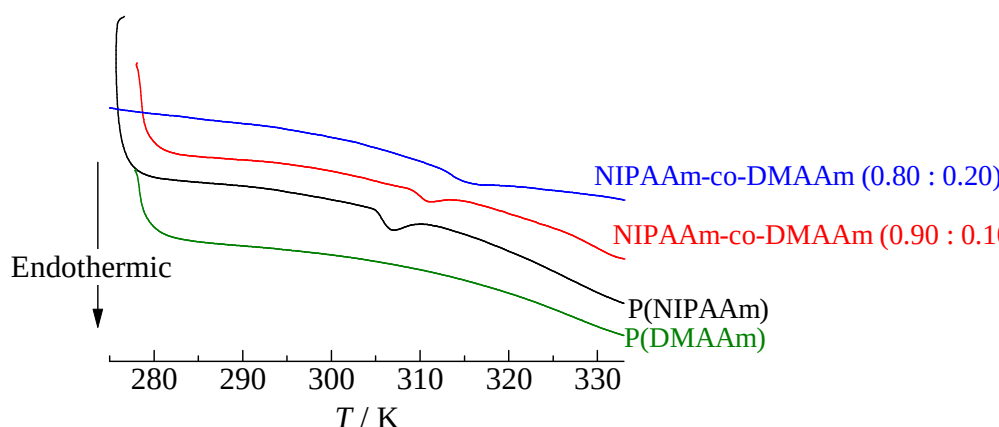


Fig. 4.
DSC
thermogr
ams of
P(DMAA
m),
P(NIPAA
m), and
NIPAAm-
co-
DMAAm

with mole ratios of 0.90:0.10 and 0.80:0.20.

In order to evaluate the hydrophobic/hydrophilic effects on the switch temperature in NIPAAm-co-BA-co-DMAAm, the LCSTs of copolymers with various NIPAAm:BA:DMAAm mole ratios in aqueous solution were determined and are plotted in Fig. 6. The LCST decreased with increasing BA ratios and increased slightly with increasing DMAAm ratios. This tendency is similar to that observed for NIPAAm-co-BA and NIPAAm-co-DMAAm, shown in Fig. 5. DSC measurements of these copolymers were also attempted; however, the signal intensity was very weak. This can be explained by the different chemical environments of the NIPAAm regions in the copolymer of NIPAAm-co-BA-co-DMAAm as compared with those in NIPAAm-co-BA and NIPAAm-co-DMAAm; the switch temperatures in the three component copolymer are therefore distributed over a wide range.

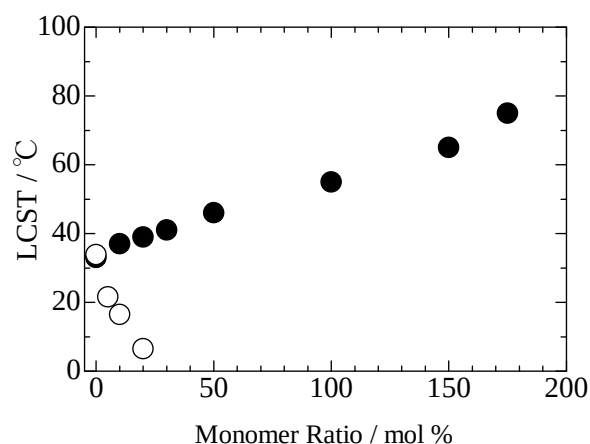


Fig. 5. Monomer ratio dependences of LCSTs observed for aqueous solution of NIPAAm-co-DMAAm(●) and NIPAAm-co-BA(○).

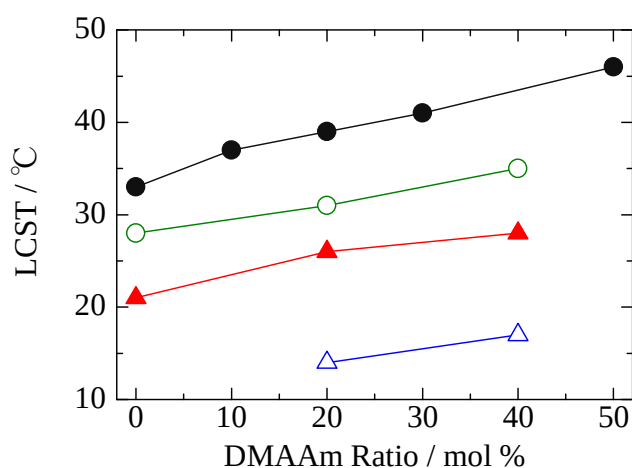


Fig. 6. LCSTs observed for NIPAAm-co-BA-co-DMAAm as a function of DMAAm ratios. In this figure, ratios of DMAAm are plotted as a function of total amount of NIPAAm and BA (ratios of NIPAAm:BA are 1.00:0.00 (●), 0.95:0.05 (○), 0.90:0.10 (▲), and 0.80:0.20 (△), respectively).

In order to evaluate the cooling effects of NIPAAm-co-BA-co-DMAAm, copolymers with various DMAAm ratios were coated onto the outer surface of glass bottles, which were placed in the apparatus together with the reference container, as displayed in Fig. 3. The temperature variations inside the containers are plotted in Fig. 7. The spikes of temperature difference (ΔT = reference - sample) recorded at around 6 and 17 o'clock can be attributed to the different heat capacity of the copolymer and the reference. As shown in Fig. 7(a), when the outer temperature was above approximately 30 °C, the inner temperature of the bottles coated with 20 mol% copolymer (0.90:0.10) was lower than that of the reference. However, in the afternoon, ΔT was reduced to about 0°C although the outer temperature remained >30°C. This tendency is similar to that observed with NIPAAm-co-BA [2]. In contrast, negative ΔT values were recorded for 40 mol% (0.90:0.10) and 50 mol% (0.90:0.10) of NIPAAm-co-BA-co-DMAAm over a wide period of time when the ambient temperature was above approximately 35°C, as shown in Figs. 7(b) and (c). This tendency of the actuated temperature to increase with increasing DMAAm concentration is

similar to that of the LCST, as displayed in Fig. 6. Thus, the negative ΔT can be attributed to the cooling effect of the copolymer. In the case of the 20 mol% (0.90:0.10) copolymer (Fig. 7(a)), the cooling effect was observed for a short period, although the outer temperature exceeded 30°C until evening. This can be explained by the same argument used for NIPAAm-co-BA [2]: because an average switch temperature of 25°C was measured for the copolymer, as displayed in Fig. 6, it can be considered that a small amount of water molecules was adsorbed on the copolymer during the night. In contrast, the LCST of the copolymers with DMAAm ratios of 40 and 50 mol% was about 30°C. Because the outer temperature decreased below this value at night, it can be deduced that the copolymer adsorbed water molecules at night and the cooling effect continued into the next day. In order to determine the amount of water molecules adsorbed on the copolymers, the weight changes of the copolymer were observed as a function of time (t) at 38 °C (although this temperature is much higher than the LCST of PNIPAAm and room temperature, it is reported that the whole polymers of P(NIPAAm) can't be condensed in aqueous solution at around 32°C (the condensation is continued until approximately 36 °C) [1]). Prior to this measurement, the NIPAAm-co-BA-co-DMAAm copolymers were exposed to water vapor at room temperature (about 20°C). The weight ratios, defined by the following equation, were plotted versus t (Fig. 8).

$$\text{weight ratio} = \frac{\text{weight of sample}(t) - \text{weight of dried sample}}{\text{weight of dried sample}} \times 100 \quad (1)$$

At a constant temperature of 38 °C (humidity of about 50%), the ratios decreased gradually with t . These weight reductions are due to the vaporization of the water molecules from the copolymer. After the first cycle of measurements, the same samples were again exposed to water vapor at room temperature (about 20°C) and then reheated (second cycle). The weights of the copolymers at the beginning and at the end of the second cycle were comparable to the values measured in the first cycle. Thus, it can be concluded that the water molecules are repeatedly absorbed and removed from the copolymers. The values reported for P(NIPAAm) adsorbed on mesoporous silica [1] and NIPAAm-co-BA [2] are also displayed, to show the effect of DMAAm on the adsorbed water weight. These data revealed that a larger amount of water molecules was repeatedly adsorbed on NIPAAm-co-BA-co-DMAAm as compared with that adsorbed on NIPAAm-co-BA. In addition, the values of water ratio recorded at $t = 0$ in the first cycle is decreased with decreasing DMAAm concentration in NIPAAm-co-BA-DMAAm. Similar ratios were recorded for 50 mol% NIPAAm-co-BA-co-DMAAm and for P(NIPAAm) in mesoporous silica at the beginning and at the end of the first and second cycle; this suggests that an amount of water molecules sufficient to cool the atmosphere is linked to the copolymers of 50 mol% NIPAAm-co-BA-co-DMAAm. These tendencies are consistent with the cooling effects observed for the copolymers and reported for P(NIPAAm) in mesoporous silica and NIPAAm-co-BA: P(NIPAAm) in mesoporous silica [1] and NIPAAm-co-BA-co-DMAAm repeatedly show the cooling effect during daytime, whereas NIPAAm-co-BA can serve until noon [2].

4. CONCLUSION

We developed new cooling paints based on NIPAAm-co-BA-co-DMAAm, which exploit the vaporization heat of water from the coating materials. The copolymers present a hydrophobic/hydrophilic switch at approximately 30°C. These systems can be widely applied to buildings, trains, cars, etc. Thus, the temperature of a room painted with the copolymers decreases if the external temperature increases to above 30°C. Because this cooling system is based on the absorption of water molecules from air during the night (if the temperature is < 30 °C), it can be activated using only temperature changes, without the use of electrical energy and labor. Thus, this system depends on climatic conditions and can be therefore applied in Southeast Asia, where temperature and humidity are high and the increasing urban population would require an enormous amount of energy in the future.

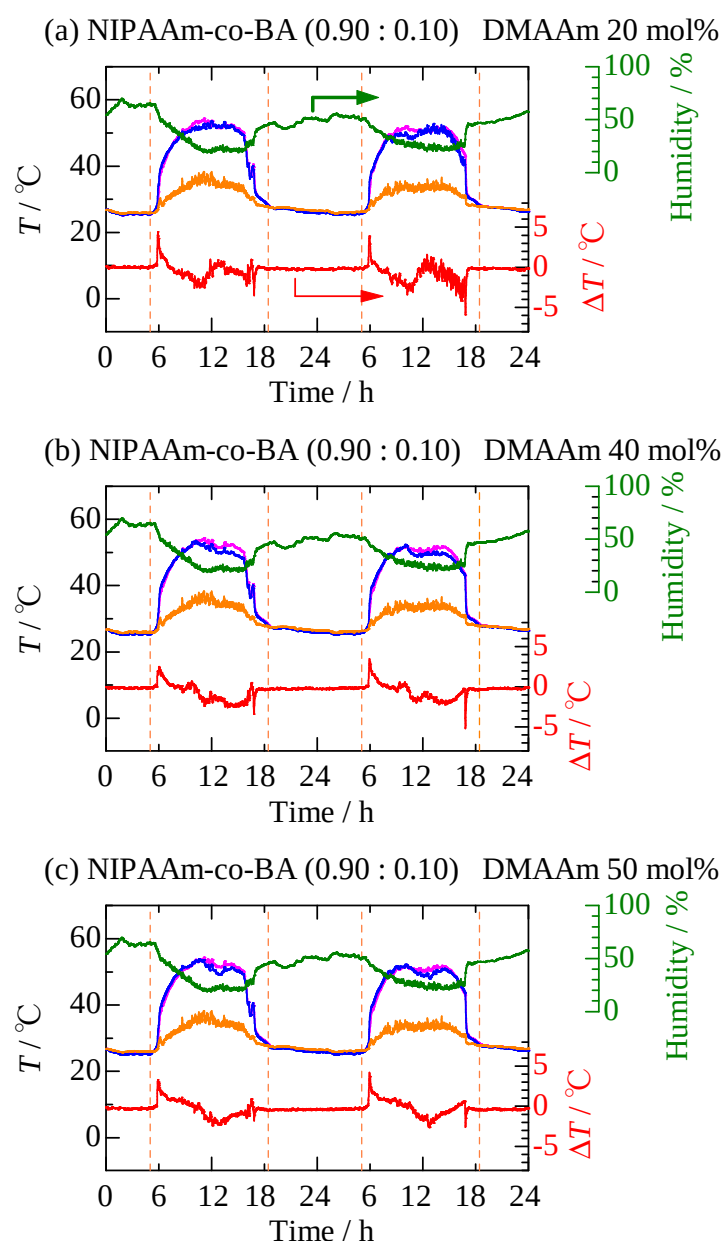


Fig. 7. Temperature changes in glass bottles coated with copolymer of NIPAAm-co-BA-co-DMAAm. DMAAm concentrations of (a) 20, (b) 40, and (c) 50 mol% relative to total amount of NIPAAm and BA with a mole ratio of 0.90:0.10. Temperatures of outer environment, reference, and sample are shown by orange, purple, and blue solid-lines, respectively. Temperature difference between sample and reference, and humidity are displayed by red and green curves. In this figure, sunrise and sunset times are shown by orange dotted lines.

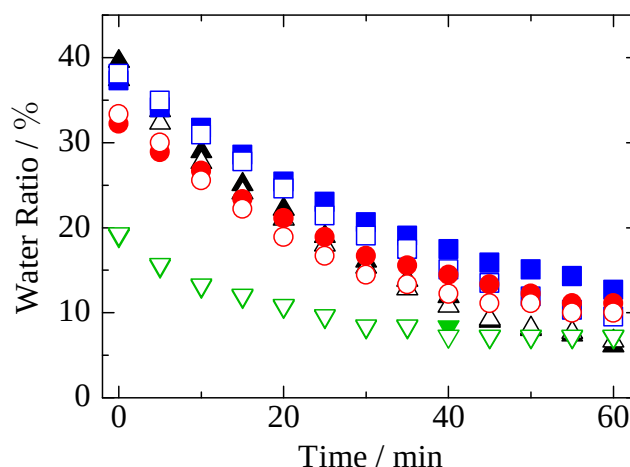


Fig. 8. Weight ratios of NIPAAm-co-BA-co-DMAAm in the first (solid) and second (open symbols) cycles at 38°C as a function of time. Red circles, and blue squares indicate DMAAm ratios of 20, and 50 mol% relative to total amount of NIPAAm and BA (0.90:0.10), respectively. Data reported in P(NIPAAm) adsorbed on mesoporous silica [1] and NIPAAm-co-BA [2] are also displayed as black triangle and green opposite-triangle, respectively.

REFERENCES

1. Suzue A, Honda H, Kadokura M, Tanaka S, Tukada H. Investigation of New Cooling Systems Based on Complexes of Temperature-Responsive Poly(N-isopropylacrylamide) with Porous Materials. *Bull. Chem. Soc. Jpn.* 2014; 87:1186-94.
2. Kadokura M, Honda H, Sasaki H, Fujita R, Tosaka A, Sekimoto K, et. al. Investigation of New Cooling Paints Actuated on Hot Days without Electrical Energy and Labors. *Asian Journal of Science and Technology*. 2016; in press.
3. Heskins M, Guillet JE. Solution Properties of Poly(N-isopropylacrylamide). *J. Macromol. Sci.* 1968; 2:1441-55.
4. Maeda Y, Higuchi T, Ikeda I. FTIR Spectroscopic and Calorimetric Studies of the Phase Transitions of N-Isopropylacrylamide Copolymers in Water. *Langmuir*, 2001; 17:7535-9.
5. Schild HG, Tirrell DA. Microcalorimetric detection of lower critical solution temperatures in aqueous polymer solutions. *J. Phys. Chem.* 1990; 94:4352-6.
6. Inomata H, Goto S, Otake K, Saito S. Effect of additives on phase transition of N-isopropylacrylamide gels. *Langmuir*. 1992; 8: 687-90.
7. Walter R, Rička J, Quellet Ch, Nyffenegger R, Binkert, Th. Coil-Globule Transition of Poly(N-isopropylacrylamide): A Study of Polymer-Surfactant Association. *Macromolecules*. 1996; 29:4019-28.
8. Fujishige S, Kubota K, Ando I. Phase transition of aqueous solutions of poly(N-isopropylacrylamide) and poly(N-isopropylmethacrylamide). *J. Phys. Chem.* 1989; 93:3311-13.
9. Cheng H, Shen L, Wu C. LLS and FTIR Studies on the Hysteresis in Association and Dissociation of Poly(N-isopropylacrylamide) Chains in Water. *Macromolecules*. 2006; 39:2325-9.

- 279 10. Maeda Y, Higuchi T, Ikeda I. Change in Hydration State during the Coil–Globule Transition of
280 Aqueous Solutions of Poly(N-isopropylacrylamide) as Evidenced by FTIR Spectroscopy. *Langmuir*. 2000;
281 16:7503-9.
- 282 11. Katsumoto Y, Tanaka T, Sato H, Ozaki Y. Conformational Change of Poly(N-isopropylacrylamide)
283 during the Coil–Globule Transition Investigated by Attenuated Total Reflection/Infrared Spectroscopy and
284 Density Functional Theory Calculation. *J. Phys. Chem. A*. 2002; 106:3429-35.
- 285 12. Stillinger FH. Water revisited. *Science*. 1980; 209:451-7.
- 286 13. Katsumoto Y, Tanaka T, Ozaki Y. Relationship between the coil-globule transition of an aqueous
287 poly(N-isopropylacrylamide) solution and structural changes in local conformations of the polymer.
288 *Macromol. Symp.* 2004; 205:209-24.
- 289 14. Sun B, Lin Y, Wu P, Siesler HW. A FTIR and 2D-IR Spectroscopic Study on the Microdynamics
290 Phase Separation Mechanism of the Poly(N-isopropylacrylamide) Aqueous Solution. *Macromolecules*.
291 2008; 41:1512-20.
- 292 15. Meersman F, Wang J, Wu Y, Heremans K. Pressure Effect on the Hydration Properties of Poly(N-
293 isopropylacrylamide) in Aqueous Solution Studied by FTIR Spectroscopy. *Macromolecules*. 2005;
294 38:8923-8.
- 295 16. Dingenouts N, Seelenmeyer S, Deike I, Rosenfeldt S, Ballau M, Lindner P, Narayanan T. Analysis of
296 thermosensitive core–shell colloids by small-angle neutron scattering including contrast variation. *Phys.*
297 *Chem. Chem. Phys.* 2001; 3:1169-74.
- 298 17. Seelenmeyer S, Deike I, Rosenfeldt S, Norhausen Ch, Dingenouts N, Ballauff M, Narayanan T,
299 Lindner P. Small-angle x-ray and neutron scattering studies of the volume phase transition in
300 thermosensitive core–shell colloids. *J. Chem. Phys.* 2001; 114:10471-8.
- 301 18. Seelenmeyer S, Deike I, Dingenouts N, Rosenfeldt S, Norhausen Ch, Ballauff M, Narayanan T.
302 Analysis of the volume transition in thermosensitive core-shell particles by synchrotron small-angle X-ray
303 scattering. *J. Appl. Cryst.* 2000; 33:574-6.
- 304 19. Yu YL, Zhang MJ, Xie R, Ju XJ, Wang JY, Pi SW, Chu LY. Thermo-responsive monodisperse core–
305 shell microspheres with PNIPAM core and biocompatible porous ethyl cellulose shell embedded with
306 PNIPAM gates. *J. Colloid Interface Sci.* 2012; 376:97-106.
- 307 20. Crassous JJ, Ballauff M. Imaging the Volume Transition in Thermosensitive Core–Shell Particles by
308 Cryo-Transmission Electron Microscopy. *Langmuir*. 2006; 22:2403-6.
- 309 21. Crassous JJ, Wittemann A, Siebenbürger M, Schrinner M, Drechsler M, Ballauff M. Direct imaging of
310 temperature-sensitive core-shell latexes by cryogenic transmission electron microscopy. *Colloid Polym.*
311 *Sci.* 2008; 286:805-12.
- 312 22. Mackiewicz M, Rapecki T, Stojek Z, Karbarz M. Environmentally sensitive, quickly responding
313 microgels with lattice channels filled with polyaniline. *J. Mater. Chem. B*. 2014; 2:1483-9.
- 314 23. Špeváček J, Dybal J. Temperature-Induced Phase Separation and Hydration in Aqueous Polymer
315 Solutions Studied by NMR and IR Spectroscopy: Comparison of Poly(N-vinylcaprolactam) and
316 Acrylamide-Based Polymers. *Macromol. Symp.* 2014; 336:39-46.
- 317 24. Ishida, N. and Biggs, S. Direct Observation of the Phase Transition for a Poly(N-isopropylacrylamide)
318 Layer Grafted onto a Solid Surface by AFM and QCM-D. *Langmuir*. 2007; 23:11083-8.

- 319 25. Ishida, N. and Biggs, S. Salt-induced structural behavior for poly(N-isopropylacrylamide) grafted onto
320 solid surface observed directly by AFM and QCM-D. *Macromolecules*. 2007; 40:9045-52.
- 321 26. Timko BP, Arruebo M, Shankarappa SA, McAlvin JB, Okonkwo OS, Mizrahi B, et. al. Near-infrared-
322 actuated devices for remotely controlled drug delivery. *PNAS*. 2014; 111:1349-54.
- 323 27 Qian J, Wu F. Thermosensitive PNIPAM semi-hollow spheres for controlled drug release. *J. Mater.*
324 *Chem. B*. 2013; 1:3464-9.
- 325 28. Wang D, Cheng D, Guan Y, Zhang Y. Thermoreversible hydrogel for in situ generation and release of
326 HepG2 spheroids. *Biomacromolecules*. 2011; 12:578-84.
- 327 29. Hoffman AS, Afrassiabi A, Dong LC. Thermally reversible hydrogels: II. Delivery and selective
328 removal of substances from aqueous solutions. *J. Controlled Release*. 1986; 4:213-22.
- 329 30. Hruby M, Konak C, Kucka J, Vetrik M, Filippov SK, Vetvicka D, et. al. Thermoresponsive,
330 Hydrolytically Degradable Polymer Micelles Intended for Radionuclide Delivery. *Macromol. Biosci*. 2009;
331 9:1016-27.
- 332 31. Saitoh T, Yoshida Y, Matsudo T, Fujiwara S, Dobashi A, Iwaki K, Suzuki Y, Matsubara C.
333 Concentration of hydrophobic organic compounds by polymer-mediated extraction. *Anal. Chem*. 1999;
334 71:4506-12.
- 335 32. Kimhi O, Bianco-Peled H. Microcalorimetry Study of the Interactions between Poly(N-
336 isopropylacrylamide) Microgels and Amino Acids. *Langmuir*. 2002; 18:8587-92.
- 337 33. Sassi AP, Shaw AJ, Han SM, Blanch HW, Prausnitz JM. Partitioning of proteins and small
338 biomolecules in temperature- and pH-sensitive hydrogels. *Polymer*. 1996; 37:2151-64.
- 339 34. Castellanos A, DuPont SJ, Heim II AJ, Matthews G, Stroot PG, Moreno W, Toomey RG. Size-
340 Exclusion "Capture and Release" Separations Using Surface-Patterned Poly(N-isopropylacrylamide)
341 Hydrogels. *Langmuir*. 2007; 23:6391-5.
- 342 35. Tokuyama H, Iwama T. Temperature-swing solid-phase extraction of heavy metals on a poly(N-
343 isopropylacrylamide) hydrogel. *Langmuir*. 2007; 23: 13104-8.
- 344 36. Fujinaga K, Yamamoto Y, Seike Y, Okumura M. An attempt to develop the hybrid liquid-solid
345 extraction method - centrifugal phase separation using poly(N-isopropylacrylamide) as an adsorbent.
346 *Anal. Sci*. 1997; 13:141-4.
- 347 37. O'Shea JP, Qiao GG, Franks GV. Solid-liquid separations with a temperature-responsive polymeric
348 flocculant: Effect of temperature and molecular weight on polymer adsorption and deposition. *J. Colloid*
349 *and Interface Science*. 2010; 348:9-23.
- 350 38. Koizumi K, Sato K, Ishimaru S. Cu²⁺ and Zn²⁺ Ion Adsorption onto a Fluorohectorite Clay-Poly(N-
351 Isopropylacrylamide) Nanocomposite Hydrogel. *Chem. Lett*. 2014; 43:769-771.
- 352 39. Hofmann C, Sch nhoff M, Do additives shift the LCST of poly (N-isopropylacrylamide) by solvent
353 quality changes or by direct interactions? *Colloid Polym. Sci*. 2009; 287:1369-76.
- 354 40. Badiger MV, Rajamohanan PR, Kulkarni MG, Ganapathy S, Mashelkar RA. Proton MASS-NMR: a
355 new tool to study thermoreversible transition in hydrogels. *Macromolecules*. 1991; 24:106-11.

- 356 41. Sasaki H, Honda H, Fujita R, Tosaka A, Sekimoto K, Kita Y, Tukada H. Application of Copolymers of
357 N-Isopropylacrylamide and Vinyl Acetates for use in Cooling Materials. *International Journal of Innovative*
358 *Research in Technology & Science*. 2016; 4:8-17.
- 359 42. Huh KM, Hashi J, Ooya T, Yui N. Synthesis and characterization of dextran grafted with poly(N-
360 isopropylacrylamide-co-N,N-dimethyl-acrylamide). *Macromol. Chem. Phys.* 2000; 201: 613-9.
- 361 43. Kumashiro Y, Huh KM, Ooya T, Yui N. Modulatory Factors on Temperature-Synchronized
362 Degradation of Dextran Grafted with Thermoresponsive Polymers and Their Hydrogels.
363 *Biomacromolecules*. 2001; 2:874-9.
- 364 44. Liu SQ, Tong YW, Yang Y. Thermally sensitive micelles self-assembled from poly(N-
365 isopropylacrylamide-co-N,N-dimethylacrylamide)-b-poly(D,L-lactide-co-glycolide) for controlled delivery of
366 paclitaxel. *Mol. BioSyst.* 2005; 1:158-65.
- 367 45. Liu SQ, Tong YW, Yang Y. Incorporation and in vitro release of doxorubicin in thermally sensitive
368 micelles made from poly(N-isopropylacrylamide-co-N,N-dimethylacrylamide)-b-poly(d,l-lactide-co-
369 glycolide) with varying compositions. *Biomaterials*. 2005; 26:5064-74.
- 370 46. Zhang JL, Misra RDK. Magnetic drug-targeting carrier encapsulated with thermosensitive smart
371 polymer: Core-shell nanoparticle carrier and drug release response. *Acta. Biomaterialia*. 2007; 3:838-50.
- 372 47. Zhang JL, Srivastava RS, Misra RDK. Core-Shell Magnetite Nanoparticles Surface Encapsulated
373 with Smart Stimuli-Responsive Polymer: Synthesis, Characterization, and LCST of Viable Drug-Targeting
374 Delivery System. *Langmuir*. 2007; 23:6342-51.
- 375 48. Liu SQ, Wiradharma N, Gao S, Tong YW, Yang Y. Bio-functional micelles self-assembled from a
376 folate-conjugated block copolymer for targeted intracellular delivery of anticancer drugs. *Biomaterials*.
377 2007; 28:1423-33.
- 378 49. Contreras-Garcia A, Bucio E, Concheiro A, Alvarez-Lorenzo C. Surface functionalization of
379 polypropylene devices with hemocompatible DMAAm and NIPAAm grafts for norfloxacin sustained
380 release. *Journal of Bioactive and Compatible Polymers*. 2011; 26:405-19.
- 381 50. Yeh J, Yang H, Hsu Y, Su C, Lee T, Lou S. Synthesis and characteristics of biodegradable and
382 temperature responsive polymeric micelles based on poly(aspartic acid)-g-poly(N-isopropylacrylamide-co-
383 N,N-dimethylacrylamide). *Colloids and Surfaces A: Physicochem. Eng. Aspects*. 2013; 421:1-8.
- 384 51. Yeh J, Hsu Y, Su C, Wang M, Lee T, Lou S. Preparation and characterization of biocompatible and
385 thermoresponsive micelles based on poly(N-isopropylacrylamide-co-N,N-dimethylacrylamide) grafted on
386 polysuccinimide for drug delivery. *Journal of Biomaterials Applications*. 2014; 29:442-53.
- 387 52. Hu Y, Darcos V, Monge S, Li S, Zhou Y, Su F. Tunable thermo-responsive P(NIPAAm-co-DMAAm)-b-
388 PLLA-b-P(NIPAAm-co-DMAAm) triblock copolymer micelles as drug carriers. *J. Mater. Chem. B*. 2014;
389 2:2738-48.
- 390 53. Hu Y, Darcos V, Monge S, Li S, Zhou Y, Su F. Thermo-responsive release of curcumin from micelles
391 prepared by self-assembly of amphiphilic P(NIPAAm-co-DMAAm)-b-PLLA-b-P(NIPAAm-co-DMAAm)
392 triblock copolymers. *International Journal of Pharmaceutics*. 2014; 476:31-40.