

Original Research Article

CORROSION BEHAVIOUR OF ALUMINIUM-IRON (Al-Fe) METAL MATRIX COMPOSITE (MMC) REINFORCED WITH SILICON CARBIDE (SiC) PARTICLES IN VARIOUS MEDIA CONCENTRATION OF TETRAOXOSULPHATE IV ACID (H₂SO₄)

Abstract:-

The current study focused on the investigation of the corrosion behavior of aluminium-iron (Al-Fe) Metal matrix Composite (MMC) reinforced with silicon carbide (SiC) particles in various media concentration of tetraoxosulphate iv acid (H₂SO₄). The Al/Fe materials were combined in various proportion of 10% wt Al/87.5% wt Fe, 15%wt Al/80% wt Fe and 20%wt Al/73% wt Fe respectively. They were fed into an electric furnace and mechanically stirred to form a fine vortex. The respective molten compositions were reinforced with silicon carbide (SiC) particles. The fabricated composite were of the composition; 2.5% SiC/10% wt Al / 87.5% wt Fe, 5%wtSiC/15%wt Al/80% wt Fe and 7%wt SiC/20%wt Al/73% wt Fe. Microstructurally scan showed signs of porosity and the weight loss corrosion test result expressed reduction in corrosion resistance with SiC addition

Keywords:- corrosion, iron, analysis, regression, statistics

INTRODUCTION

1.0 BACKGROUND OF STUDY

Corrosion is mostly a naturally occurring phenomenon commonly defined as the deterioration of a substance or its properties because of a reaction with contents in its environment. Like other natural hazard such as earthquakes, or severe weather disturbances, corrosion can cause dangerous and expensive damage to everything from automobiles, home appliances drinking water system, pipeline of various categories, bridges, glass waves, metals of different shades and buildings. It has been shown that virtually everything responds to corrosion impact from metallic and nonmetallic materials to living things in one form transformation in either shapes or content (Anyalebechi, Owate and Avwiri 2013, Koch, bronger, Thompson, Virmani and Payer 2002, Ross and Lott 2001).

Corrosion control and treatment are of vital concern because corrosion of equipment and primary structures has a great effect on the operational and structural integrity of systems including economy (John F. Kennedy space center (KSC) TM-584C. Revision C 1994). Time proven methods for preventing and controlling corrosion depend on the specific nature of the material, environmental factors such as soil resistivity, humidity, acidity or alkalinity of the conducting medium (PH factor), temperature, active of biological organism (precisely anaerobic bacterial), variation in composition of the corrosive medium and water

intrusion (Koch *et., al.*). In general, the severity of the corrosion damage cannot be overemphasized. Therefore, it is important to make corrosion prevent and control a priority in Material selection and usage in various fields of science and engineering. Among the methods employed in corrosion control and prevention are; organic and metallic protective coating, corrosion resistant alloys, plastic and polymer, corrosion inhibitors and cathodic protection used in pipeline, underground storage tanks and shore structures that create an electrochemical cell in which the surface to be protected in the cathode and corrosion reactions are mitigated (Uhlig 2008).

One of the best procedures for corrosion control is to minimize the potential for corrosive attack while designing the material and equipment through the use of corrosive resistant materials and avoiding dissimilar metal couple. Metal matrix composite is a material design technique aimed at improving material quality and corrosion resistance. A composite is a material having two or more distinct constituents, whose corrosion is affected by; the specificity of a given corrosion toward the individual components and galvanic interactions between them (Anyalebechi *et., al* 2013, Ihom, Nyior, Nor, Segun and Ogbodo 2012). Considering the importance of composite, Fontana (1987) stressed the need to assess composite in environments in which they may be likely operating. In line with the suggestion some researchers have studied composite behavior in a number

of environments. Anyalebechi et., al. (2013) studied the reduction of corrosion in various concentrations of hydrochloric acid by compositional design. Their findings showed that 30wt%Al/ 70wt%Fe composition reduced corrosion by 50%. Ihom et., al. (2012) evaluated the corrosion resistance of aluminum alloy matrix 2.5% particulate glass reinforced composite in HCl, NaOH and NaCl solution. They concluded that the composition cannot be used in NaOH and HCl environments but NaCl. Ogbonna et., al (2004) studied the corrosion susceptibility of squeeze cast Aluminum based metal composites. The work submitted that the rate of corrosion attack was proportional to volume fraction of the reinforcement agent alumina. Other relevant works are; Darvishi et., al. (2010), Owate et., al. (2012), Adeosun et., al. (2012), Asuke et., al (2009) and Bobic et., al (2010).

1.1 AIM OF STUDY

The aim of this study is to evaluate the corrosion behavior of Aluminum/iron metal matrix composite, reinforced with Silicon carbide (SiC) particulate in various media concentration of tetraoxosulphate IV acid solution.

MATERIAL AND METHOD

2.0 MATERIALS

The materials used are Aluminum alloy with determined chemical composition of;

Al	Cu	Mg	Si	Fe	Mn	Zn	Ti	Cr	Ni	K
92.01	0.06	0.57	6.58	0.16	0.06	0.20	0.14	0.20	0.01	0.01

Iron (Fe) material and silicon carbide (SiC) particles used as reinforcing material other were materials for weight less analysis, electric furnace and string rod, electronic weighing machine, mould for fabrication.

2.1 PROCEDURE

The Al/Fe material were combined in various proportion by 10%wt Al/ 87.5%wt Fe, 15%wtAl/80%wt Fe and 20%wtAl/ 73%wt Fe respectively by weight in gram. They were separately fed into an electric furnace of 1000⁰c capacity. The metal composition was stirred with the help of mechanical stirrer to form a fine vertex. The silicon carbide particles preheated was added with the molten metal composite. The molten mixture is then stirred continuously at 320 censuses. The final molten liquid metal of Al/Fe/SiC is poured into the mould which has preheated at 400⁰c. The various fabrications composite was at composite 2.5%wtSiC/ 10%wt Al/ 87.5%wtFe, 5%wtSiC/ 15%wtAl/80%wtFe and 7%wtSiC/

20%wtAl/ 73wtFe respectively. The various fabricated composite was subjected to weight loss corrosion test using various concentration of H₂SO₄ of 0.1m, 0.5m and 1.0m respectively.

Table 1: Specimen (2.5%wt sic/ 10%wt Al/ 87.5%wt Fe) in 0.1m H₂SO₄

Time(hours)	Initial weight (g) wi	Final weight (g) wf	Weight loss $\Delta w = w_i - w_f$	%weight loss $\frac{\Delta w}{w_i} \times 100$	Change in weight $w_i - \Delta w$	Log (wi- Δw)
24	34.8560	33.9253	0.9307	2.6700	33.9253	1.5305
48	34.8560	33.1515	1.7045	4.8900	33.1515	1.5202
72	34.8560	32.8553	2.0007	5.7400	32.8533	1.5166
96	34.8560	32.6148	2.2412	6.4300	32.6148	1.5134
120	34.8560	32.4160	2.4400	7.0000	32.4160	1.5107
144	34.8560	31.8235	3.0325	8.7000	31.8235	1.5027
168	34.8560	30.4990	4.3570	12.5000	30.4990	1.4883

Regression Analysis: Log versus Time(hrs)

The regression equation is

$$\text{Log} = 1.536 - 0.000249 \text{ Time(hrs)}$$


Model Summary

S	R-sq	R-sq(adj)
0.0040026	92.60%	91.12%

Analysis of Variance (ANOVA)

Source	DF	SS	MS	F	P
Regression	1	0.0010020	0.0010020	62.54	0.001
Error	5	0.0000801	0.0000160		
Total	6	0.0010821			

107

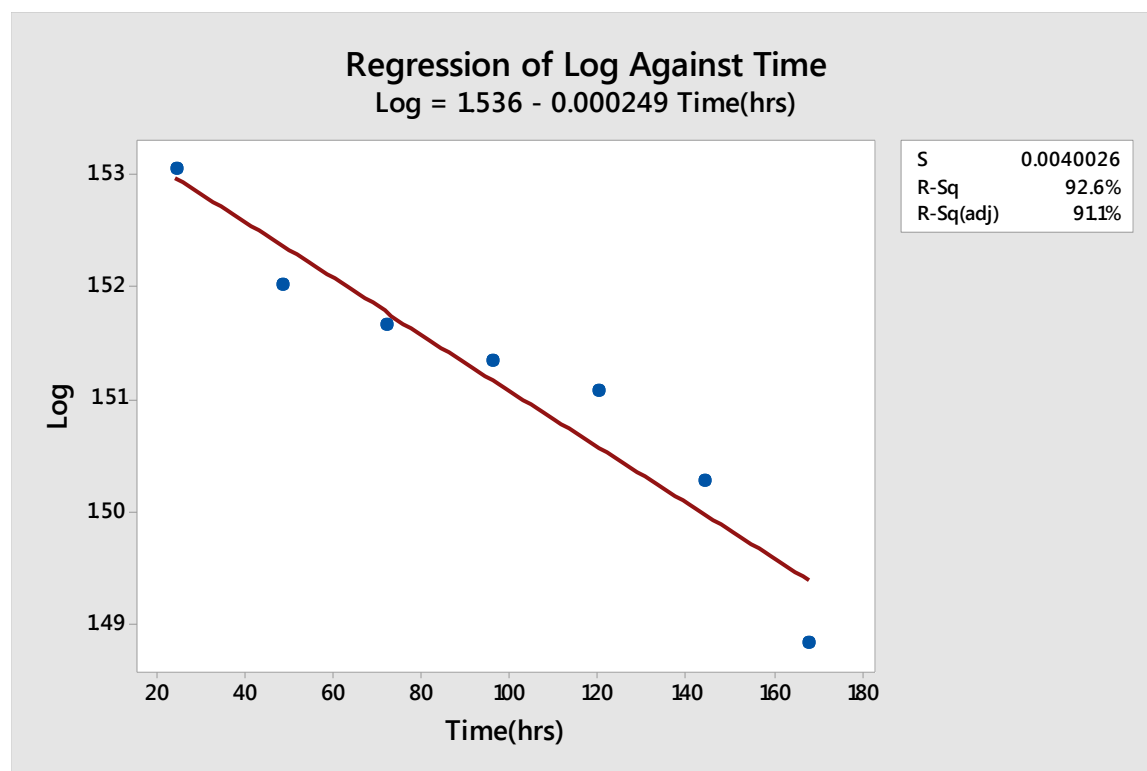

108

Figure 2.1: Regression of Log Versus Time (hrs)

109

110

Regression Analysis: %Weight Loss versus Time(hrs)

111

The regression equation is

112

%Weight Loss = 1.366 + 0.05710 Time(hrs)

113

114

Model Summary

115

S	R-sq	R-sq(adj)
1.04970	90.52%	88.62%

116

Analysis of Variance (ANOVA)

Source	DF	SS	MS	F	P
Regression	1	52.5806	52.5806	47.72	0.001
Error	5	5.5093	1.1019		
Total	6	58.0899			

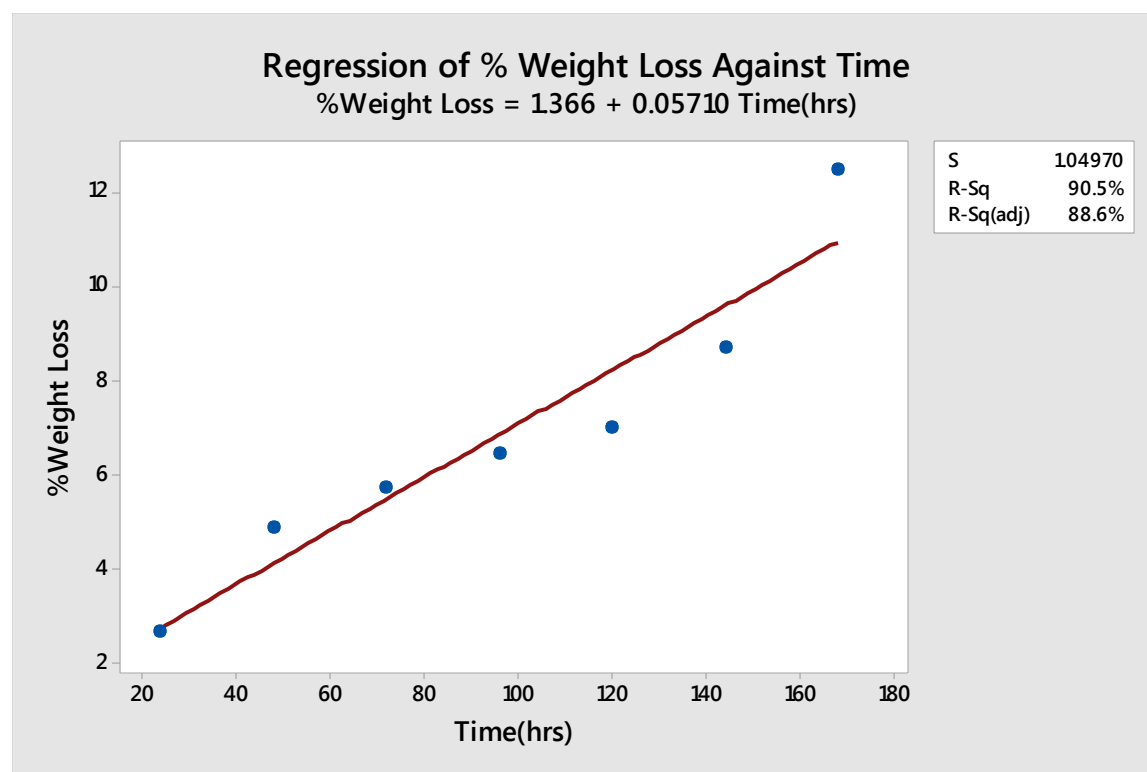


Figure 2.2: Regression of %Weight Loss Versus Time (hrs)

123 **Table 2:** Specimen (2.5% wt sic/ 10% wt Al/ 87.5% wt Fe) in 0.5m H₂SO₄

Time(hours)	Initial weight (g) wi	Final weight (g) wf	Weight loss $\Delta w = w_i - w_f$	%weight loss $\frac{\Delta w}{w_i} \times 100$	Change in weight $w_i - \Delta w$	Log (wi- Δw)
24	28.4510	27.5975	0.8535	3.0000	27.5975	1.4409
48	28.4510	27.0284	1.4226	5.0000	27.0184	1.4263
72	28.4510	26.6870	1.7640	6.2000	26.6870	1.4263
96	28.4510	26.2318	2.2192	7.8000	26.2318	1.4188
120	28.4510	26.0371	2.4183	8.5000	26.0327	1.4155
144	28.4510	25.7766	2.6744	9.4000	25.7766	1.4112
168	28.4510	25.3214	3.1296	11.0000	25.3214	1.4035

124
125 **Regression Analysis: Log versus Time(hrs)**

126 The regression equation is
127 $\text{Log} = 1.442 - 0.000228 \text{ Time(hrs)}$

128
129 **Model Summary**

S	R-sq	R-sq(adj)
0.0031130	94.54%	93.44%

130
131 **Analysis of Variance (ANOVA)**

Source	DF	SS	MS	F	P
Regression	1	0.0008382	0.0008382	86.50	0.000
Error	5	0.0000485	0.0000097		
Total	6	0.0008867			

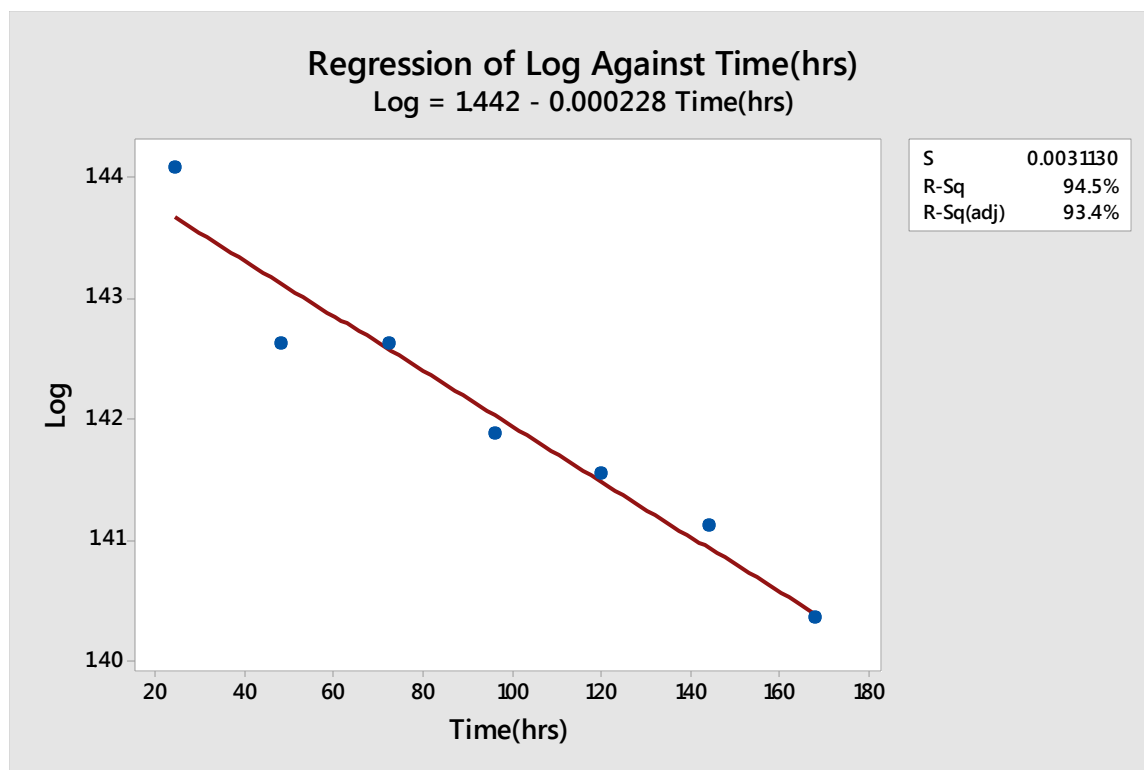


Figure 2.3: Regression of Log Versus Time (hrs)

Regression Analysis: %Weight Loss versus Time(hrs)

The regression equation is

$$\% \text{Weight Loss} = 2.257 + 0.05223 \text{ Time(hrs)}$$

Model Summary

S	R-sq	R-sq(adj)
0.393428	98.27%	97.93%

Analysis of Variance (ANOVA)

Source	DF	SS	MS	F	P
Regression	1	44.0004	44.0004	284.27	0.000
Error	5	0.7739	0.1548		
Total	6	44.7743			

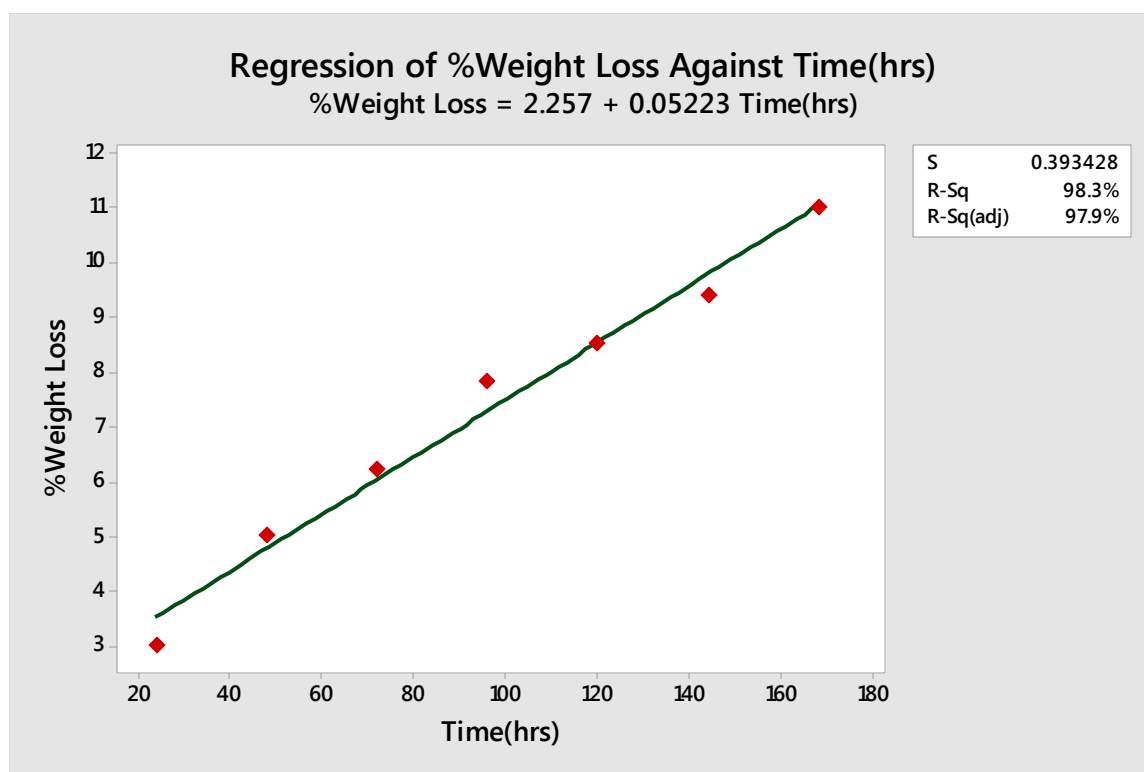


Figure 2.4: Regression of %Weight Loss Versus Time (hrs)

Table 3: Specimen (2.5%wt sic/ 10%wt Al/ 87.5%wt Fe) in 1.0m H₂SO₄

Time(hours)	Initial weight (g) w_i	Final weight (g) w_f	Weight loss $\Delta w = w_i - w_f$	% weight loss $\frac{\Delta w}{w_i} \times 100$	Change in weight $w_i - \Delta w$	Log ($w_i - \Delta w$)
24	33.6712	32.2223	1.4479	4.3000	32.2223	1.5082
48	33.6712	31.7519	1.9193	5.7000	31.7519	1.5018
72	33.6712	31.3816	2.2896	6.8000	31.3816	1.4987
96	33.6712	30.9775	2.6937	8.0000	30.7081	1.4872
120	33.6712	30.7081	2.9631	8.8000	30.7081	1.4830

Time(hours)	Initial weight (g) w _i	Final weight (g) w _f	Weight loss $\Delta w = w_i - w_f$	% weight loss $\frac{\Delta w}{w_i} \times 100$	Change in weight w _i - Δw	Log (w _i - Δw)
144	33.6712	30.4051	3.2661	9.7000	30.4051	1.4737
168	33.6712	29.7653	3.9059	11.6000	29.7653	1.4702

Regression Analysis: Log versus Time (hrs)

The regression equation is

$$\text{Log} = 1.516 - 0.000277 \text{ Time (hrs)}$$

Model Summary

S	R-sq	R-sq(adj)
0.0019540	98.48%	98.17%

Analysis of Variance (ANOVA)

Source	DF	SS	MS	F	P
Regression	1	0.0012342	0.0012342	323.25	0.000
Error	5	0.0000191	0.0000038		
Total	6	0.0012533			

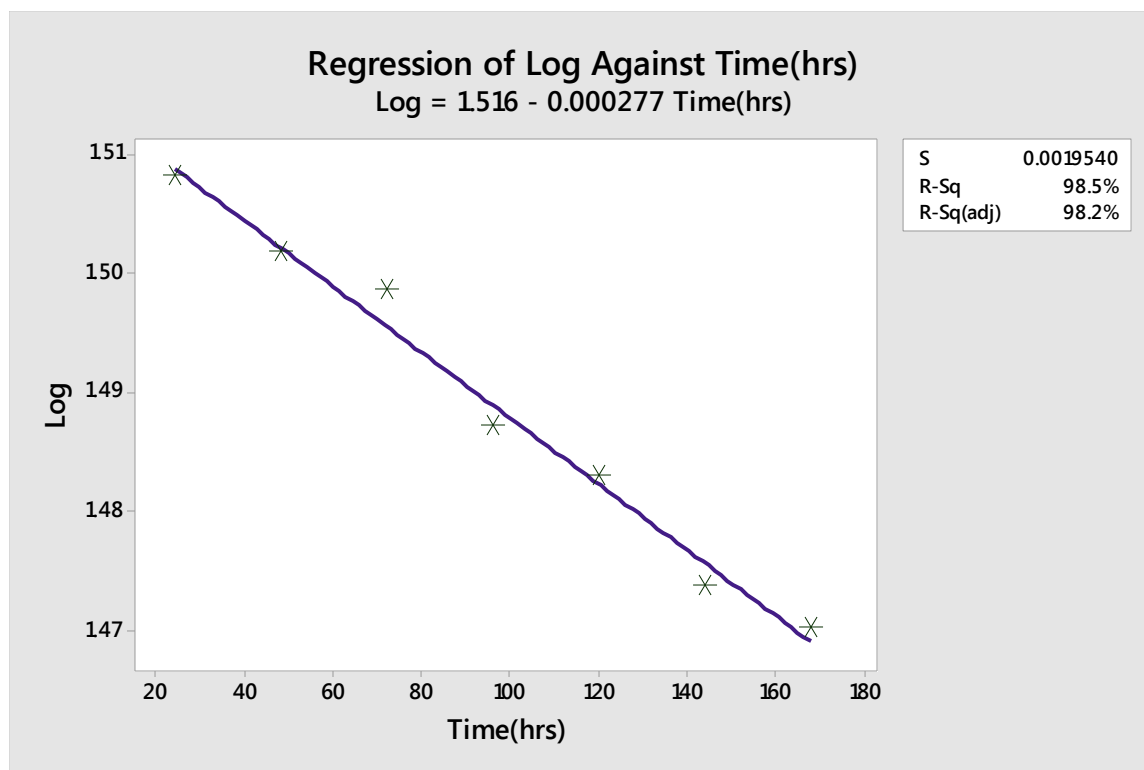


Figure 2.5: Regression of Log Versus Time (hrs)

Regression Analysis: %Weight Loss versus Time (hrs)

The regression equation is

$$\% \text{Weight Loss} = 3.286 + 0.04747 \text{ Time (hrs)}$$

Model Summary

S	R-sq	R-sq(adj)
0.280688	98.93%	98.71%

Analysis of Variance (ANOVA)

Source	DF	SS	MS	F	P
Regression	1	36.3432	36.3432	461.29	0.000
Error	5	0.3939	0.0788		
Total	6	36.7371			

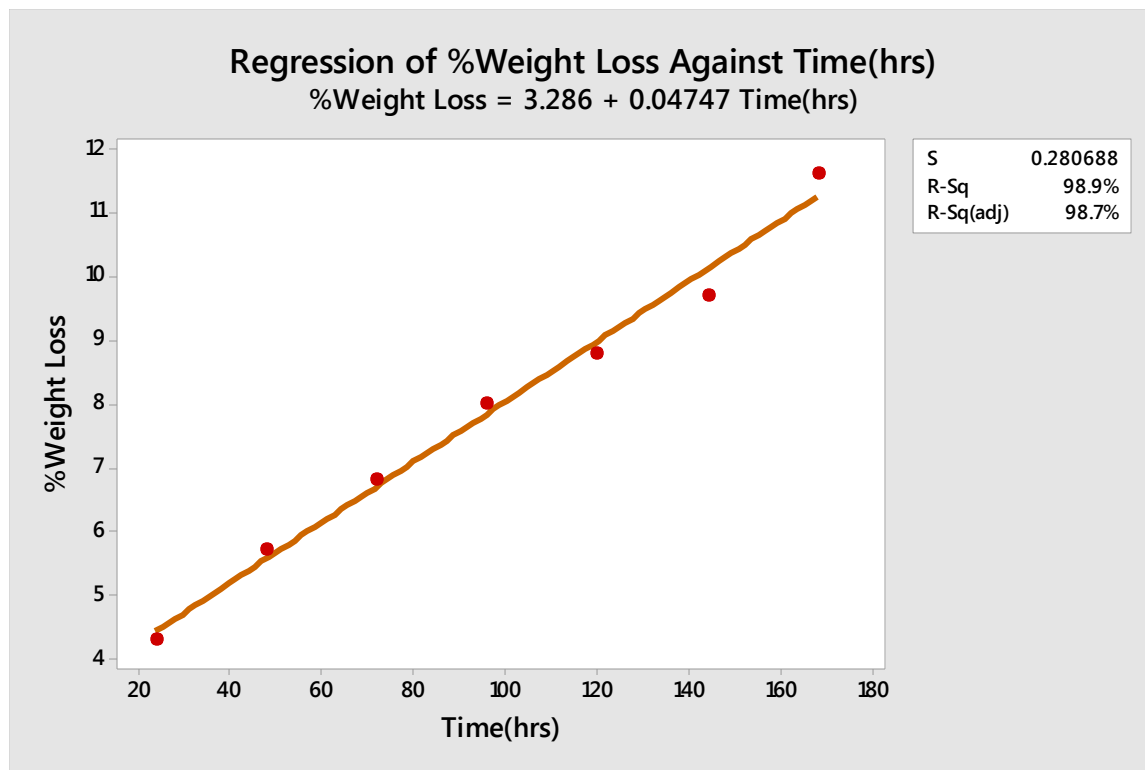


Figure2.6: Regression of %Weight Loss Versus Time (hrs)

RESULTS AND DISCUSSION

The results of this work are as presented in the tables 1-3 and figures 2.1-2.6

DISCUSSION

The graphs of $\log (w_1 - \Delta w)$ plotted against time as shown in *figures 2.1, 2.3 and 2.5* above show a straight line indicating a first order reaction kind of corrosion mechanism. The rate is found to be faster at the initial time, arising from quick depletion of dissolved oxygen (O_2) and possible temperature variation as the kinetic of the reactions are affected by the ambient environmental conditions. This is supported by the result of the regression analysis for the same $\log (w_1 - \Delta w)$ with time which gave a regression of equation of:

$$y = 1.536 - 0.000249x \dots \dots \dots eqn. 3.1$$

Indicating that reactivity was reducing with time. The reaction rate depends on the composition and the temperature of the reacting mixture (Atkin 2008, Veltegreen et., al 2003, Owate et., al 2008). This observed trend did not change remarkably throughout the composites. The graph of percentage weight loss i.e. %weight loss $(\frac{\Delta w}{w_i} \times 100)$ against time (*see figures 2.2, 2.4 and 2.6* above) was linearly increasing with an increase in SiC addition. The tendency for weight loss to increase with concentrate is obvious, initially without the addition of SiC, given that Aluminum (Al) dissolves in diluted mineral acid to liberate Hydrogen, also in Sodium Hydroxide (NaOH) solution. Again Fe/Al are amphoteric slightly, hence, the

observed behavior was further enhanced by SiC addition. This is in line with Adeosun et., al 2012, observation on issue of porosity in metal matrix composite (MMCs). Bobic et., al (2010) noted that in aqueous solution silicon carbide can serve as an inert electrode for proton or oxygen reduction depending on the SiC type, galvanic corrosion with aluminum is possible. The extent of the galvanic corrosion is strongly dependent on the type of SiC reinforcement. The electrical resistivity of SiC depend on its purity. Pitting attack is reported to be the major form of corrosion in SiC/ aluminum MMCs. Cramer et., al (2005). The resolution here is further buttressed by Aqida et., al (2004) who noted that porosity in cast metal matrix composite (MMC) has been known as a defect affecting the enhancement of strength, particularly in particle reinforced MMc. The presence of porosity decreased the mechanical properties of cast MMc as the failure process is initiated from the void formed.

The composite behavior is characterized by pitting attack in the presence of H_2SO_4 . This is in support by the finding of Ramachandra et., al (2006). Therefore, it is likely that in homogenous structure of metal matrix composite (MMC) are responsible and must be considered in designing a corrosion protection system. This inhomogeneous tendency is made obvious by the presence of SiC particles as a reinforcement material. Ramachandra et al (2006) study has shown that sliding wear, slurring, erosive wear and corrosive wear of an aluminum based metal

matrix reinforced with SiC particles resistance were considerably improved with the addition of Sic particles whereas composite corrosion resistance decreased. Emphasis on SiC addition becomes strong, giving the submission of the findings of Anyalebechi et al (2013) that after metal matrix composite reduced corrosion by 50%. Therefore, in the present study, it can be submitted in line with Ramachandra et al (2006) that the observed decrease in composition resistance of the composite was a direct consequent of SiC addition which gives rise to porosity and formation of remarkable void which reduced cohesion and inter mechanical failures.

REFERENCE

- Adesosun, S.O, Akpan, E.I, Sekunowo, O.I, Ayoola, W.A and Balogun, S.A. (2012). Mechanical characteristic of 6063 Aluminum steel dust composite. *ISSN mechanical Engineering* Vol. 2012, article ID 461853, Doi: 5402/2012/461853.
- Anyalebechi, O, Owate, I.O and Avwiri, G. (2013) reduction of corrosion in carious concentration of hydrochloric acid by compositional design. *Academic journals* vol.8 (27) pp.1328-1333.
- Aqida S. N, Ghazali M.I and Hashim J (2014). Effect of porosity on mechanical properties of metal matrix composite; *an overview journal Teknologi* 400 (A) 17-32
- Barbuleseu and OiAC, I. (2008) Corrosion analysis and Models for some composites behavior in saline media. *International journal of Energy and Environment*, issue 1. Vol.2
- Bobic B, Mitrovic S., Babic M. and Bobic I. (2010) corrosion of metal-matrix composite with Aluminum Alloy substrate. *Tribology in industry* Vol. 32. No1 pp 11

- Darvishi A, Maleki A, Alabaki, M.M and Zargami, M. (2010) the mutual effect of iron and manganese on microstructure and mechanical properties of Aluminum- silicon Alloy. *Mjom*, Vol.16. no.1. pp. **11-24**.
- Ihom, A.P, Nyior G.B, Nor I.J, Segun, S and Ogbodo, J (2012) Evaluation of the corrosion Resistance of Aluminum Alloy matrix 12.5% particulate Glass Reinforced Composite in various media. *International Journal of Science and Technology*, Vol.1 No,10 pp. **560-568**.
- Kamaal Haider, Md. Azid Alam, Amit Redhewal and Vishal saxena (2015). Investigation of mechanical properties of Aluminum based metal matrix composite reinforced with SiC and Al₂O₃. *Int. journal of Engineering Research and Application*. ISSN 2248-9622. Vol.5. Issue 9 (part 2) **pp 63-69**
- Mamatha, G.P, Pruthviriral, R.D and Ashok, S.D (2011). Weight loss corrosion studies of Aluminum -7075 Metal Matrix Composites Reinforced with Sic Particulates in HCl solution. *International Journal of research in Chemistry and Environment*. Vol.1 issue 1.pp. **85-88**. ISSN 2248-9649.
- Owate, I.O, Ezi, C.W and Avwiri, G (2002) impact of environmental condition on sub-surface storage tanks. *Journal of applied Science and Environmental Management*, Vol.6. NO.2, pp. **79-83**.
- Sridhar Raja K.S and Bupesh Raja V.K (2015) corrosion Behaviour of Boron carbide reinforced Aluminum metal matrix composite. Asian research publishing Network (ARPN). *www. April journals.com*