

Kinetic Study, Modelling and Optimization of Adsorption Processes for Removal of Crude Oil from Contaminated Water using Chitosan-Rice Husk Ash Composite

ABSTRACT

This study was aimed at developing chitosan-rice husk ash adsorbent for the removal of crude oil from contaminated water. Design Expert software 6.06 was used to design the adsorption experiment. The adsorption was tested for Langmuir, Freundlich and Temkin isotherm and the kinetic studies also carried out. The effect of influencing parameters such as contact time, adsorbate concentration, adsorbent dosage and formulation ratio were studied. It was generally shown that adsorption process increases with time and adsorbate concentration and decreases with adsorbent dosage. Models for the prediction of adsorption capacity for the composite was significant with R^2 value of 0.8382 and P-value of 0.0017. optimum conditions were found to be 0.90 wt/wt chitosan/silica ratio, contact time of 5 min, and oil/water ratio of 0.25 v/v, which gave 20.66 g/g sorption capacity respectively. Adsorption isotherm studies of Langmuir, Freundlich and Temkin were carried out for the chitosan-rice husk ash composite. Temkin isotherm best fitted with R^2 value of 0.9999. The adsorption capacity of composite from isotherm studies was obtained to be 18.85 g/g adsorbent. The heat of adsorption b_T (kJmol^{-1}) obtained from Temkin isotherm study was -48.67 kJ/mol indicating physisorption of adsorbents to the crude oil. For the kinetic studies, the pseudo-second order model suitably described the removal of crude oil by composite with R^2 value 0.9999.

Keywords: rice husk ash; Adsorption; Batch studies, Adsorption isotherms; Adsorption kinetics, Design Expert.

1. INTRODUCTION

Oil contamination is one of the most serious environmental problems and it is becoming increasingly inevitable. The dependency on crude oil derivatives for energy demand has created a need to transport petroleum from drilling point to industries where it is being processed into fuels and petrochemical products and then to areas needed for use and consumption. Crude oil spill constitutes one of the major sources of contamination in seas, oceans and navigable waters. The enormous and undesirable taste and odour that affects tourism, economy and environment make it rapid to be removed quickly. So, water sources protection must be one of the essential concerns in our life and necessary actions should be done to remove these pollutants because the balance of the ecosystem depends on water purity. Also transportation process from petroleum industries sometimes contaminate the environment with crude oil and its products as a result of aging of pipelines, equipment failure, corrosion, accidental operational problems or by sabotage. [1-6, 17]. There is a major

need to explore the biological means of control especially agricultural waste for sustainability and consideration of economy of operation.

Raw rice husk has been used for oil removal in a laboratory simulated case of about 5g/g adsorbent [8]. Thermally treated rice husk silica has also been used for crude oil sorption [9] with sorption capacity of 15.2g/g of adsorbent at optimum temperature of 700°C. Chitosan which occurs naturally in the environment in large quantities and runs second in abundance to cellulose, has been used for adsorption purposes. It has an amine functional group which is strongly reactive with metal ions [10]. Acetylated rice husk was used as reported by Nwankwere *et al.* [11] to carry out crude oil sorption studies with sorption capacity of 10.31g/g of adsorbent. Researches have shown the uptake of metal cations [12] and crude oil [13] by chitosan. The high porosity of this natural polymer results in novel binding properties for metal and lipids making it buoyant on surface of water while rice husk silica which can be easily sourced is not.

The aim of this study is to develop chitosan-rice husk ash adsorbent for removal of crude oil from crude oil contaminated water. Response surface methodology which is one of the powerful tools for developing and improving processes will be employed to study and optimize the effect of factors that affect the adsorption process and to develop model equation for the prediction of the adsorption capacity. This is in addition to conducting equilibrium and kinetic studies of the process.

2. MATERIALS AND METHODS

2.1 Adsorbent preparation

Rice husk was locally sourced from Zaria – Nigeria, thoroughly washed with tap water to remove stones and dirt. It was then dried under atmospheric condition to avoid thermal shock on the material. The dried rice husk was then soaked in 10 w/w % sulphuric acid and boiled for 1 hour and then allowed to stay for 24 hours in the boiled acid solution to remove excess carbohydrates. The rice husk was then thoroughly washed with distilled water to reduce its pH to 6.6 which was close to neutrality and was then dried atmospherically. The beneficiated and acid pre-treated rice husk was charred in an oven for 2 hours at 200 °C. The charred rice husk was transferred to the furnace where it was carbonized at 700 °C for 6 hours to avoid phase transformation of silica from amorphous to crystalline surface [11].

Chitosan powder was locally synthesised from shrimp shell by demineralization (1M HCl treatment for 6 hours 25°C), deproteinization to obtain chitin using 1M NaOH (Sigma Aldrich, 98) treatment for 16 hours at 25°C and finally deacetylation of chitin to obtain chitosan (25M NaOH treatment for 20 hours at 115 °C 1atm). Rice husk ash and chitosan powder were mixed using physical admixture method using different formulation ratios obtained by Design Expert. Other influencing factors like contact time and crude oil-water contamination ratio were also studied.

2.2 Batch adsorption experiment

Batch biosorption experiments were conducted to investigate the influence of parameters such as contact time, oil-water initial concentration ratio and adsorbent dosage crude oil adsorption using Design Expert 6.06. For adsorption process, 0.25 grams of composite was put into a beaker containing the calculated 0.25% v/v oil/water ratio for five minutes and agitating the mixture for 200 r.p.m using mechanical shaker for each run. The same procedure was repeated for other designed conditions of formulation ratios, time and adsorbate concentration. The mixture was poured into a sieve and allowed to drain to get the new weight of the added adsorbent.

The oil sorption capacity (OSC) of the sorbents was determined from Equation 1 [11].

$$OSC = \frac{\text{Weight Gain}}{\text{Original Weight}} \quad (1)$$

2.3 Optimization of the adsorption process

The response (OSC) was fed into the experimental design and generated the model equation for the adsorption process. Optimization study was also conducted using the Design Expert, this gave the optimum conditions for the process. The results were statistically analyzed and presented in the appropriate section.

2.4 Isotherm and kinetic studies

Studies were conducted for Langmuir, Freundlich and Temkin adsorption isotherm. Pseudo-first-order, Second order, Pseudo-second-order and Elovich kinetic model were also studied.

The amount of oil adsorbed into the adsorbent is designated by q in g/g of the adsorbent and given by the formula $q = \frac{V}{W}(C_o - C_e)$ (2)

Where C_o and C_e (g/mL) are the concentration of oil at initial and equilibrium respectively, W is the weight of the adsorbent used in grams and V is the volume of the solution in litres

3. RESULTS AND DISCUSSION

Table 1 presents the experimental design as well as the response (OSC) for the adsorption of laboratory simulated water contaminated with crude oil.

Table 1: Results of adsorption of crude oil from water/crude oil mixture using chitosan-silica composite.

Run	Chitosan/Silica wt/wt %	Time Minutes	Oil/Water v/v. %	OSC g/g, %
1	0.50	32.50	0.14	8.9920
2	0.10	60.00	0.14	5.5520
3	0.90	32.50	0.02	12.232
4	0.90	5.00	0.14	11.192
5	0.10	32.50	0.25	19.497
6	0.50	32.50	0.14	8.1520
7	0.90	60.00	0.14	8.8320
8	0.50	5.00	0.25	8.4720
9	0.90	32.50	0.25	7.4720
10	0.50	32.50	0.14	6.5920
11	0.50	32.50	0.14	7.9920

12	0.50	32.50	0.14	8.2320
13	0.50	60.00	0.25	21.632
14	0.10	5.00	0.14	7.3920
15	0.50	5.00	0.02	6.5920
16	0.50	60.00	0.02	14.272
17	0.10	32.50	0.02	8.4800

106

107

108 Table 2 shows the analysis of variance (ANOVA) for linear model and parameters
 109 contributing to adsorption. The Model F-value of 8.63 implies the model is significant. The
 110 model terms are also significant ($P = 0.0017$). In this case A and AB are significant model
 111 terms.

112


113

114 Table 2: ANOVA response for linear model to identify the significant contributing factors

Source	Sum of Squares	DF	Mean Square	F Value	Prob>F
Model	258.25	6	43.04	8.63	0.0017*
A	175.67	1	175.67	35.23	0.0001*
B	7.22	1	7.22	1.45	0.2566
C	23.23	1	23.23	4.66	0.0563
AB	32.95	1	32.95	6.61	0.0279*
AC	12.93	1	12.93	2.59	0.1384
BC	6.25	1	6.25	1.25	0.2891
Residual	49.87	10	4.99		
Lack of Fit	49.74	6	8.29	260.51	0.0001 *
Pure Error	0.13	4	0.032		
Cor Total	308.1	16			

115 Std. Dev.=1.52; R-Squared=0.8382 * significant variable

116

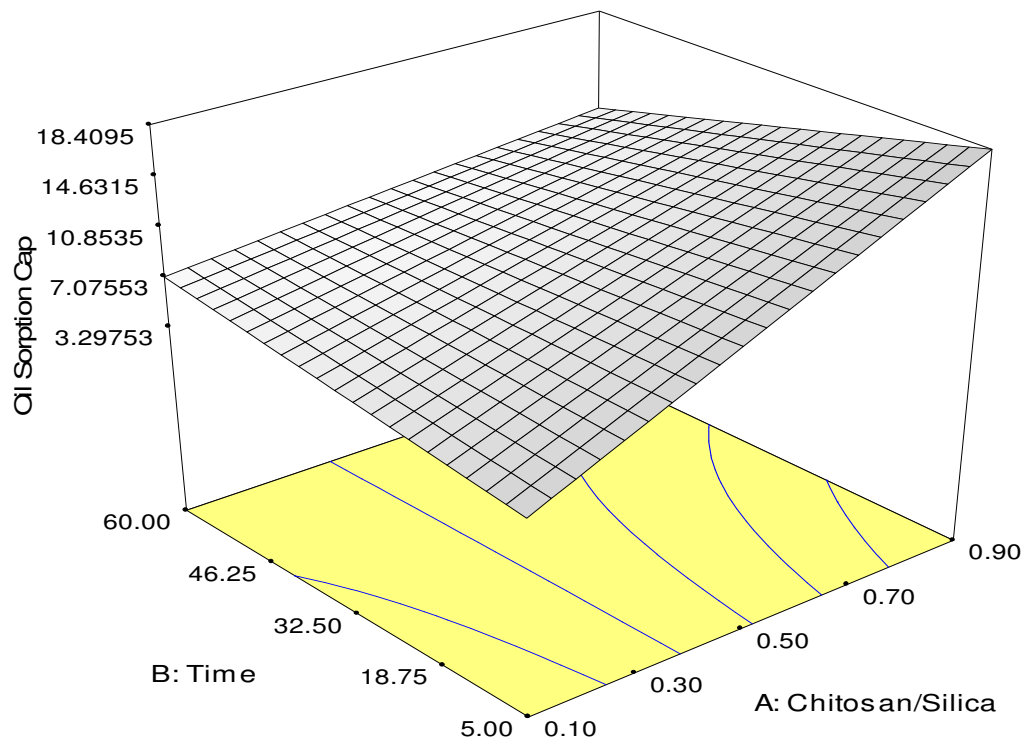

117
118 Figure 1: Response surface 3D plot of OSC versus Contact time and Chitosan/Silica.

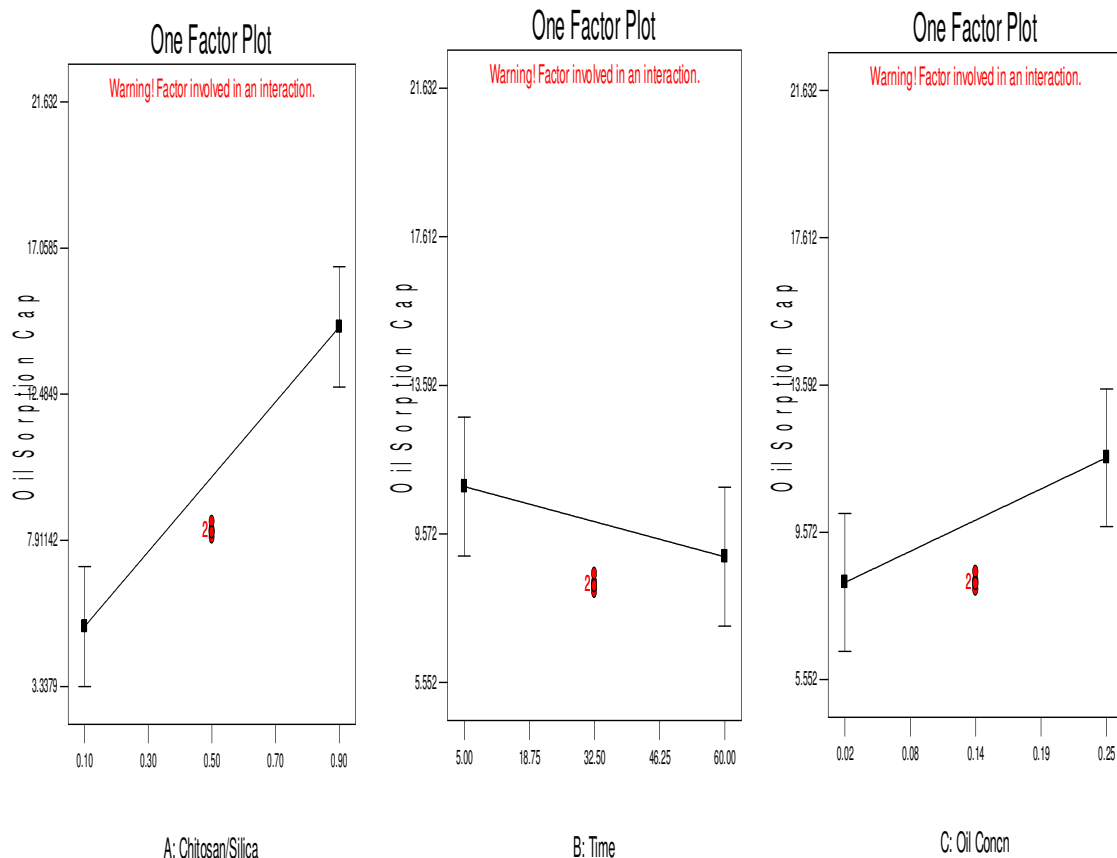


Figure 2: Composite adsorption capacity curve against the variables

Figure 1 (3-D plot) presents the response (Oil sorption capacity) with two combined influencing factors while Figure 2 shows the effect of one factor at a time. It can be interpreted that oil sorption capacity of composite increased with increase in the formulation ratio and oil water ratio while contact time decreased as sorption increased. This could be attributed to the high adsorption capacity of chitosan present in the composite over rice husk silica. Thus, the more percentage composition of **chitosan present** in the composite blend, the better the adsorption. This is due to enhanced buoyancy and lipids attracting ability of chitosan.

Final equation in terms of actual influencing factors:

$$OSC = +3.30120 + 14.91781A + 0.042549B - 17.57194C - 0.26091AB + 39.08696AC + 0.39526BC \quad (3)$$

where A, B and C are Chitosan/Silica ratio, Contact time and Oil/water ratio respectively. The model equation can be used to predict the adsorption capacity of the process. Optimization was also conducted for the process using the Design Expert and the results for the optimum conditions were found to be 0.90 wt/wt, 5 min, 0.25 v/v, and 20.66 g/g for chitosan/silica ratio, contact time, oil/water ratio and sorption capacity respectively.

3.1 Langmuir adsorption isotherm

Langmuir is the simplest type of theoretical isotherms. Langmuir adsorption isotherm describes quantitatively the formation of a monolayer of adsorbate on the outer surface of the adsorbent, and after that no further adsorption takes place. Langmuir thus represents the equilibrium distribution of adsorbate between the solid and liquid phases [15].

The Langmuir isotherm assumes that the ability of molecule to bind and be adsorbed is independent of whether or not neighbouring sites are occupied. This means, there will be no interactions between adjacent molecules on the surface and immobile adsorption. It also means, trans-migration of the adsorbate in the plane of the surface is prevented. Equation 4:

$$\frac{C_e}{q_e} = \frac{1}{q_m} C_e + \frac{1}{q_m b} \quad (4)$$

Where C_e = equilibrium concentration q_e = the amount of adsorbate adsorbed for unit mass.

The plot of $\frac{C_e}{q_e}$ against C_e will help determine q_m and b , they are related to standard monolayer adsorption capacity and the Langmuir constant, respectively.

A dimensionless separation factor or equilibrium parameter, R_L was proposed by Hall *et al* [9] as an essential feature of the Langmuir Isotherm to predict favourability of adsorption which is defined as:

$$R_L = \frac{1}{1 + bC_0} \quad (5)$$

C_0 = reference fluid-phase concentration of adsorbate (mg/l) b = Langmuir constant (ml/mg)

3.2 Freundlich adsorption isotherm

Freundlich isotherm is commonly used to describe the adsorption characteristics for the heterogeneous surface. It represents an initial surface adsorption followed by a condensation effect resulting from strong adsorbate-adsorbate interaction. Freundlich isotherm curves in the opposite way of Langmuir isotherm and is exponential in form. The heat of adsorption, in many instances, decreases in magnitude with increasing extent of adsorption. This decline in heat is logarithmic implying that the adsorption sites are distributed exponentially with respect to adsorption energy. This isotherm does not indicate an adsorption limit when coverage is sufficient to fill a monolayer. It is given by Equation 6.

$$\log q_e = \frac{1}{n} \log C_e + \log K_f \quad (6)$$

K_f = Freundlich constant related to maximum adsorption capacity (mg/g). It is a Temperature-dependent constant.

n = Freundlich constant related to surface heterogeneity (dimensionless). It gives an indication of how favourable the absorption process is.

3.3 Temkin adsorption isotherm

Temkin isotherm contains a factor that explicitly takes into the account of adsorbent – adsorbate interactions. By ignoring the extremely low and large value of concentrations, the model assumes that heat of adsorption (function of temperature) of all molecules in the layer would decrease linearly rather than logarithmic with coverage [16]. Its equation is given:

$$q_e = \frac{RT}{b_T} \ln C_e + \frac{RT}{b_T} \ln K_T \quad (7)$$

Where A_T = Temkin isotherm equilibrium binding constant (L/g)

b_T = Temkin isotherm constant R = universal gas constant (8.314J/mol/K)

T = Temperature at 298K. B = Constant related to heat of sorption (J/mol)

The isotherm studies of chitosan-rice husk silica ash composite are shown in the Figure 3, 4 and 5. The kinetic and isotherm parameters are also as presented in Table 3 and 4 respectively.

190 3.4 Pseudo-first-order kinetics

191 Lagergren showed that the rate of adsorption of solute on the adsorption is based on the
192 adsorption capacity and follows a pseudo-first-order equation [12, 20]. Equation 8 present
193 integrated rate law after application of the initial condition of $q_t = 0$ at $t = 0$ from its non-linear
194 form given by Equation 8

$$195 \log(q_e - q_t) = \log q_e - \frac{k_1 t}{2.303} \quad (8)$$

196 where, q_e and q_t are the amounts of adsorbate adsorbed g/g at equilibrium time and at any
197 instant of time, t respectively, and $k_1 \text{ min}^{-1}$ is the rate constant of the pseudo first-order
198 adsorption operation.

199 3.5 Second order-kinetic model

200 The second order-kinetic model is shown in Equation 9; it is often used for chemical
201 reaction, in kinetics and chemical reaction engineering, but can also be applied for
202 adsorption processes [19].

$$203 \frac{1}{c_e} = k_2 t + \frac{1}{c_o} \quad (9)$$

204 3.6 Pseudo-second-order kinetics

205 Pseudo-first-order kinetics differs from a true first order equation in two ways: (i) the
206 parameter $k_1(q_e - q_t)$ does not represent the number of available sites, and (ii) the parameter
207 $\log(q_e)$ is an adjustable parameter and often found not to be equal to the intercept of the
208 plot of $\log(q_e - q_t)$ versus t , whereas in a true first order $\log q_e$ should be equal to the
209 intercept. In such cases, applicability of the second order kinetics should be tested with the
210 rate equation

$$211 \frac{t}{q_t} = \frac{1}{h} + \frac{t}{q_e} \quad (10)$$

212 Where $h = k_2 q_e^2$


213 3.7 Elovich model

214 Elovich model is applicable for chemisorption processes [18]. The equation is valid for
215 adsorption surface that is heterogeneous. Equation 11

$$216 q_t = \frac{1}{b} \ln(ab) + \frac{1}{b} \ln t \quad (11)$$


217 Where a is the initial adsorption rate (mg/gmin) and b is related to the extent of surface
218 coverage and the activation energy for chemisorption (g/mg). A plot of q_t against $\ln t$ gives a
219 straight line with a slope of $\frac{1}{b}$ and an intercept of $\frac{1}{b} \ln(ab)$ with correlation coefficients.

220

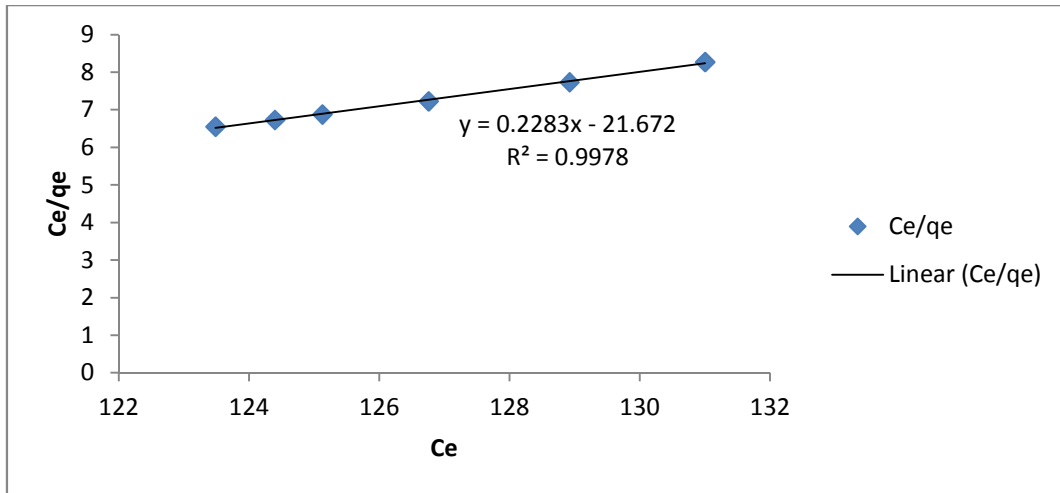

221
222 Figure 3: Composite Langmuir adsorption isotherm plot

223
224

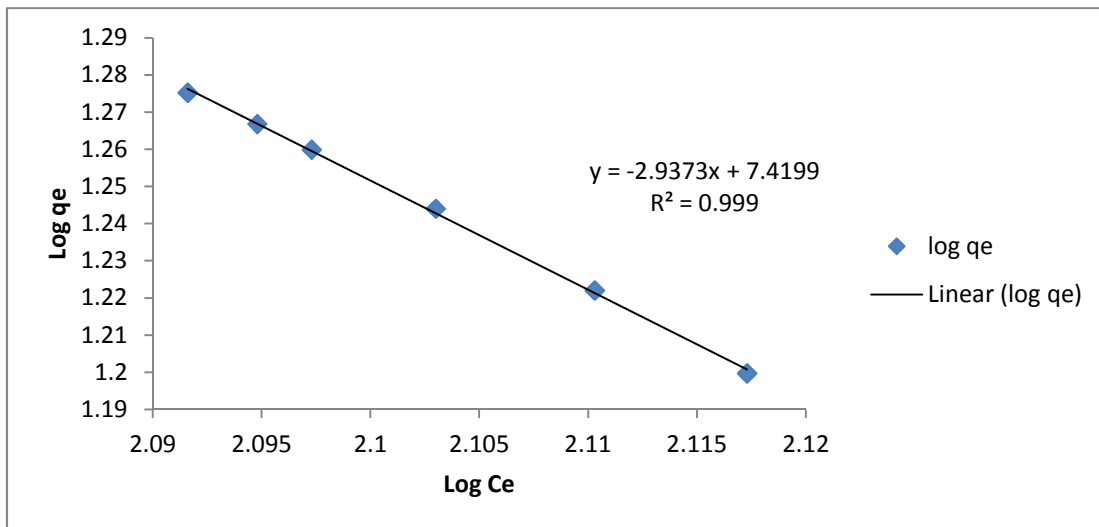

225
226 Figure 4: Composite Freundlich adsorption isotherm

227

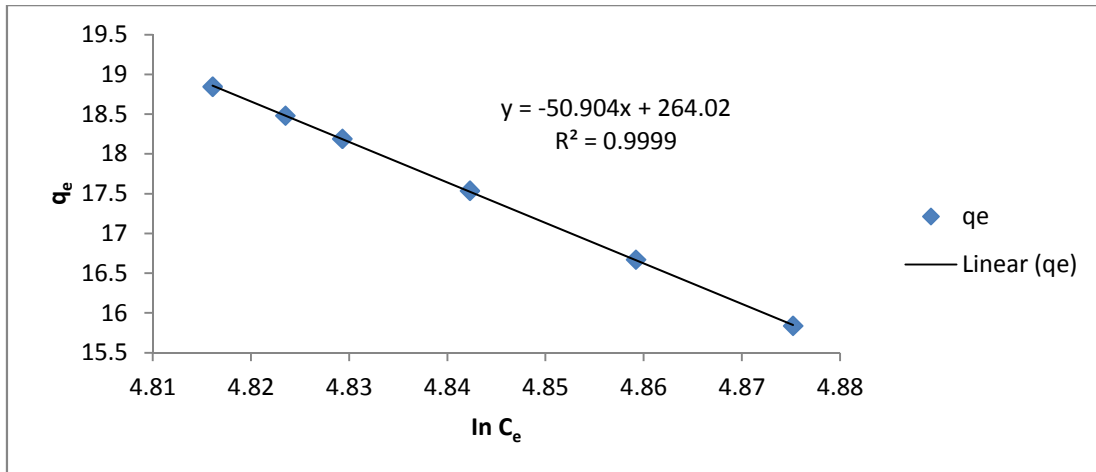



Figure 5: Composite Temkin adsorption isotherm plot

The heat of adsorption from Temkin b_T value -48.6715 kJ/mol is very low signifying that it is physisorption. Table 3 presents the adsorption isotherm studies parameters.


Table3: Composite adsorption isotherm value

Isotherm	Parameter	Value
Langmuir	b	0.03895
	R_L	0.1335
	R^2	0.9978
Freundlich	K_f	19.0546
	$1/n$	-2.9373
	R^2	0.999
Temkin	K_T	0.6885
	b_T	-48.6715
	R^2	0.9999

Only Temkin isotherm **best fits the** adsorption with highest R^2 value of 0.9999. Lagmuir R_L value was 0.1335 (favourable adsorption isotherm studies)

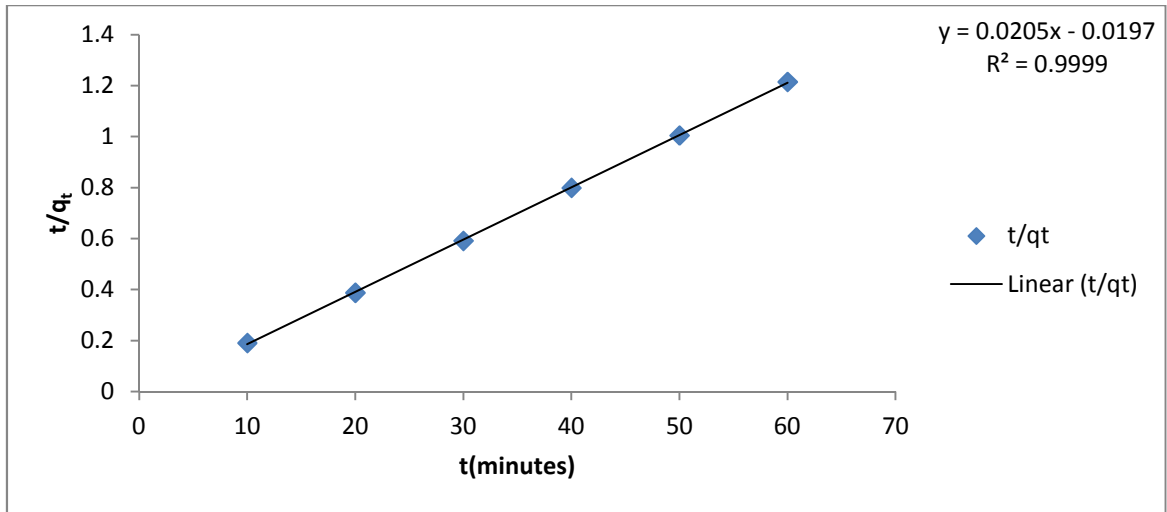

240
241 Figure 6: Composite pseudo-second order kinetic model
242

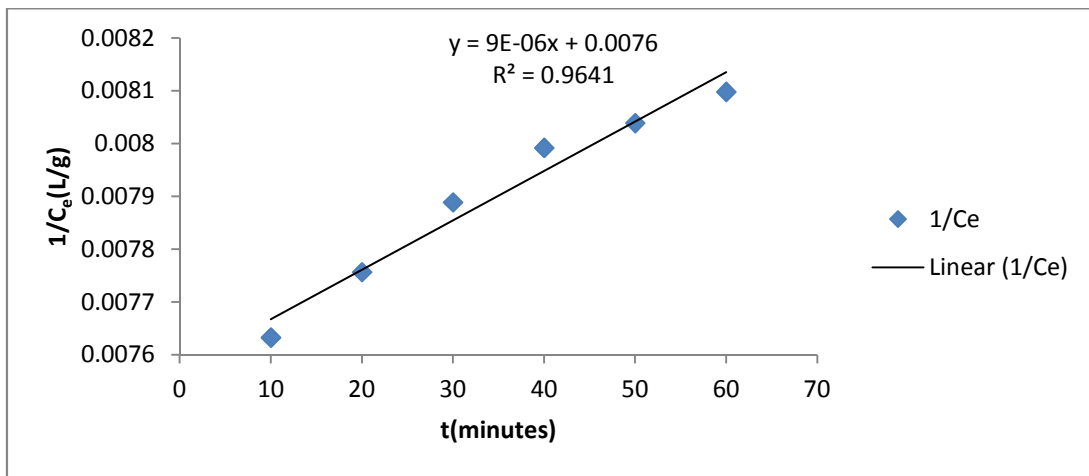

243
244 Figure 7: Composite second order kinetic model

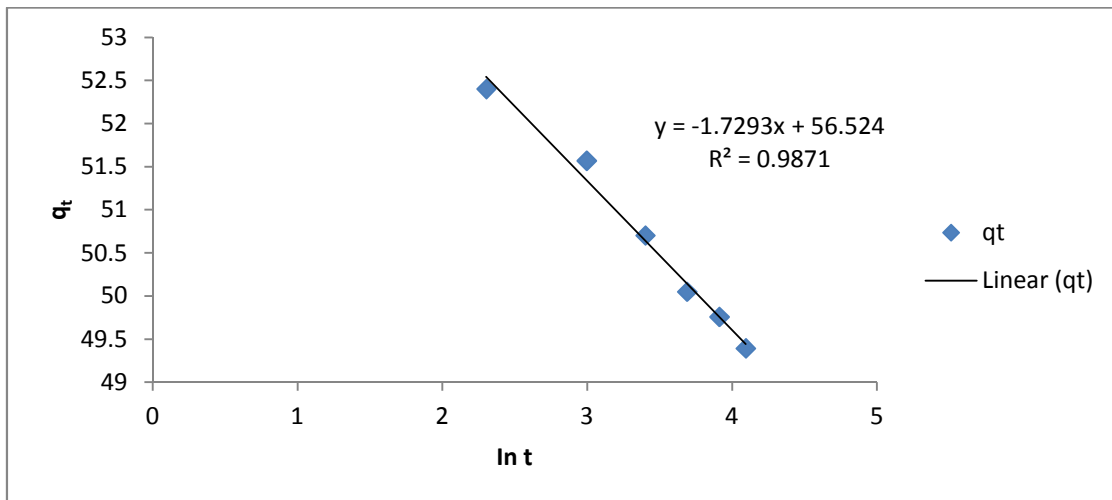


Figure 8: Composite Elovich kinetic model

Table 4.: Evaluated constants obtained from the tested kinetic model for the composite

Kinetic model	R ²	Intercept	K	Other constants
Second order	0.9641	0.0076	0.000000009	C _o = 131.579
Pseudo-second	0.9999	0.0197	0.0189	q _e = 50.7614
Elovich	0.9871	56.524	b = -0.5783	a = 1.1027E-14

4. CONCLUSION

Empirical model for the prediction of adsorption capacity of chitosan-rice husk silica ash was developed using response surface methodology. Analysis of variance indicated that the model was significant with $P = 0.0017$. Also optimum conditions were found to be 0.90 wt/wt chitosan/silica ratio, contact time of 5 min, and oil/water ratio of 0.25 v/v, this gave 20.66 g/g sorption capacity.

Temkin isotherm best fitted with R² value of 0.9999. The adsorption capacity from isotherm studies of the adsorbent obtained was 18.85 g/g. Also, the heat of adsorption b_T (-48.67 kJmol⁻¹) for the composite obtained from Temkin isotherm studies was low, indicating physisorption of adsorbents to the crude oil. Pseudo-second order kinetic model best fitted for composite with R² value 0.9999.

AUTHORS' CONTRIBUTIONS

G. G. Oseke performed the laboratory experiment, manage the literature searches and produced the first draft of the manuscript. M. T. Isa design the study and wrote the protocol. M. S. Galadima and A. O. Ameh performed the statistical analysis, and managed the analyses of the study. All authors read and approved the final manuscript.

REFERENCES

1. Aisien, F.A., Ebewe, R.O. and Hymore, F.K. (2003). *Potential Application of Recycled Rubber in Oil Pollution Control. Environmental Monitoring and Assessment.* 85, 175-190.
2. Zhao J, Xiao C F, Xu N K. *Diffusion and swelling behavior in treatment of oil spill to semi-interpenetrating polymer network from oil-absorptive fiber [J]. Journal of Journal of Central South University, Materials, Metallurgy, Chemical and Environmental Engineering, 2012, 33: 1197–1203.*
3. Reza Behnood Bagher, Anvaripour Nematollah Jaafarzadeh and Masoome Farasati. *Oil spill sorption using raw and acetylated sugarcane bagasse [J]. Journal of Dispersion Science and Technology, July 2016, Volume 23, Issue 7, pp 1618–1625*
4. Park I, Efimenko K, Sjöblom J, Genzer J. *Rapid removal of organics and oil spills from waters using silicone rubber "Sponges" [J]. Journal of Dispersion Science and Technology, 2009, 30: 318–327.*
5. Cojocaru C, Macoveanu M, Cretescu I. *Peat-based sorbents for the removal of oil spills from water surface: Application of artificial neural network modeling [J]. Colloids and Surfaces A: Physicochemical and Engineering Aspects, 2011, 384: 675–688.*

- 290 6. Annunciado T R, Sydenstricker T H D, Amico S C. *Experimental investigation of various*
 291 *vegetable fibers as sorbent materials for oil spills [J]. Marine Pollution Bulletin, 2005, 50:*
 292 *1340–1346.*
- 293 7. Karan C P, Rengasamy R S, Das D. *Oil spill clean-up by structured fibre assembly [J].*
 294 *Indian Journal of Fibre & Textile Research, 2011, 36: 190–200.*
- 295 8. Yang, H., Viola, D., Belinda, J., Rmbo, X. and Tony, S. *Rice husks and oil pollution.*
 296 Fall 2005, Roskilde University.
- 297 9. Isa, M.T., Ameh, A.O., Tijjani, M. and Adama, K.K. (2012) 'Extraction and
 298 Characterisation of Chitin and chitosan from Nigerian Shrimps', International Journal of
 299 Biological and chemical Sciences, vol. VI, no. 1, pp. 446-453.
- 300 10. Abdul A. A, Abdulrauf R. A, Enamul H. M. (2012). 'A Novel Sustainable Oil Spill Control
 301 Technology' Dept. of Petroleum Engineering, King Fahd University of Petroleum &
 302 Minerals, Dhahran 31261, Saudi Arabia
- 303 11. Kudaybergenov K.K., Ongarbayev E.K. and Mansurov Z.A.. (2012). 'Thermally treated
 304 rice husks for petroleum adsorption'
- 305 12. Ozturk N and Kavak D, (2005) Adsorption of boron from aqueous solutions using fly ash:
 306 batch and column studies, J. Hazard Mater., 127 81–88.
- 307 13. Amita Ummadisingua and Suresh Gupta. Characteristics and kinetic study of chitosan
 308 prepared from seafood industry waste for oil spills clean-up. J. 44 Taylor and Francis
 309 Group.
- 310 14. Tsai W.T., Chang C.Y., Wang S.Y., Chang C.F., Chien S.F., and Sun H. F., (2001),
 311 Utilization of agricultural waste corncob for the preparation of activated carbon, Journal
 312 of Environmental Science and Health, 5B(36), 677-686.
- 313 15. Hall, K.R., Egleton, L.C., Acrivos, A. and Vemeulen, T. (1966). *Pore and solid diffusion*
 314 *kinetics in fixed bed adsorption under constant pattern conditions.* Industrial and
 315 Chemical Engineering Fundamentals, 5, 212-223.
- 316 16. Temkin, M., & Pyzhev, J. A. V., (1940). *Kinetics of ammonia synthesis on promoted iron*
 317 *catalysts.* Acta Physiochim 12: 217-222.
- 318 17. M. Likon, M. Remškar, V. Ducman, and F. Švegl, "Populus seed fibers as a natural
 319 source for production of oil super absorbents," Journal of Environmental Management,
 320 vol. 114, pp. 158–167, 2013.
- 321 18. Zeldowitsch, J. (1934) Über den mechanismus der katalytischen oxydation von CO an
 322 MnO₂, Acta Physicochimica U.R.S.S., Vol. 1, Nos. 3–4, pp.449–464.
- 323 19. Li, YH, Wang, S, Luan, Z, Ding, J, Xu, C, Wu, D: Adsorption of Cadmium (II) from
 324 aqueous solution by surface oxidized carbon nanotubes. Carbon 41, 1057–1062 (2003)
- 325 20. Wang, H, Zhou, A, Peng, F, Yu, H, Yang, J: Mechanism study on adsorption of acidified
 326 multi-walled carbon nanotubes to Pb(II). J. Colloid Interface Sci. 316, 277–283 (2007)