

CHARACTERIZATION OF CASSAVA CYANIDE ON HEAT TREATED DUCTILE CAST IRON

Abstract

The present study explored the feasibility of using cassava leaves (CL) cyanide for surface strengthening of ductile cast irons through heat treatment. Dried cassava leaves were pulverized and sieved to 500µm particle size, the pulverized mass was mixed with BaCl₂ (energizer) at a ratio of 4:1 by weight. Standard ductile iron samples were produced using sand casting technique and the samples were heat treated at temperatures ranging from 750 to 900 °C in steps of 50 °C for the period of 3—5 hours. Characterization of the cyanided ductile iron was carried out using JEOL 7600F Field Emission Scanning Electron Microscope (SEM), Oxford X-Man (EDS), PANALYTICAL Empyrian X-Ray Diffractometer (XRD) and LECO ASTM E384 hardness tester. All analyses are carried out to ascertaining the formation of a case within the microstructure and phase formation owing to the heat treatment. The results revealed graphite nodules surrounded by pearlite in a ferrite matrix for the as-cast samples while the Pack Cyanided Cassava Leaves (PCCL) samples revealed dark structures (visible diffusion zone) at the edges of the samples containing carbides and appreciable amount of nitrides precipitation in the matrix (case) while the center reveals a ferritic/pearlite matrix (core).

keywords: Cassava, cyanide, ductile cast iron, surface strengthening

1.0 INTRODUCTION

Ductile cast iron is a versatile engineering material which has formed the subject of leading international research. Cast iron is finding increasing application through materials combination for engineering components and modification of properties such as mechanical properties (hardness, wear resistance, toughness, ductility, etc) and cost savings (Imasogie and Afonja, 2003). Cast iron is widely used in the manufacturing of components such as machine tool beds, cylinders, cams, and pistons. Ductile cast iron can be use as a good replacement for steels in applications that has comparable properties such as good machinability, good strength to toughness ratio, low cost of production, a high fatigue resistance, good fluidity, and good wear resistance (Gulzar et al., 2009)

Heat treatments are often applied to ductile iron to create or alter microstructures that improve some mechanical properties such as stress relieving annealing to achieve ferritic matrix structures, normalizing heat treatment for a pearlitic matrix structures, hardening to achieve martensitic structures, and surface strengthening produce hardened case with a tougher core matrix.

The aim of this study is to explore the feasibility of using cassava leave for surface strengthening of ductile iron by thermochemical method of diffusion using cassava leaf as source of cyanide. However, the choice of cassava leaves is based on the amount of cyanoglucoside content present in the leaves which generally ranges from 140 — 1000 ppm depending on the variety of the cassava, planting period and age, the condition of soil, fertilizer application, weather and other factors (Falade and Akingbala, 2011; Komolafe and Arawande 2011). In Nigeria, cassava is at present predominantly used for food and production of cassava remains low in terms of yield per hectare compared to its potential (AIIT 2008). Cassava may play a very significant role in surface strengthening since it produces relatively high amounts of Hydrogen cyanide, is easily hydrolysed and has a high content of dry matter (Kosugi *et al.*, 2009). The cellulosic and lignocellulosic content in cassava are also used as feed stocks in production of bio-ethanol (Londo *et al.*, 2009).

When cassava leaves are crushed, glucose and acetone cyanohydrin are hydrolysed in the presence of the enzyme *linamarase*, the acetone cyanohydrin decomposes rapidly in neutral or alkaline conditions liberating hydrogen cyanide and acetone as in Figure 1.



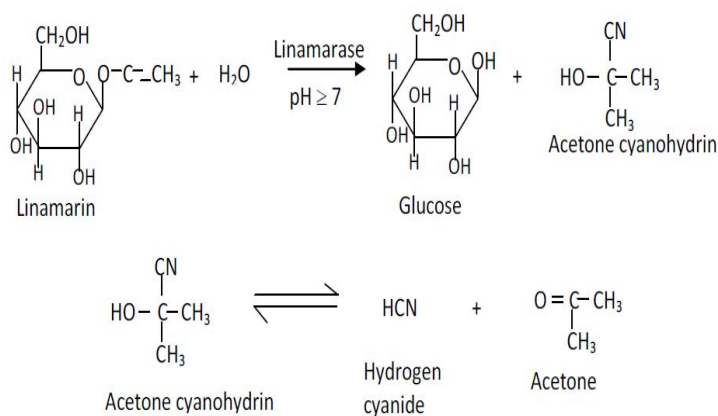


Figure 1: Enzymatic hydrolysis of linamarin (Orjiekwe *et al.*, 2013; Mburu *et al.*, 2012)

51 The following decomposition reactions are proposed for the intermediate-temperature pack
52 cyaniding process:



55 Where BaCl_2 is the energizer that is used in the intermediate-temperature treatment, the energizer
56 is added to increase the diffusion rate and case depth.

57 Also, the hydrogen cyanide (HCN) reacts with oxygen gas as follows:



59 The hydrogen cyanate (HCNO) formed decomposes at the surface of the iron according to the
60 following reaction:



62 The nitrogen (4N) formed diffuses interstitially into the iron surface during the pack cyaniding
63 process, similar to pack nitriding process (Li and Xiang, 2010).

64

65 **2.0 METHODOLOGY**

66 **2.1 Production of ductile cast iron**

67 The ductile iron used was cast by charging cast iron scraps, ductile iron returns, engine
68 sleeves, ferro-silicon alloy and ferro-silicon-magnesium, FeSiMg (5% Mg) alloy into a rotary
69 furnace. After melting was achieved between 1350 -1450 °C, inoculation with 2.4 wt. % of ferro-
70 silicon (FeSi) containing 75% Si was added to the melt to improve fluidity and the ejection of the
71 metal during dissolution of magnesium was prevented by means of special enclosed reaction
72 vessels for desulphurization and deoxidation treatment (Imasogie *et al.*, 2000). After tapping,
73 inoculation with 0.6 wt.% ferro-silicon containing 75% Si was carried out in the ladle and a
74 reaction chamber which holds the inoculants material in the running system was used to ensure
75 the uniform pouring of inoculants over the whole casting, to achieve a satisfying distribution of
76 spherical graphite and to maximize the efficiency of the inoculant material (Imasogie, 2002).

77 The melts were tapped and poured into a Y-block shaped mold, according to the ASTM A897M-
78 90 standard, followed by shakeout and appropriate sample preparation.

79 **2.2 Pack cyaniding Process**

The cassava leaves were harvested fresh, oven-dried at 70 °C (Famurewa and Emuekele, 2014) and pulverized to 500 µm using ball mills. Ductile iron samples were machined to a cylindrical shape of 20mm X 20mm, immersed in a mixed of pulverized cassava leaves (cyanide source) and Barium chloride BaCl₂ (energizer) at a ratio 4:2 by weight sealed in 50 mm × 500 mm × 500 mm mild steel boxes. The samples were subjected to heat-treatment process by varying the temperature from 750 °C to 900 °C in steps of 50 °C with holding time of 3 to 5 hrs in steps of 1 hr, total number of 64 samples was produced in all.

2.3 Heat Treatment of Ductile Iron

Heat treatments are applied to cause desired changes in the metallurgical structure and properties of metallic and alloy parts (Imosogie, 2001).

- a) Stress-relief heat treatment is the uniform heating of material to a suitable temperature below the (Ac₁) transformation range, holding at this temperature for a predetermined period of time and followed by uniform cooling (Callister, 2007). Treatment is used to relieve stresses (removal of residual stresses in iron) that remain locked in a structure as a consequence of manufacturing processes
- b) Annealing is a softening process in which ferrous materials are heated to a temperature above the transformation range (Ac₃) and, after being held for a sufficient time at this temperature, is cooled slowly in the furnace to a temperature below the transformation range (Ac₁).
- c) Hardening is the process of heating materials above the Ac₃ transformation, holding long enough to insure the attainment of uniform temperature and solution of carbon in the austenite, and the cooling rapidly in water (quenching).

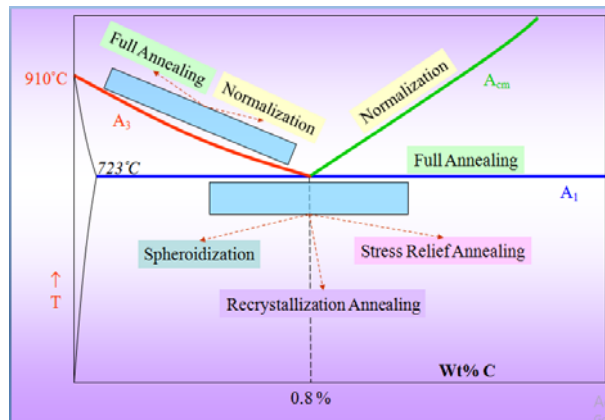


Figure: Comparison of time-temperature cycles for normalizing and full annealing (Romesch, 1993)

a) Austempering Heat Treatment is an isothermal transformation of ferrous materials by heating to austenitizing temperature above 800 °C with holding time long enough for the formation of fine grain austenite followed by quenching in a salt bath at temperature ranging from 260 to 400 °C for bainite transformation and finally cooling to room temperature (Yescas, *et al.*, 2001).

b) Surface hardening is a technique used to improve the wear resistance of engineering parts without affecting the materials interior properties. (Akinluwade *et al.*, 2013). There are two different approaches of surface hardening, namely Layer addition by the use of thin films, coatings, or hard-facings process and Surface modification attain by diffusion methods and selective hardening methods such as cyaniding, carbonitriding, nitriding, and nitrocarburizing processes.

2.4 Sample Preparation

The microstructures of pack cyanided samples were studied using the *Olympus BH-2* microscope with a digital camera. In preparing the specimens for microstructural studies, rough polishing was carried out on 240, 320, 400, and 600, 800 and 1200 SiC grit papers while final polishing was accomplished with alumina pastes of 1µm, and 0.5µm, respectively, etched with 2% nital.

3.0 Results and Discussion

3.1 Chemical Analysis

The chemical composition of ductile iron in the as-cast condition and alloying element was determined by Optical Emission Spectroscopy and is provided in Tables 1 and 2.

Table 1: chemical composition of the produced ductile cast iron

Elements	Fe	C	Si	Mn	P	Mg	S	Cr	Ni
Ductile Cast iron (%)	92.8	3.80	2.60	0.30	0.06	0.05	0.02	0.10	0.07

Table 2: Commercial Standard Grade Inoculants (Ferro-silicon, 75%) Composition

Elements	Si	P	S	Al	Fe
Composition (%)	75	0.02	0.05	2	Balance

The chemical composition of the produced ductile cast iron as presented in Table 1 revealed that the cast iron has the carbon equivalent value (CEV) of 4.68 which is hyper-eutectic iron and Figure 2 shows the micrograph of the as-cast ductile iron.

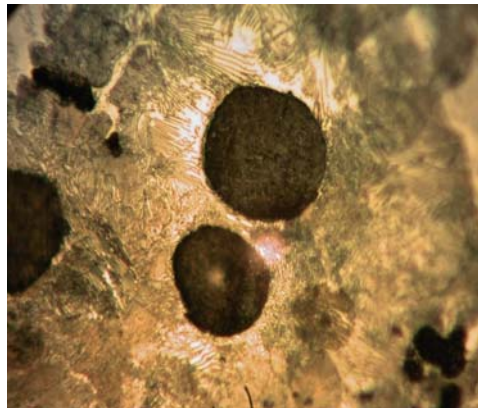


Figure 2: Micrograph of as-cast ductile iron showing graphite nodules and pearlite in a ferrite matrix with free carbide (light irregular particles), 2% nital etched x500.

The cyanide concentration analysis was carried out using the alkaline titration method (Famurewa and Emuekele, 2014). Cyanide concentration, morphology and elemental composition results are presented in Tables 3 and figure 3,

Table 3: Cyanide value present in the Experimental cassava leaf

S/N	Sample	Titre Value	Cyanide Content HCN (mg/kg)
1	TMS30572	6.038	20.38

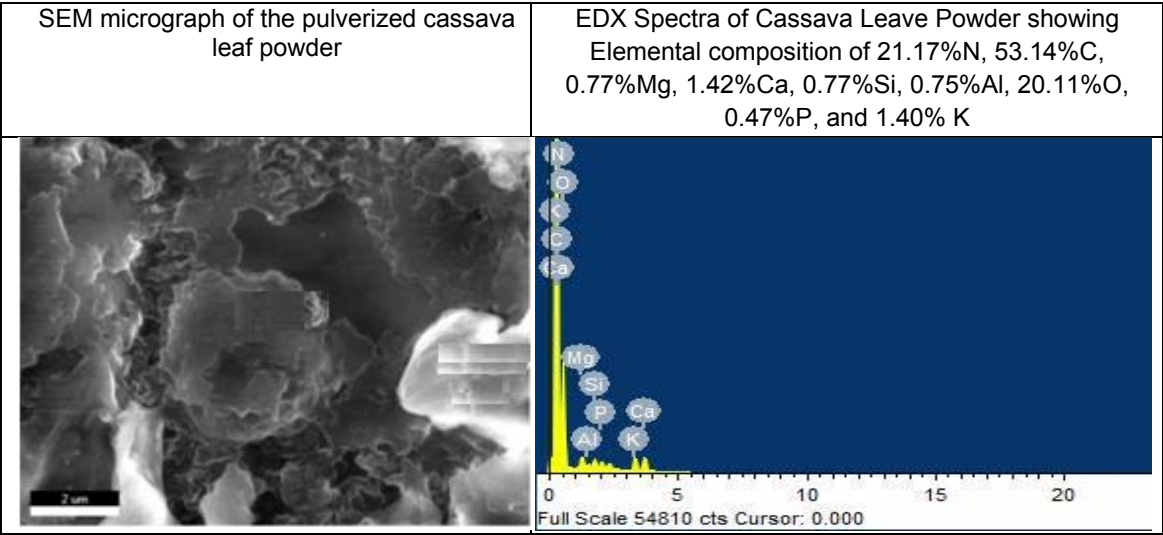


Figure 3: SEM and EDX of the cassava leaf powder

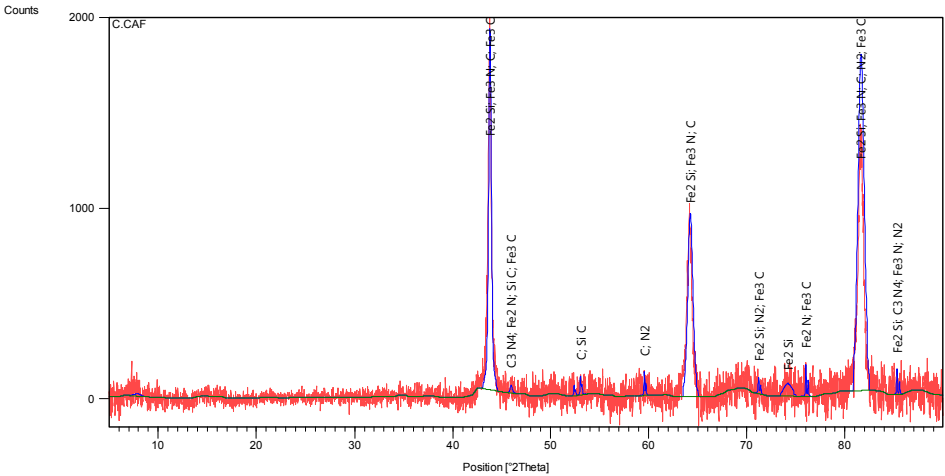


Figure 4a: XRD Pattern of PCCL ductile iron at 850°C for 5 hrs showing intense peak of Fe₃C, Fe₂Si, C phases at the core


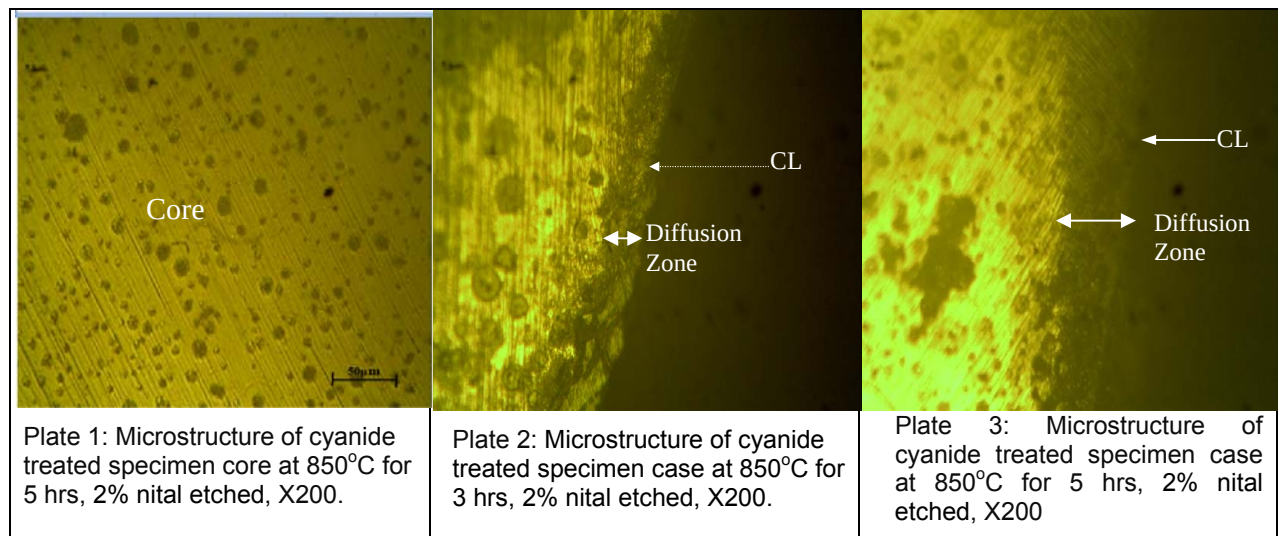


Figure 5: The microstructures of cassava leaves heat treated samples at 850°C. 200X

3.3 SEM Observation

The micrographs of the cyanided samples were studied using Scanning Electron Microscopy (SEM). Results obtained after heat treatments revealed a thin hard case with an enhanced hardness at the surface and from the surface inward, the hardness decreases toward the center core which denote the diffusion zone as illustrated in figure 6(a,b). During the cyaniding treatment process, the diffusion of carbon and nitrogen produced precipitates of carbide (FeC_3) and nitrides ($\epsilon\text{-Fe}_2\text{N}$ and $\gamma'\text{-Fe}_4\text{N}$) within the matrix of the sample as illustrated in figure 4. The microstructure of the core reveals a predominantly carbide phases (fig. 4a) while the cases reveals a combination of carbides, nitrides and an appreciable amount of cementite at the circumference of the sample (fig. 4b). The morphological changes in the SEM micrographs of the un-treated and treated samples against the hardness profile was illustrated in figure 6, this reveals decrease in hardness value from the edge (surface) toward the centre (core) of sample B, C and D respectively.

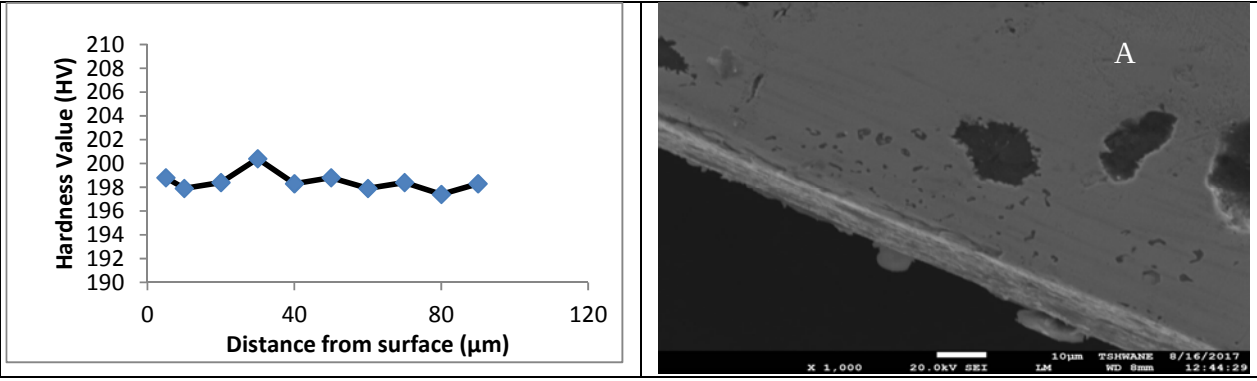

189 **Figure 6a: Table showing the correlation between Hardness profiles against SEM micrographs**
190 **of the un-treated sample**
191

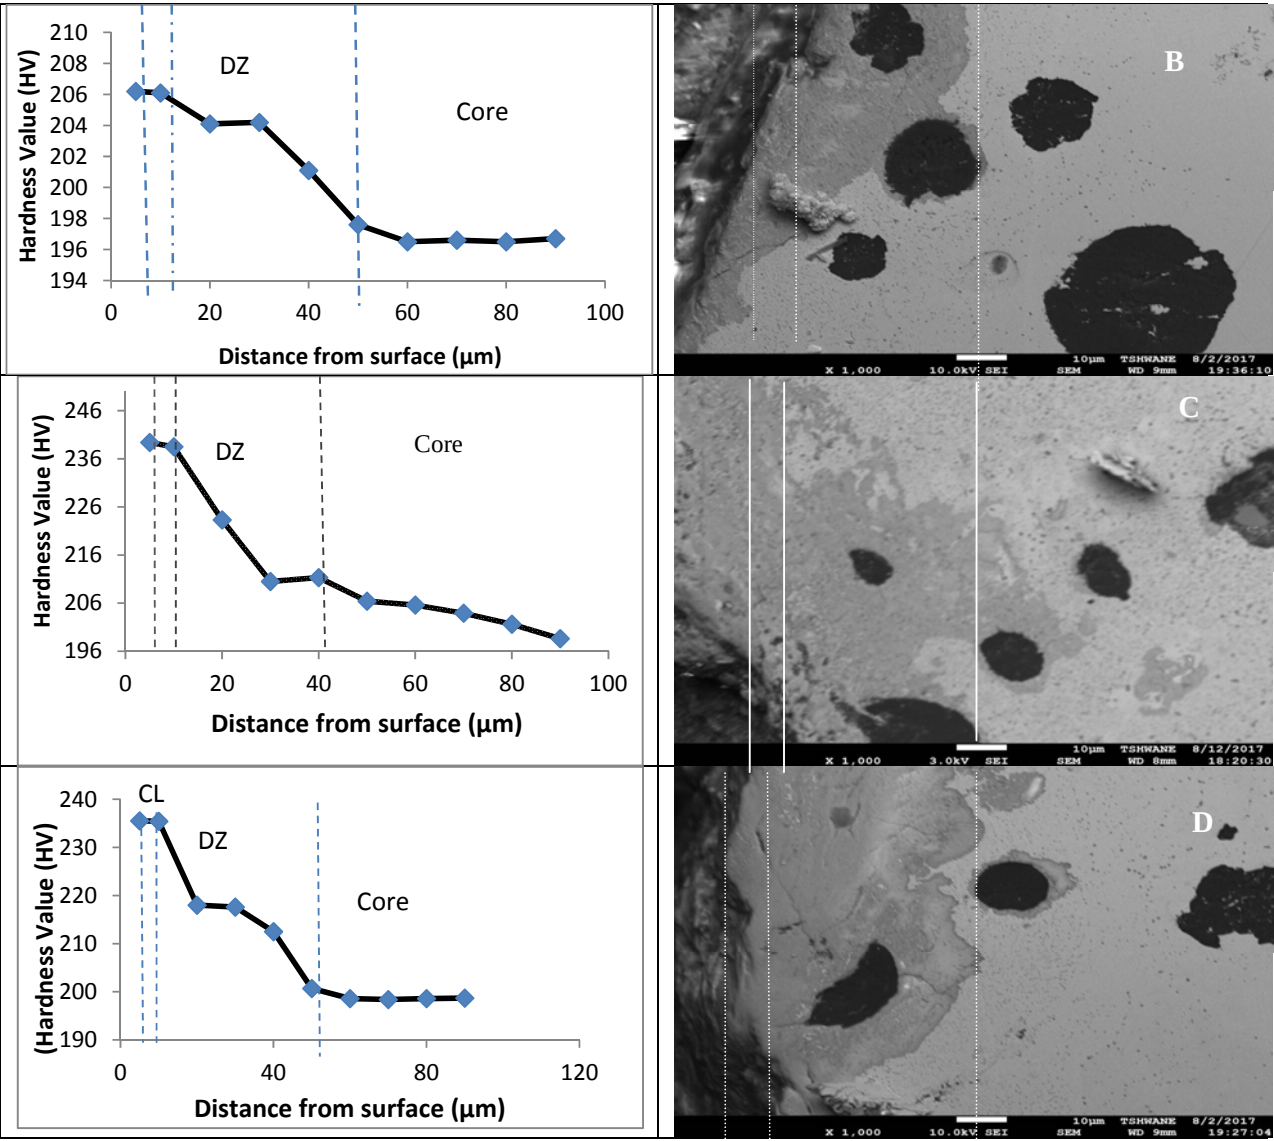


Figure 6b: Table showing the correlation between Hardness profiles against SEM micrographs of the treated cyanided samples

3.4 Compound layer thickness and diffusion zone depth

The compound layer thicknesses and diffusion zone depths of ductile iron were studied using the SEM micrographs cross-sectional structures as presented in figure 6. Figure 7 illustrates the relation between the thickness of the compound layer and the diffusion zone respectively, the figure reveals a progressive increase in the compound layer thickness of samples treated at 750°C with holding time of 3hrs to a thickness value of 9.2 μm while samples pack cyanided at 850°C with holding time of 5hrs has the highest compound layer value of 9.4 μm , this is expected due to the presence of carbides (Fe_3C), free carbon (C) and an appreciable amounts of ϵ -nitride, γ' -nitride (figure 4) at the surface (case) of the treated samples (Sample C, Fig. 6,) follow by decreases in compound layer thickness at 900°C the owing to decrease in saturated effect of the carbon and nitrogen diffusivity at high temperature.

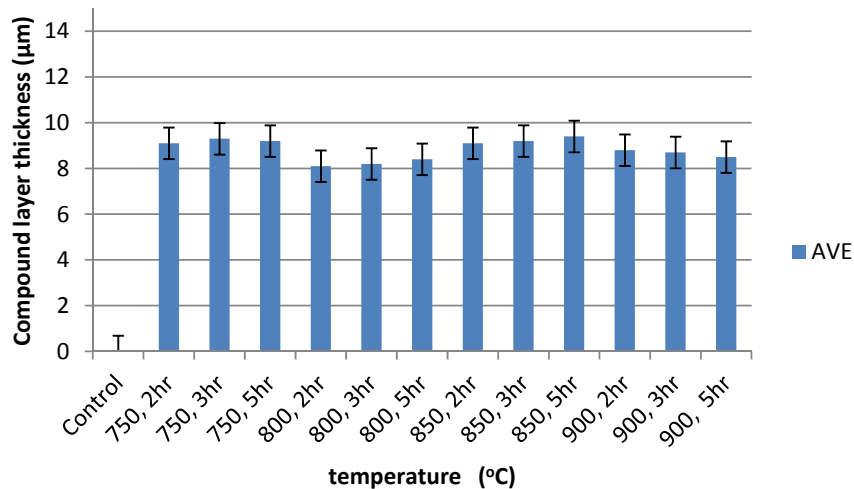


Figure 7: Compound layer and diffusion zone thickness of the pack cyanided cassava leaves samples

3.5 Hardness Test Result

The hardness results illustrated in figure 6 and figure 8 explains the hardness value of 198.4 HV at the case and 197.2 HV at the core was obtained for sample A (as-cast), sample B at 750 °C held for 3hrs reveals a hardness value of 207 HV at the case and 198 HV at the core, Sample C has a

hardness value of 235.3HV at the case and 197.6 HV at the core, while sample D reveals a hardness value of 242.6 HV was observed at the circumference (case) and 208.4 HV at the core at 850°C held for 5 hrs and a decrease to hardness value of 223.4 HV at the case and 209.6 HV at the core of sample D at 900°C held for 5hrs as illustrated in figure 6b. The increase in hardness is as a result of the presence of ϵ -nitrides at the compound layer consisting of Fe_2N and Fe_4N in figure 4b with reduction in hardness value at the core for the treated cassava cyanided samples respectively, This may be expected because at temperatures above the eutectic temperature, the ferrite iron will transform to austenite which encourages appreciable diffusion of carbon (C) and diminutive nitrogen (N) simultaneously into the matrix of the iron, depleting the 'dark' case structure and hence increasing the hardness. At temperatures above the A_{CM} line (Fig. 1), the degree of C diffusion is much higher than that of N; this is because carbon has high diffusivity at high temperature than nitrogen (Akinluwade *et al.*, 2013; Ampaw *et al.*, 2016). Thus, the optimum treatment condition experienced in this process was observed in the treated PCCL at a temperature of 850°C held for 5 hours (sample C) and at the boundaries of the sectioned specimen the increase in the hardness was due to the presence of carbides, significant nitrides and retained austenite within the matrix.

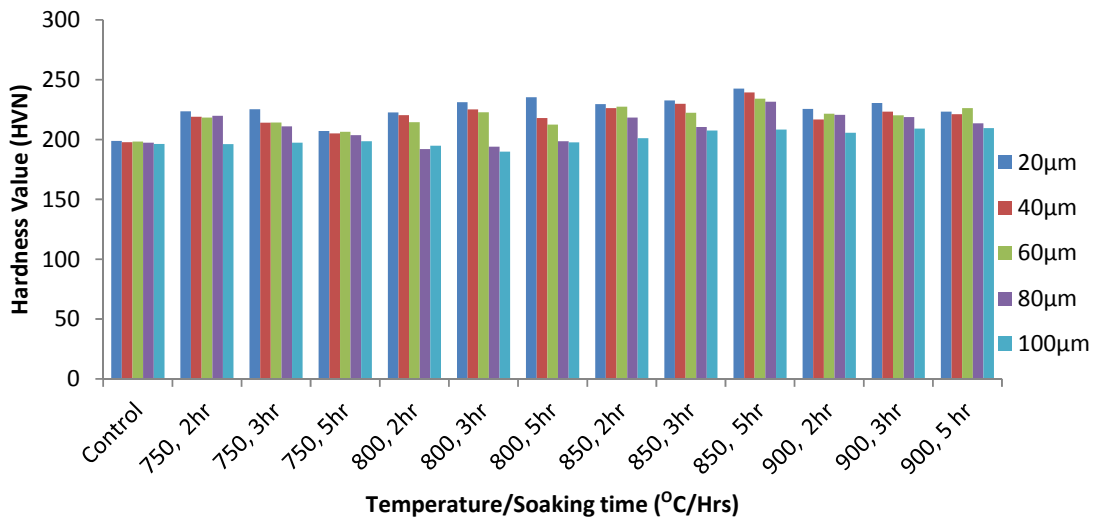


Figure 8: Case hardness with respect to the soaking time for the control and Cassava cyanided Samples

4.0 Conclusion

The cassava pack cyaniding method inturn shows an increase in the hardness values of ductile cast iron as a result of the interstitial diffusion of carbon as carbides (Fe_3C), retained Austenite and nitrogen as nitrides (Fe_4N , Fe_2N , N , and Fe_3N) at the surface of sample, this phenomenal indicate a potential use of cassava leaves for cast iron strengthening and the method also demonstrates potentials for increasing wear resistance of ductile iron components for an extensive application service life. Thus, harnessing cassava (tuber) for food and leaves (waste) for Engineering application such as surface strengthening of ductile iron components.

References

- Akinluwade K J., Adetunji A. R., Adeoye M, Umore L. E., Taiwo A. T., Kalu P., Rominiyi A., Isadare D. A., Soboyejo W., and Adewoye O. O. Light and Electron Microscopy Studies of the Visible Diffusion Zone of Mild Steel Pack Cyanided in Processed Cassava Leaves', *Journal of Materials Science and Engineering B* 3, 2013; (9); 567-570
- Ampaw E. K., Arthur E. K., Adewoye, O. O., Adetunji A. R., Olusunle S. O. O. and Soboyejo W. O., Carbonitriding "Pack cyaniding" Ductile Irons', *Advanced Materials Research*, 2016 ;1132; 330-348
- Callister (Jr.) W. D., Cast irons, *Materials Science and Engineering; An Introduction*, 7th ed., John Wiley and Sons Inc., New York. 2007; 366-377,
- Falade, K. O. and Akingbala, J. O. Utilization of cassava food', *Food reviews international*, 2011; 27; 51-58.
- Famurewa, J. A. V. and Emuekele, P.O. Cyanide reduction pattern of cassava (*manihot Esculenta*) as affected by variety and air velocity using fluidized bed dryer. *Afr. J. Food Sci. Technol.* 2014; 5(3):75-80
- Gulzar A., Akhter J. I., Ahmad M., Ali G., Mahmood M., Ajmal M., Microstructure evolution during surface alloying of ductile iron and austempered ductile iron by electron beam melting' *Applied Surface Science*. 2009; 255:8527-32.
- Imasogie, B. I, Afonja, A. A and Ali, J. A. Properties of Ductile Cast Iron Nodularised with a Multiple Calcium-Magnesium Based Master Alloy', *Materials Science and Technology*. 2000 ;16(2)194-201.
- Imasogie, B. I. and Afonja, A. A., Effect of Austempering on the Microstructure and Impact Toughness of Ductile Iron, *Materials Engineering*, 2003;14(3); 251-259.
- Imasogie, B. I. and Afonja, A. A., Effect of Austempering on the Microstructure and Impact Toughness of Ductile Iron, *Materials Engineering*, 2003; 14(3); 251-259.

269 Imasogie, B. I., Ali, J. A., Afonja, A. A. Properties of As Cast and Heat Treated Nodular Graphite Cast
 270 Irons Melts Treated with CaSi-CaF₂ Alloy. Scandinavian Journal of Metallurgy, 2001; 30(2); 91-
 271 102.

272 Komolafe E. A., Arawande A. O. Quality characteristics of garri produced in some selected cassava
 273 processing centers in Owo, Ondo State, Nigeria. Journal of Research in National Development.
 274 2010; 8(1).

275 Mburu F. W., Swaleh S., Njue W. Potential toxic levels of cyanide in cassava (*Manihot esculenta*
 276 Crantz) grown in Kenya'. African Journal of Food Science. 2012; 6 (16):416 - 420.

277 Orjiekwe C. L., Solola A., Iyen E. and Imade S. Determination of cyanogenic glucosides in cassava
 278 products sold in Okada, Edo State, Nigeria' African Journal of Food Science, Academic Journals,
 279 2013; 7(12);468-472

280 Pye D. Practical Nitriding and Ferritic Nitrocarburizing: ASM International; 2003.
 281
 282 Romesh C Sharma, 'Principles of Heat Treatment of Steels' *Materials Science and Engineering*, New
 283 Delhi: New Age International (P) Ltd, (1993), 150-155

284
 285 Wang J, Lin Y. H., Yan J. Zen Zhang Q., Huang R. B., Fan H. Y. Influence of Time on the
 286 microstructure of AISI 321 austenitic Stainless steel in salt bath nitriding. Surface and Coatings
 287 Technology. 2012; 206; 3399-404

288 Zaidao Yang The use of Nitriding to enhance wear resistance of cast iron and 4140 steel' Electronic
 289 Theses and Dissertation, <https://scholar.uwindsor.ca/etd/4717>. 2013.

290