

Temperature dependence of the dielectric constant and dielectric loss of composite materials HDPE + InP

ABSTRACT

In this paper presented study results of the temperature and frequency dependence of the dielectric constant and dissipation, dielectric loss in the temperature range 290-440 K and in the frequency range 25-10⁶ Hz, composite materials (high-density polyethylene) HDPE/InP with solid fillers. It was found that the increase in the percentage of filler in the matrix of InP leads to an increase of the dielectric constant and dielectric loss of the composites of HDPE / InP. It was revealed that by the variation of the amount of fillers and the effects of external factors can receive new composite materials with the required dielectric properties.

Keywords: *InP, HDPE, the dielectric constant, dielectric permittivity, dielectric loss, Maxwell-Wagner theory.*

1. INTRODUCTION

Creation of composite materials is one of the main directions in the development of advanced materials. In special, fine fillers in polyethylene contribute to the issue of novel structural components that can serve as charge carrier traps: interracial loosened absorption polymer layer near the airfoil of the filler. Filling polymers leads to alterations in the characteristics of high molecular structuring and packing density as superfine solid excipients may serve the adjustable seed crystals or imperfections in [1]. Fillers have a substantial impact on the mobility of the various kinetic units of the polymer and its relaxation time spectrum. Filler particles play the role of the center the structure and boundary layer of the polymer with the filler has a curious structure of saturation. These trapping centers with different activation energies, which are stabilized as a effect of electrons and is an improvement of the properties of the electro active polymer. It should be mentioned that depending on the nature, size, form and dispersion of the filler, the resulting resin composition can be electrically conductive or antistatic dielectric [2-3].

In recent years, as a filler often used advanced semiconductor compounds and materials have been received, presenting scientific and practical interest [4]. Let out that using filler ternary compounds of the type, $A^{III}B^{III}C_2^{VI}$, based on polyethylene can obtain new classes of electrical material with a record time of life [5].

We describe here the results of a survey of the dielectric properties of composite materials HDPE + x vol.% InP.

2. METHODS OF CALCULATION

By mechanically mixing powders of HDPE and semiconductor InP produced a homogeneous mix. This mix is then subjected to hot pressing under a force per unit area of 10 MPa at a temperature $T = 140^\circ\text{C}$ 15 minimum and quickly cooled, samples are prepared from a mix of a thickness of 120 μm between two fluoroplastic.

Samples for measurement of dielectric characteristics of the distribution according to the exemplary electric field were prepared in the form of discs 20 mm in diameter and about 120 mkm deep. Reliable electrical contact electrodes made of stainless steel with a diameter of 20 mm provide the use of electrodes made of extruded aluminum foil thickness of 9 mkm. Permittivity measurement - ϵ and dielectric loss tangent - $\text{tg}\delta$ conducted in the temperature range 290-440 K for linear growth temperature at a rate of 2.5°C/min using a setup block diagram is described in Figure 1. The frequency dependence of the dielectric constant - ϵ and dielectric loss tangent - $\text{tg}\delta$ carried out in the frequency range from 25 to 10^6 Hz, the amplitude of the test voltage 1B. Measurement error did not exceed 5%.

The measurements were posted out ϵ and $\text{tg}\delta$ using the bridge E8-7 at alternating current a frequency of 1

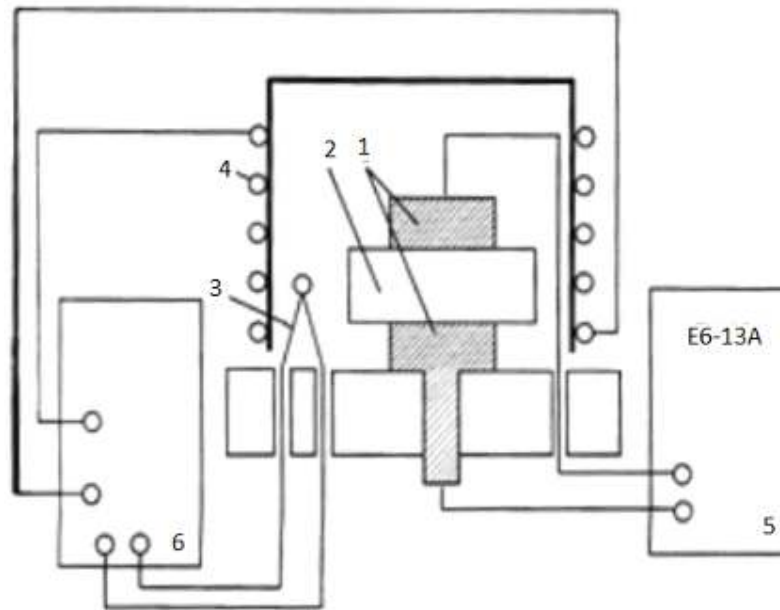


Fig. 1. Setting for the measurement of electrophysical parameters.

kHz and meter E7-20. Sample (2) is installed between two electrodes (1) in the measuring cell. The sample was then fired up using a heater box (4) which is risen in the chapeau of the cubicle. The sample temperature was recorded with a thermocouple (3) a system (6) which controls the heater (4). In measuring of ϵ the error is 5% and in measuring of $\text{tg}\delta$ the error is 9%.

3. RESULTS AND DISCUSSION

The outcomes of the study of temperature and frequency dependence of the dielectric permittivity and dielectric loss of HDPE + x vol. % in ($0 \leq x \leq 9$) are presented in Figures 2 and 3. Fig. 2 shows the temperature dependence of the dielectric permittivity of the dielectric loss of HDPE + x on. % InP in the temperature range 290-440 K. As shown schematically in Fig. 2a in the temperature range studied the dielectric permittivity with increasing temperature, typical for all investigated composites decreases almost linearly. With the growth in the volume content of the file is increasing in permittivity values, especially for high density polyethylene pure ϵ at room temperature was 2.07 (curve 1), the composite with the increase of 1 vol.% InP 2,5 (curve 2), 3 of the composite 3 vol.% InP 2,57 (curve 3), for about 5 composites. 5 vol.% InP 2,75 (curve 4), and 7 in. 7 vol.% InP 3,24 (curve 5). Characteristic changes in the investigated composites with increasing temperature with the

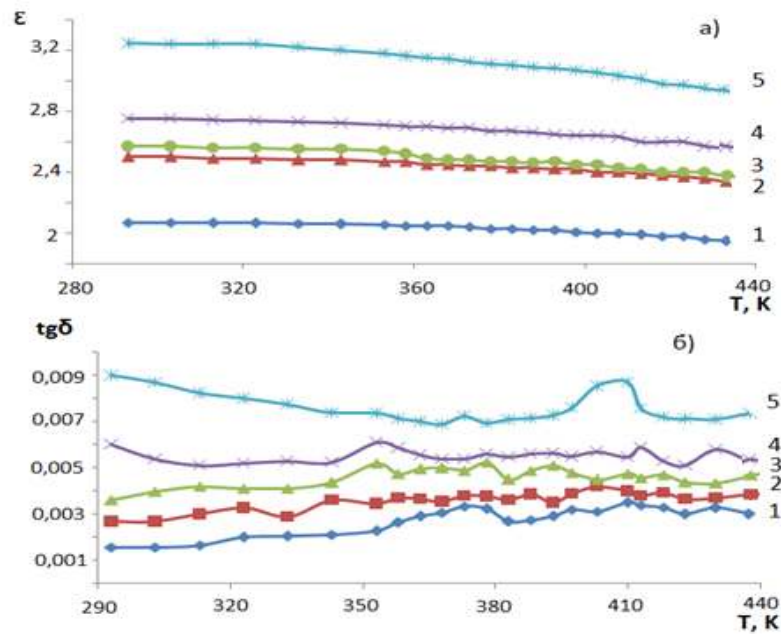


Fig.. 2. Temperature dependence of the dielectric permittivity (a) and dielectric loss tangent composite HDPE+x vol.% InP, here 1-x=0; 2-x=1; 3-x=3; 4-x=5; 5-x=7.

addition of InP (pic. 2 a) shows the influence of the isomerism carbonized kernel, on the dipole polarization. This behavior of ϵ with temperature indicates a decrease in M-phase polymer chain due to increase conformation set.

The terminations of the written report the temperature dependence of the dielectric loss tangent of composite materials HDPE + x vol.% InP is shown in Fig. 2b. As can be seen from Fig. 2b $\text{tg}\delta$ composites change with temperature is comparatively complicated. In particular, depending on the pure HDPE $\text{tg}\delta$ (T) (curve 1) increases $\text{tg}\delta$, at 378 K, a maximum diffuse, at least 383K, and weak peaks at a temperature of 395 K, 412 K and 430 K, respectively, and the minima at 390 K and 425K. For the composite with the increase of 1 vol.% InP in (curve 2) on the curve $\text{tg}\delta$ (T) at 323 K, 342 K, 390 K and 402K observed mild maxima and minima at 353 K and 391 K. For the composite with the addition of 3 vol.% InP in (curve 3) peaks were observed at temperatures of 353 K, 378 K and 390 K and 362 K minima at 380 and K. For the composite with the increase of 5 vol.% InP in curve $\text{tg}\delta$ (T) weak maxima are observed at 370 K and 410 K (curve 4). To this composite, a decrease $\text{tg}\delta$ from room temperature up to 380 K.

Fig. 3 shows the frequency dependence of the dielectric permittivity and dielectric loss of the composites of HDPE + x. vol.% InP in the frequency range 25-10⁶GHz.

As can be determined from the data in Fig. 3a investigated in the frequency range characteristic for all composites and pure ϵ HDPE virtually change with increasing frequency. A slight increase in ϵ , is observed at a frequency of about 10⁶ Hz.

Note that in this case, with increasing filler content InP bulk increases the magnitude of the dielectric constant. When the filler content in the composition of InP 0, 3, 5, 7 and 9 vol.% At the same frequency (25 Hz) the dielectric constant is 2.09, 2.55, 2.60, 3.2 and 3.29 respectively, and at a frequency of 5·10⁵ Hz, these values are 2.08, 2.51, 2.54, 3.09 and 3.19, respectively. Typical for all investigated composites since this frequency is increased ϵ .

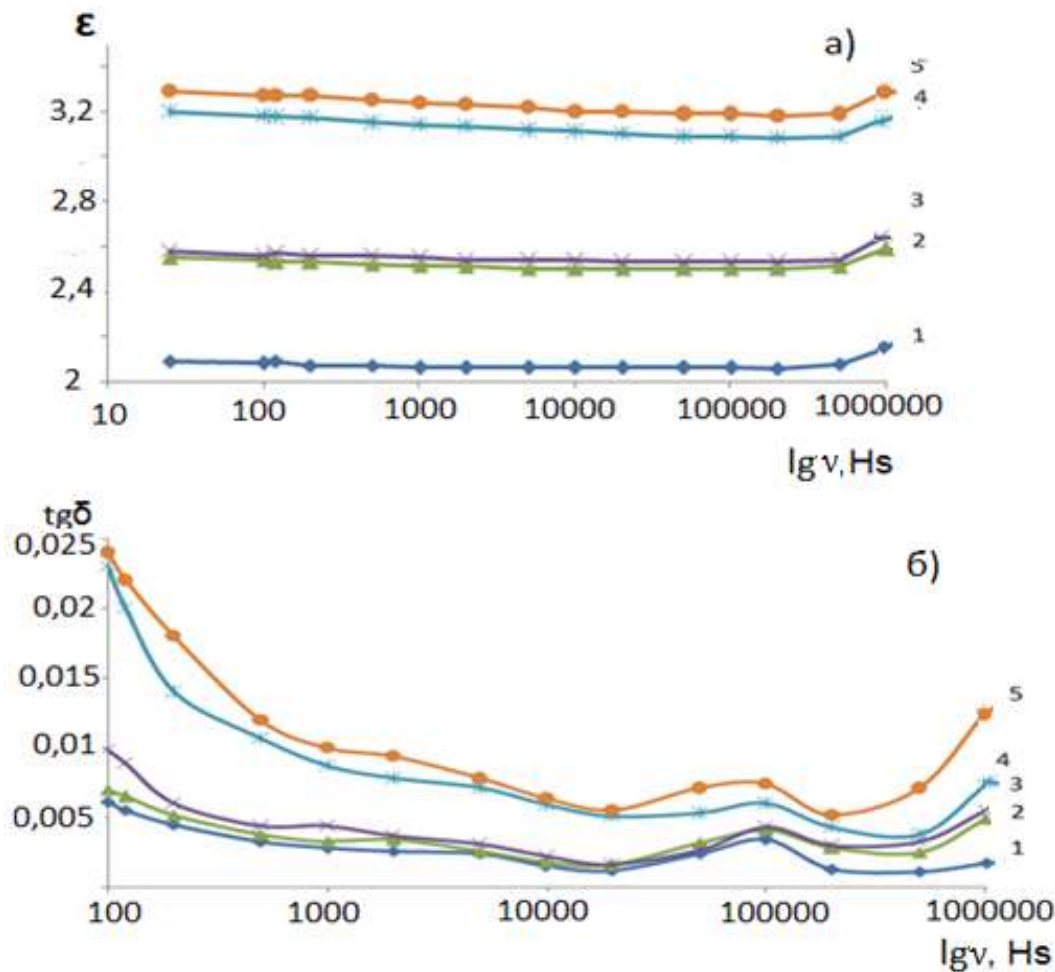


Fig. 3 Frequency dependence of the dielectric permittivity (a) and dielectric loss tangent composite HDPE+x vol.% InP, here 1- x=0; 2- x=1; 3- x=3; 4- x=5; 5- x=7.

The results of a study of the frequency dependence $\text{tg} \delta(\nu)$ are shown in Fig. 3b. As can be seen from Fig. 3b and in this case with increasing the filler content increases $\text{tg} \delta$, so at a frequency of 100 Hz, for composites with fillers 0: 3: 5, 7 and 9 in. % InP, $\text{tg} \delta$ is 0.0061: 0.0071: 0.0098 : 0.023 and 0.024, and at 106 Hz frequency of the same value becomes 0.0017: 0.0046: 0.0053: 0.0073 and 0.0126. For pure HDPE curve $\text{tg} \delta(\nu)$ at 10^5 Hz is observed variance $\text{tg} \delta(\nu)$ (curve 1). Maxima on the curves 2, 3, 4 and 5 are also observed at the same frequency. Notice that for the composites studied since the frequency of 10^5 Hz $\text{tg} \delta(\nu)$ increases.

Psychoanalysis of the results show that with the growth in the volume content of input is an increase in ϵ and $\text{tg} \delta$. This conduct of the dielectric parameters of composites HDPE + x vol.% InP is largely shaped by the Maxwell-Vagnerskoy polarization [3,6], the surface energy components. With an increment in the filler content of the composite structure becomes unstable and the InP particles form clusters whose surface are smaller than the entire surface of the particles comprising them. Increasing the number of clusters with increasing volume filler content decreases the dielectric layer between the particles and leads to increased electrical capacity and thus ϵ and $\text{tg} \delta$. It should be noted that conductivity of a filler of InP is constant. Only their distribution of volume of a matrix changes. And this fact has the defining impact on conductivity and dielectric permeability of composites, i.e. with an increase in the volume maintenance of fillers promotes their increase [7].

4. Conclusion

By researching of temperature dispersion of composites of Polyethylene of high density+xo6%InP it is revealed that the composite materials filled with semiconductor connection are very sensitive to temperature changes and can be of interest to practical application, for example, temperature sensors, etc.

REFERENCE

1. M.M.Guliyev, R.S.Ismailov The electrical properties of composites filled with oxide-dispersed. Electronic processing of textiles. №4, 2009, pp. 48-51.
2. G.E.Kuleshov, V.I.Suslyayev Dielectric permittivity and electrical conductivity of composite materials based on carbon nanostructures. Radio engineering and communication. №1, vol.31, 2014, pp.84-87.
3. N.M.Ushakov, A.N.Ulzutyev, I.D.Kosobudsky Thermo-electric properties of polymer composite nanomaterials based on copper-copper oxide in a matrix of high-density polyethylene. Sh. №12, vol.78, 2008, pp.65-69.
4. E.M.Gojayev, Kh.R.Ahmadova, S.I.Safarova, G.S.Djafarova, Sh.M.Mextiyeva Effect of Aluminum Nano-Particles on Microrelief and Dielectric Properties of PE+TiInSe₂. Open Journal of Inorganic Nonmetallic Materials. №5, 2015, pp.11-19.
5. E.M.Gojayev, A.M.Maharramov, S.S.Osmanova, M.M.Nureyev, E.A.Allahyarov Charge state of compositions based on polyethylene filled with the semiconductor. Electronic processing of materials. № 2, 2007, pp.84-88.
6. M.M.Guliyev, R.S.Ismailov The electrical properties of composites filled with oxide-dispersed. Electronic processing of materials. №4, 2009, pp. 48-51.
7. А.Г.Баннов, С.М.Шировская, электропроводность и диэлектрическая проницаемость эпоксидных композиционных материалов на базе нановолокнистого углерода. Международная научно – практическая конференция «современные техника и технологии» секция 12: наноматериалы, нанотехнологии и новая энергетика. С.381-383